



# Natural resistance of four Amazon woods submitted to xylophagous fungal infection under laboratory conditions

## Resistencia natural de cuatro maderas amazonas sometidas a hongos xilófagos en condiciones de laboratorio

Alisson Rodrigo Souza Reis<sup>1\*</sup>, Luciane Pereira Reis<sup>1</sup>, Miguel Alves Júnior<sup>2</sup>, Josiane Celerino de Carvalho<sup>3</sup>  
and Jhonata Ribeiro da Silva<sup>1</sup>

<sup>1</sup> Universidade Federal do Pará, Faculdade de Engenharia Florestal. Altamira, Pará, Brasil.

lucyanne\_reis@hotmail.com; deivisonvs@ufpa.br

\* Corresponding author. alissonreis@ufpa.br

<sup>2</sup> Universidade Federal do Pará, Faculdade de Engenharia Agrônômica. Altamira, Pará, Brasil.

alvesjr@ufpa.br

<sup>3</sup> Instituto Nacional de Pesquisas da Amazônia -INPA. Petrópolis, Manaus, Brasil.

josiane.celerino@gmail.com

### ABSTRACT

The present study aimed to assess the natural resistance of four Amazon tropical wood species, used in the production of sawn timber, against infection with xylophagous fungi. *Apuleia leiocarpa* (amarelão), *Dinizia excelsa* (angelim vermelho), *Vochysia maxima* (quaruba), and *Bagassa guianensis* (tatajuba) were selected to perform the accelerated laboratory test. These species were exposed to white rot xylophagous fungi *Pycnoporus sanguineus*, *Phanerochaete chrysosporium* and *Schizophyllum commune*, and to the brown rot fungus *Gloeophyllum abietinum*. The laboratory test was performed following the methodology and classification of the natural resistance of wood according to ASTM D2017-86 (American Society for Testing Materials). All species were classified as highly resistant to fungal attack; however, *V. maxima* lost the highest percentage of weight. Therefore, we recommend that *D. excelsa*, *A. leiocarpa*, and *B. guianensis* be used in the production of sawn timber since they exhibited lower weight loss in the presence of all the fungi tested during a period of 12 weeks.

KEYWORDS: biodeterioration, sawn timber, tropical woods.

### RESUMEN

El presente estudio tuvo como objetivo evaluar la resistencia natural de cuatro especies de madera tropical de la Amazonia utilizadas en la confección de listones sometidos al ataque de hongos xilófagos. Las especies seleccionadas para la prueba de laboratorio fueron: *Apuleia leiocarpa* (Vogel) J. F. Macbr, *Dinizia excelsa* Ducke, *Vochysia maxima* Ducke e *Bagassa guianensis* Aubl. Sometidas al ataque de hongos xilófagos de pudrición blanca *Pycnoporus sanguineus*, *Phanerochaete chrysosporium*, *Schizophyllum commune* y al hongo de pudrición parda *Gloeophyllum abietinum*. El ensayo de laboratorio siguió la metodología de clasificación de resistencia natural de madera de acuerdo con la norma ASTM D2017-86 de la American Society for Testing Materials. Todas las especies fueron clasificadas como altamente resistentes en relación al ataque de hongos; sin embargo, la especie *V. maxima* presentó mayor porcentaje de pérdida de masa. Ante esa situación se recomienda a las especies *D. excelsa*, *A. leiocarpa* e *B. guianensis* para la confección de piezas de listones, debido a que presentan menor pérdida de masa para todos los hongos evaluados en el período de 12 semanas.

PALABRAS CLAVE: biodeterioro, madera, maderas tropicales.

## INTRODUCTION

In 2014, round wood production in Brazil decreased by 3.2%, particularly in the states of Pará, Mato Grosso, and Rondônia, which together accounted for 73.8% of the national production (Instituto Brasileiro de Geografia e Estatística, 2016). The wood produced in Brazil fulfills a wide range of purposes, including applications in the pulp and paper industry, for furniture, wood-based panels' production, and in civil construction. Based on this information, in 2013, the Brazilian National Standards Organization (ABNT) published the norm NBR- 15575:2013, which established technical parameters and standards in building, improving the quality of the products industrially manufactured and creating specifications to guarantee increased safety and comfort.

Natural biodegradation of wood, which directly influences the safety of these products, can be examined using different techniques. These techniques are frequently used in wood-based panel studies, such as those performed by Mendes *et al.* (2014) on *Pinus taeda*, Mendes, Bortoletto Júnior, Garlet, De Almeida and Surdi, (2013) on *Acacia mangium* and Gonçalves, Brocco, Paes, Loiola and Lelis (2014) on oriented strand board (OSB) panels of *P. taeda*.

In products based on sawn timber from Amazon woods, these tests are scarcely performed because the natural density and durability of the wood is high; however, the woods have stains that indicate the start of biodegradation. Biodegradation begins with the spread of microorganisms on the surface of the wood, resulting in changes certain properties of the wood such as color or aesthetics (Sudár *et al.*, 2013).

According to Kirk and Cullen (1998), wood-decay fungi can be classified into three groups: white rot fungi, which can degrade the three components of the plant cell wall (cellulose, hemicellulose, and lignin); brown rot fungi, which can degrade the polysaccharide fractions (cellulose and hemicellulose); and soft rot fungi, which can slowly degrade both the polysaccharide fractions and the lignin.

Therefore, it is of utmost importance to assess Amazon wood species since this will contribute to a wider knowledge

on the subject and avoid potential loss and damages derived from the replacement of deteriorated woods.

## OBJECTIVES

The objective of the present study aimed to assess the natural resistance of four Amazon tropical wood species used in the production of sawn timber, against infection with xylophagous fungi.

## MATERIALS AND METHODS

### Local and selected species

The study was conducted in the Technology Laboratory at the Forest Engineering Faculty – Federal University of Pará. The assay was performed according to ASTM D2017-86 (American Society for Testing Materials [ASTM], 2005), with the following alterations:

- a) The test wood specimens were prepared to the following dimensions: 2 cm × 2 cm × 2 cm.
- b) The fungus was cultured in liquid media containing malt and distilled water.

A survey was conducted on the main timber companies and site offices in the municipality of Altamira-PA to identify the most-used species in sawn timber production; thus, four wood species were selected (Table 1). To confirm whether the samples collected belonged to the reported species, the samples were identified macroscopically with the aid of a magnifier and compared with the collection at the Technology Laboratory of the Federal University of Pará.

A total of 192 samples that were free of any type of defect such as wood knots, fissures, and cracks were prepared. The specimens were then sanded with sandpaper grit size no. 200 and 12 specimens were selected for each fungal species. Subsequently, each side of the sample (tangential, radial, and transverse) was identified with a number using a waterproof ink pen. In addition, 12 samples each were prepared for *Pinus* sp. and *Cecropia* sp., which were used as reference woods according to the norm.



TABLE 1. Wood species selected for the accelerated resistance test.

Scientific name	Common name	Family
<i>Apuleia leiocarpa</i> (Vogel) J.F. Macbr	Amarelão	Fabaceae
<i>Dinizia excelsa</i> Ducke	Angelim vermelho	Fabaceae
<i>Vochysia maxima</i> Ducke	Guaruba	Vochysiaceae
<i>Bagassa guianensis</i> Aubl.	Tatajuba	Moraceae

Moisture content in the test specimens was monitored in a group of five samples, which were representative of each wood species. First, the wet weight of the samples was obtained; subsequently, the samples were incubated at  $103\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$  until the weight of the samples was constant. Thus, it was possible to calculate the moisture content of the material analyzed.

Four species of wood-decay fungi were used, including three white rot fungi and one brown rot fungus, obtained from pure cultures of the Department of Plant Pathology, Federal University of Lavras, which were codified with specific names as described in Table 2.

TABLE 2: Fungal species used in the test.

Code	Species	Tipo Rot
PD01	<i>Pycnoporus sanguineus</i> (L. Fr.) Murrill	Blanco
PD14	<i>Phanerochaete chrysosporium</i> Burds	Blanco
PD21	<i>Schizophyllum commune</i> Fries	Blanco
PD63	<i>Gloeophyllum abietinum</i> (Bull.) P. Karst.	Marron

### Decay assay

The assay was performed at the Plant Pathology Laboratory in the Faculty of Agronomy Engineering of the Universidade Federal do Pará. We used 250-mL flasks (clear glass) with screw caps, containing 70 g of soil (red latosol), free of organic matter. Limestone had been previously added to the soil to raise the pH to 6.0.

A support plate of 2.5 cm × 2.5 cm × 0.5 cm was placed in each flask to allow the initial growth of the

fungus. Support plates of pinus (*Pinus* sp.) were used for the cultivation of *G. abietinum*, and plates of embauba (*Cecropia* sp.) were used for the cultivation of *P. sanguineus*, *Phanerochaete chrysosporium*, and *Schizophyllum commune* fungi. The flasks were autoclaved at  $121\text{ }^{\circ}\text{C}$  for 45 min. Then, each flask was inoculated with 3 mL of malt liquid media containing fragmented mycelia, which was directly placed over the support plate.

After inoculation, the flasks were placed in an incubator at  $27\text{ }^{\circ}\text{C}$  until the mycelium completely covered the support plate (2 weeks).

### Air conditioning and sterilization of the test specimens

The test specimens were acclimatized in an incubator at  $50\text{ }^{\circ}\text{C} \pm 1\text{ }^{\circ}\text{C}$  for 24 h, so that all results could be obtained under the same conditions. After air conditioning, the specimens were placed in a desiccator containing silica for approximately 10 min and were then weighed. Before the inoculation, the specimens were sterilized in an autoclave at  $121\text{ }^{\circ}\text{C}$  for 1 h.

### Inoculation, period of fungal attack, and removal of test specimens

The specimens were introduced aseptically to the flasks containing the fungus with the aid of tweezers. Three samples were added to each flask and maintained for 2 weeks. After the fungal attack period, the specimens were removed from the flasks and gently cleaned with a brush to remove mycelia that had accumulated on the surface of the samples. Thereafter, the specimens were acclimatized in an

incubator at  $50\text{ }^{\circ}\text{C} \pm 1\text{ }^{\circ}\text{C}$  for 24 h and weighed to obtain the final weight after the period of fungal infection.

### Assessment of weight loss

After the 12-week period, the degree of natural resistance of each wood specimen was assessed according to its weight loss.

Thus, we obtained the average weight loss values for the species under study and for the reference wood species *Pinus* sp. and *Cecropia* sp., to further assess the intensity of biodegradation.

The classification of the natural resistance of wood species was determined according to the norm ASTM D 2017 (Table 3).

### Statistical analyses

The results obtained regarding the weight loss of the wood specimens, expressed in percentage, were statistically analyzed. For the assessment, we used the factorial analysis of variance in a completely randomized experiment with two factors: fungi and wood species, with each of the factors having four levels. For each combination of fungus  $\times$  wood species, 12 completely randomized repetitions were performed. For multiple comparison of the means, Tukey's test was used at 5% probability.

## RESULTS AND DISCUSSION

### Wood-decay fungi attack

Faster growth and development was observed in the mycelia of the white rot fungi, with *Schizophyllum commune* (PD21) showing a greater development than the other species examined. On the other hand, *G. abietinum* (PD63) exhibited growth and rest periods, demonstrating overall slow growth (Fig. 1).

When analyzing the behavior of *P. sanguineus* and *Gloeophyllum trabeum*, Alves *et al.* (2006) observed faster development of *P. sanguineus* when compared with *G. trabeum* in six Amazon woods under study. Eaton and Hale (1993) reported that *G. trabeum* showed a slower development when compared to white rot fungi.

TABLE 3: Classification of the natural resistance of woods submitted to rot fungi attack under an accelerated laboratory test.

Weight Loss Average (%)	Classification
0–10	Highly resistant
11–24	Resistant
25–44	Moderately resistant
> 45	Slightly or nonresistant



FIGURE 1. Mycelial growth of *Pycnoporus sanguineus* (PD01), *Phanerochaete chrysosporium* (PD14), *Schizophyllum commune* (PD21) and *Gloeophyllum abietinum* (PD63) fungi, respectively.

According to Carvalho, Canilha, Ferraz and Milagres (2009), the white rot fungi are considered more efficient at wood biodegradation, since they are able to break down the three components of the plant cell wall (cellulose, hemicellulose, and lignin), whereas the brown rot fungi mainly degrade the polysaccharide fractions (cellulose and hemicellulose).

Eaton and Hale (1993) argued that the natural resistance of wood is dependent on the access routes available to fungi and the chemical composition of the wood, with the latter being a characteristic that varies substantially among species and within the same tree.

When analyzing the classification, all species in this study were considered highly resistant. Stangerlin, Da



Costa, Garlet and Pastore (2013) reported that the attack period of rot fungi, as described by the norm ASTM D2017, is not sufficient to be applied to the Amazon woods, which suggests that this parameter of the norm should be revised for tropical woods.

Table 4 shows the average weight loss in grams and as a percentage, together with the classification of natural resistance according to the norm ASTM D2017/86 of the four wood species, after exposure to attack by fungi PD01, PD14, PD21, and PD63.

The species *D. excelsa* showed lower weight loss than did the remaining wood species. This was also observed among all the fungi tested, with the fungus *P. sanguineus*

causing greater weight loss (1.20%) than the other fungi tested.

Alves *et al.* (2006) examined *Peltogyne paniculata* (purpleheart wood) and found that the fungi *Pycnoporus sanguineus* presented the lowest weight loss (4.88%) among the various fungal species analyzed in their study.

Analysis of *A. leiocarpa* and *B. guianensis* showed that these species lost similar amounts of weight for all the tested fungi, which was around 3%.

In contrast, *V. maxima* showed a higher percentage of weight loss with an average of 9.17% for all the fungi assessed. This could have occurred due to the low specific mass together with the type of parenchyma found in the

TABLE 4. Mean values of weight loss and classification of natural resistance in woods submitted to attack by *Pycnoporus sanguineus* (PD01), *Phanerochaete chrysosporium* (PD14), *Schizophyllum commune* (PD21) and *Gloeophyllum abietinum* (PD63) fungi.

Species	Fungi	Grams	%	Classification of Natural Resistance
<i>Dinizia excelsa</i>	PD01	0.0493	1.20	Highly Resistant
	PD14	0.0268	0.66	Highly Resistant
	PD21	0.0250	0.58	Highly Resistant
	PD63	0.0282	0.91	Highly Resistant
<i>Apuleia leiocarpa</i>	PD01	0.1148	4.23	Highly Resistant
	PD14	0.1059	3.49	Highly Resistant
	PD21	0.1060	3.67	Highly Resistant
	PD63	0.0917	3.11	Highly Resistant
<i>Bagassa guianensis</i>	PD01	0.0851	2.77	Highly Resistant
	PD14	0.1056	3.73	Highly Resistant
	PD21	0.0883	3.11	Highly Resistant
	PD63	0.0689	2.34	Highly Resistant
<i>Vochysia maxima</i>	PD01	0.2011	8.43	Highly Resistant
	PD14	0.2020	8.37	Highly Resistant
	PD21	0.2022	8.70	Highly Resistant
	PD63	0.2980	11.18	Highly Resistant
<i>Cecropia</i> sp.	PD01	0.7919	60.10	Nonresistant
	PD14	0.7871	60.73	Nonresistant
	PD21	1.109133	68.00	Nonresistant
	PD63	0.804933	62.50	Nonresistant
<i>Pinus</i> sp.	PD63	1.577983	28.12	Moderately resistant

species. According to Silva (2005), woods that are most resistant to the action of these organisms are those that have high specific mass, since they have a denser structure with a high content of substances such as tannins and lignin impregnating their cell walls. According to the same author, the abundance of parenchymal tissue provides low natural durability.

De Nadai, Castelo, Stargerlin and Magistrali (2013) reported that specific mass is not the main factor that provides natural durability to wood; however, this can be attributed to factors such as the content and type of extractives. Thus, it is necessary to analyze the wood extractives content to obtain more accurate data.

In contrast, among the reference woods used, the fungus *G. abietinum* did not have high ability for biodegradation in the pinus species, as the norm requires that the control species, *Pinus* sp. and *Cecropia* sp., should have weight loss greater than 50% in order to prove the fungus vigor. Nevertheless, the remaining white rot fungi showed good development, with an average of 62.83% for *Cecropia* sp.

Mendes *et al.* (2014) observed a weight loss in the reference woods of 50.76% in the cecropia wood caused by the fungus *Trametes versicolor* and of 53.33% in the pinus wood caused by the fungus *G. trabeum*.

Carneiro, Emmert, Sternadt, Mendes and Almeida (2009) reported an average weight loss of 0.60% when *B. guianensis* was tested. This value is well below those found in the present study for this wood species, which had a weight loss average of approximately 3% for the four fungi tested.

We observed that *V. maxima* showed the greatest weight loss for all the fungi tested, with the brown rot fungus contributing more to the weight loss as shown in Figure 2. This might be because this wood showed higher porosity, thus facilitating fungus penetration.

Lepage (1986) explained that, in general, brown rot causes a decrease in the physical characteristics of wood faster than does white rot. There was no difference between the averages of the fungi analyzed (Table 5); however, the averages of all the wood species tested were

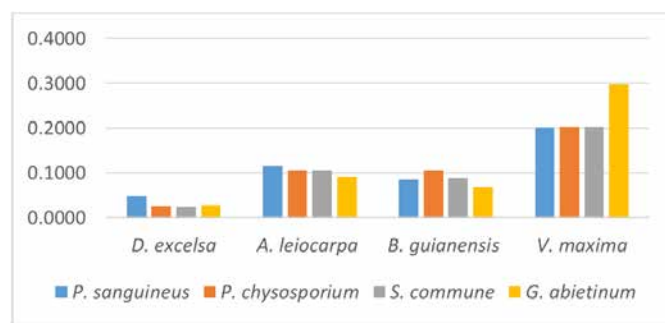


FIGURE 2. Weight loss (g) of the four wood species exposed to the four rot fungi.

significant, with the results demonstrating that the intensity of the fungal attack is associated with the wood species under attack.

Means followed by the same capital letter in the rows and lowercase in the columns do not differ by Tukey's test at 5% probability.

Weight loss in *D. excelsa*, *A. leiocarpa*, and *B. guianensis* were not statistically different; however, *D. excelsa* had the lowest average weight loss when compared with the remaining species.

When comparing the results obtained in an experiment with wood of different resistance classes exposed to xylophagous fungi. When attacked by the white rot fungus *Pycnoporus sanguineus*, the heartwood showed a weight loss lower than 10%, and could be classified as resistant. However, *V. maxima* showed a higher weight loss, demonstrating that it had lower resistance to the fungi tested.

In another study, Labat *et al.* (2000) studied *Erismia uncinatum*, which belongs to the same family as *V. maxima*, and they observed a weight loss of up to 0.3% following an incubation period of 6 weeks with the fungus *G. trabeum*.

## CONCLUSIONS

All four tested woods were found to be highly resistant to fungi. The woods *D. excelsa*, *A. leiocarpa* and *B. guianensis* showed lower weight loss, whereas *V. maxima*



TABLE 5. Comparison of weight loss averages of the species submitted to attack by fungi using Tukey's test.

<i>Species</i>					
Fungus	<i>D. excelsa</i>	<i>A. leocarpa</i>	<i>B. guianensis</i>	<i>V. maxima</i>	
PDO1	2.0501 cC	4.1077 bB	2.6176 bC	8.0558 aA	4.24352 A
PD14	1.2867 dD	3.8151 bB	2.3833 cC	9.1985 aA	4.02047 A
PD21	1.4147 dC	3.2218 bB	3.2685 bB	9.1985 aA	4.27587 A
PD63	0.9995 dC	3.2321bB	1.5273 cC	9.8569 aA	3.69864 A
AVERAGE	1.43773 d	3.59417 b	2.44919 c	9.04787a	
VC%	15.03				

showed the highest weight loss, which demonstrated that woods presenting greater density were the most resistant to rot caused by the fungi. We recommend that the *D. excelsa*, *A. leocarpa* and *B. guianensis* be used for sawn timber production.

## REFERENCES

- Alves, M. V. Da S., Da Costa, A. F., Espig, D. Da S. and Do Vale, A. T. (2006). Resistência natural de seis espécies de madeiras da região amazônica a fungos apodrecedores, em ensaios de laboratório. *Ciência Florestal*, 16(1), 17-26. doi: 10.5902/198050981884
- American Society for Testing Materials. (2005). *ASTM D2017-05, Standard test method of accelerated laboratory test of natural decay resistance of woods* (Withdrawn 2014), West Conshohocken, PA: ASTM International.
- Carneiro, J. S., Emmert, L., Sternadt, G. H., Mendes, J. C. and Almeida, G. F. (2009). Decay susceptibility of Amazon wood species from Brazil against white rot and brown rot decay fungi 10th EWLP, Stockholm, Sweden, August 25–28, 2008. *Holzforschung*, 63(6), 767-772. doi: 10.1515/HF.2009.119
- Carvalho, W., Canilha, L., Ferraz, A. and Milagres, A. M. F. (2009). Uma visão sobre a estrutura, composição e biodegradação da madeira. *Química Nova*, 32(8), 1-5. doi: 10.1590/S0100-40422009000800033
- De Nadai Corassa, J., Castelo, P. A. R., Stangerlin, D. M. and Magistrali, I. C. (2013). Durabilidade natural da madeira de quatro espécies florestais em ensaios de deterioração em campo. *Revista Ciência da Madeira (Brazilian Journal of Wood Science)*, 4(1), 108-117.
- Eaton, R. A. and Hale, M. D. (1993). *Wood: decay, pests and protection*. London: Chapman & Hall.
- Gonçalves, F. G., Brocco, V. F., Paes, J. B., Loiola, P. L. and Lelis, R. C. C. (2014). Resistência de painéis aglomerados de *Acacia mangium* Willd. Colados com ureia-formaldeído e taninos a organismos xilófagos. *Floresta e Ambiente*, 21(3), 409-416. doi: 10.1590/2179-8087.059113
- Instituto Brasileiro de geografia e estatística (2016). *Anuário estatístico do Brasil*. Retrieved from <http://biblioteca.ibge.gov.br/biblioteca/catalogo?view=detalhes&cid=720>.
- Kirk, T. K. and Cullen, D. (1998). Enzymology and molecular genetics of wood degradation by white-rot fungi. In R. A. Young and M. Akhtar (Eds.) *Environmentally friendly technologies for the pulp and paper industry* (pp. 273-307). New York: Wiley.
- Labat, G., Le Bayon, I., Gerard, J. and Amin, F. (2000). *The durability of wood polymer composites against fungi and insects*. Document presented in The International Research Group on Wood Preservation – IRG/WP 00-40161. Hawaii, USA.
- Lepage, E. S. (1986) Introdução. In Oliveira, A. M. F, De Lelis, A. T., Lopez, G. A. C., CHIMELO, J. P, Oliveira, L. C. de S., Cañedo, M. D., CAVALCANTE, M. S., Ielo, P. K. Y., Zanotto, P. A., Milano, S. *Manual de preservação de*

- madeiras* (vol. 01, pp. 1 -6). São Paulo: Instituto de Pesquisa Tecnológica de São Paulo.
- Mendes, R. F., Bortoletto Júnior, G., Garlet, A., De Almeida, N. F. and Surdi, P. G. (2013). Resistência ao ataque de fungos apodrecedores em painéis OSB termicamente tratados. *Cerne*, 19(4), 551-557. doi: 10.1590/S010477602013000400004
- Mendes, R. F., Bortoletto Júnior, G., Garlet, A., Vidal, J. M., De Almeida, N. F. and Jankowsky, I. P. (2014). Resistência de painéis compensados de *Pinus taeda* tratados com preservantes ao ataque de fungos xilófagos. *Cerne*, 20(1), 105-112. doi: 10.1590/S0104-77602014000100014
- Silva, J. C. (2005). *Anatomia da madeira e suas implicações tecnológicas*. Viçosa, Minas Gerais, Brasil: Universidade Federal de Viçosa, Departamento de Engenharia Florestal.
- Stangerlin, D. M., Da Costa, A. F., Garlet, A. and Pastore, T. C. M. (2013). Resistência natural da madeira de três espécies amazônicas submetidas ao ataque de fungos apodrecedores. *Revista Ciência da Madeira (Brazilian Journal of Wood Science)*, 4(1), 15-32.
- Sudár, A., López, M. J., Keledi, G., Vargas-García, M. C., Suárez-Estrella, F., Moreno, J., Burgstaller, C. and Pukán-szky, B. (2013). Ecotoxicity and fungal deterioration of recycled polypropylene/wood composites: Effect of wood content and coupling. *Chemosphere*, 93(2), 408-414. doi: 10.1016/j.chemosphere.2013.05.019

Received: 26 June 2016.

Accepted: 31 March 2017.

This paper must be cited as:

Reis, A. R. S., Reis, L. P., Alves Júnior, M., de Carvalho, J. C. and de Souza, D. V. (2017). Natural resistance of four Amazon woods submitted to xylophagous fungal infection under laboratory conditions. *Madera y Bosques*, 23(2), 155-162. doi:10.21829/myb.2017.232968