

# Monitoring via Infrared Spectrometry and Rheometry of a Vulcanization-Like Process of Chewing Gum Waste

## Monitoreo por espectrometría infrarroja y reometría de un proceso similar a la vulcanización de los desechos de goma de mascar

Isabel Cristina Castellanos<sup>1</sup>, Carolina Luque<sup>2</sup>, Eliseo Avella<sup>3</sup>, Stiven Huertas<sup>4</sup>, Mischel Toro<sup>5</sup>, and Daniel Rojas<sup>6</sup>

### ABSTRACT

Once chewed, chewing gum becomes a disposable and non-degradable cumulative residue that causes environmental, economic, and social problems. Collecting and treating chewing gum waste until its properties are adapted for some profitable use will generate environmental and economic savings. In this work, chewing gum waste was collected, sanitized, and subjected to a laboratory-scale rubber vulcanization-like process with sulfur. The evolution of the process was monitored via sequential measurements of torque and the acquisition of a series of ATR-FTIR spectra on the raw and resulting material of aliquots isolated from the reaction medium every 10 minutes for 4 hours. The absorbance values of the signals in the series of ATR-FTIR spectra were normalized and subjected to a descriptive statistical analysis, which allowed detecting intensity variations in bands attributed to carboxylate, as well as a slight decrease in the intensity of the bands attributed to hydroxyl, carbonyl, methylene in alpha to carbonyl, and other CHn groups in aliphatic fragments. These intensity changes and the trend of rheometric measurements during the process (vulcanization curve) evidenced that chewing gum waste did indeed react. Its vulcanization process had an absolute cross-linking maximum 5,15 minutes into the process and caused a remarkable increase in the torque of the resulting material; the Shore A hardness changed from 20 to 95 units, and the density varied from 1 280 to 1 510 kg/m<sup>3</sup>. These findings hint at an alternative treatment to reduce environmental pollution and revalue chewing gum waste.

**Keywords:** chewing gum waste, vulcanization, rheometry, mid-infrared, ATR-FTIR spectroscopy

### RESUMEN

Una vez masticada, la goma de mascar se convierte en un residuo acumulativo desechable y no degradable que causa problemas ambientales, económicos y sociales. Recoger y tratar los desechos de goma de mascar hasta que sus propiedades se adapten a un uso rentable generará ahorros ambientales y económicos. En este trabajo se recogieron y desinfectaron desechos de goma de mascar, y se los sometió a un proceso similar a la vulcanización de caucho con azufre a escala de laboratorio. La evolución del proceso se monitoreó mediante mediciones secuenciales de torque y la adquisición de una serie de espectros ATR-FTIR de la materia prima y el material resultante de alícuotas aisladas del medio de reacción cada 10 minutos durante 4 horas. Los valores de absorbancia de las señales en la serie de espectros ATR-FTIR se normalizaron y se sometieron a un análisis estadístico descriptivo que permitió detectar variaciones de intensidad en bandas atribuidas al carboxilato, así como una ligera disminución en la intensidad de las bandas atribuidas a hidroxilo, carbonilo, metileno en alfa a carbonilo y otros grupos CHn en fragmentos alifáticos. Estos cambios de intensidad y la tendencia de las medidas reométricas durante el proceso (curva de vulcanización) evidenciaron que los residuos de goma de mascar en efecto reaccionaron. Su vulcanización tuvo un máximo absoluto de entrecruzamiento a los 5,15 minutos de proceso y causó un aumento notable en el torque del material resultante; la dureza Shore A cambió de 20 a 95 unidades, y la densidad varió de 1 280 a 1 510 kg/m<sup>3</sup>. Estos hallazgos sugieren un tratamiento alternativo para reducir la contaminación ambiental y revalorizar los desechos de goma de mascar.

**Palabras clave:** desechos de goma de mascar, vulcanización, reometría, infrarrojo medio, espectroscopía ATR-FTIR.

**Received:** November 12th 2021

**Accepted:** September 09th 2022

### Introduction

Chewing gum is a popular product around the world, and its consumption has been steadily increasing. Several studies claim that chewing gum has beneficial effects on oral health, weight control, and stress relief, among others, and it has even been proposed as an efficient mechanism for medication delivery (Takahashi *et al.*, 2003; Jacobsen *et al.*, 2004; Potineni, 2007; Thivya *et al.*, 2021; Tijani *et al.*, 2022). However, its insoluble fraction can not be digested by the consumer, and it is discarded to the environment as a waste. Around the world, about 250 000 tons of environmentally

<sup>1</sup> Chemist, Universidad Nacional de Colombia, Bogotá. MSc Biochemistry, Universidad Nacional de Colombia, Bogotá. Affiliation: Associate Professor, Universidad EAN, Faculty of Engineering, Department of Basic Sciences, Colombia. E-mail: iccastellan@universidadean.edu.co

<sup>2</sup> Bachelor in Mathematics, Universidad Pedagógica Nacional de Colombia, Bogotá. Specialist in Statistics, Universidad Nacional de Colombia, Bogotá. MSc Applied Statistics, Universidad Santo Tomás, Bogotá. Affiliation: Associate Professor, Universidad EAN, Faculty of Engineering, Department of Basic Sciences, Colombia. E-mail: cluque2.d@universidadean.edu.co

<sup>3</sup> Chemist, Universidad Nacional de Colombia, Bogotá. ScD Chemistry, Universidad Nacional de Colombia, Bogotá. Affiliation: Associate Professor, Universidad Nacional de Colombia, Faculty of Sciences, Department of Chemistry, APRENA research group, Bogotá, Colombia. E-mail: eavellamo@unal.edu.co

<sup>4</sup> Chemical engineer, Universidad EAN, Bogotá. Affiliation: Universidad EAN, Faculty of Engineering, Bogotá, Colombia. E-mail:

hazardous chewing gum waste are generated per year, according to Euromonitor International (Roy, 2021).

Chewing gum waste is an environmental problem, as currently available chewing gums are products made of substantially non-degradable elastomer (Roy, 2021). An important amount of chewed gum ends up on the ground, carrying harmful toxins and microorganisms (Saber *et al.*, 2018) that can severely affect the health of any living being upon contact or by accidental or systematic ingestion. All of this implies environmental and economic costs that the inhabitants and the planet must pay.

This waste also poses an economic problem. City authorities and the people responsible for waste management must work hard to remove all of the chewed gum thrown to the environment. Such efforts are costly and not completely successful. The removal of each bit of chewing gum thrown onto the pavement costs more than three times the average price of a piece of gum (Logan and Rudolfs, 1947; Oosthuizen *et al.*, 2022). For example, in 2012, London spent more than £3 per piece of gum removed from the pavement, and three months steam-cleaning the 300000 pieces of gum that were thrown in an area of less than two miles of a street during the Olympic Games, while the consumer of such quantity of gum bought each piece for just a nickel, and threw that waste in a short period of time (BBC, 2010).

According to reports in The Telegraph (Rudgard, 2018) and The Guardian (Carter, 2005), governmental environmental protection entities of different countries charge taxes to the whole supply chain for single-use plastics (such as plastic bags) in order to diminish harms for the environment. It has already been considered that taxes to chewing gum consumption should be implemented as a way to recover some of the resources spent cleaning the gum waste.

Chewing gum waste also represents a social problem because it substantially decreases the utility and aesthetic value of public places (Simonek, 2011), generating untidiness and discomfort, as well as promoting adverse social behavior in the population. Among the tentative strategies to reduce the amount of chewing gum waste thrown onto the streets, some chewing gum waste collection campaigns have been proposed, as well as the use of improved cleaning methods (Liu and Jiang, 2003), the incorporation of anti-sticking agents into chewing gum formulations (Sozzi and Del Visco, 2011; Bullus, 2017), the production of bio-chewing Gum (Ribadeau-Dumas and Mentink, 2004; Palabiyik *et al.*, 2018; Saber *et al.*, 2018), the making of wraps for their hygienic disposal (Simonek, 2011), and their use as a filling in the formulation of plastic blends useful for manufacturing chewing gum waste collection containers (Bullus, 2017). The latter implies having to throw the chewed gum into special containers, rather than into ordinary trash bins without any appeal for the consumer. However, none of these strategies has contributed significantly to solving the pollution problem.

After the chewing, the base gum remains as a non-degradable residue. This is the main ingredient that manufacturers keep as reserved information (which is commonly not shared or declared). The base gum is a supremely soft food-grade chewable plastic made of polymers, plasticizers, and resins, which is not biodegradable. In the United States, Butadiene-styrene

rubber, Isobutylene-isoprene copolymer (butyl rubber), paraffins (obtained by Fischer-Tropsch process), natural or synthetic petroleum waxes, polyethylene, polyisobutylene, and polyvinyl acetate are some of ingredients approved for the making, formulation, and production of chewing and bubble gum (Fritz and Elias, 1980).

In this context, our work aims to study the feasibility of modifying the properties of chewing gum waste by means of a chemical reaction carried out under conditions similar to those of cross-linking rubber by vulcanization, in order to take advantage of some similarities between chewing gum and rubber regarding their structure and properties. It is expected that the cross-linking modifies the polymeric properties of chewing gum residues, as in the vulcanization of natural material (*i.e.*, through the use of sulfur, one of the most efficient and widely employed industrial methods), generating desirable characteristics in the products at a low cost. Therefore, the polymeric structure of the chewing gum base could be modified by cross-linking in a rubber vulcanization-like process to produce a less polluting material, which might have suitable properties for some applications.

Since the discovery of vulcanization, several researchers have highlighted the effect of the filler, the plasticizer, and the anti-oxidant on the process. A free-radical mechanism for rubber cross-linking was originally suggested by Flory (1953), Shelton and McDonel (1960) and Kruželák *et al.* (2017). Other evidence suggests an ionic mechanism that leads to the formation of macromolecules by sulfur bridges (C-Sx-C), which is initialized by sulfur (the cross-linking agent) with zinc salt (the accelerator) to produce a type of perthio-salt [activator-Sx-Zn-activator]. This induces the formation of a rubber-sulfur bond, removing hydrogen from the methylene groups located in alpha to an unsaturation in the structure of the natural rubber (Niyogi and Varma, 2007). However, as it probably involves a complex sequence of reactions, the mechanisms and the chemistry involved in the rubber cross-linking process using sulfur have not been fully understood and are still a subject of prime interest.

In rubber vulcanization, different types of accelerators are used to obtain better use properties and shorter process times. The cross-linking process catalyzed solely by the action of zinc salts (activators) can take up to 4 hours (Bevilacqua, 1959; Nieuwenhuizen, 2001; Sae-oui *et al.*, 2007; Bornstein and Pazur, 2020). In the cross-linking with sulfur, the selected accelerator determines the type of network structure produced, as well as the specific properties of the material obtained (Marković, 2009). The basic characteristics of the accelerators used in rubber vulcanization are usually similar and are composed of one or two sulfur atoms located between a pair of organic groups.

shuerta52029@universidadean.edu.co

<sup>5</sup> Chemical engineer, Universidad EAN, Bogotá. Affiliation: Universidad EAN, Faculty of Engineering, Bogotá, Colombia. E-mail: mtorosa91317@universidadean.edu.co

<sup>6</sup> Chemical engineer, Universidad EAN, Bogotá. Affiliation: Universidad EAN, Faculty of Engineering, Bogotá, Colombia. E-mail: drojasm30899@universidadean.edu.co

**How to cite:** Castellanos, IC., Luque, C., Avella, E., Huertas, S., Toro, M. and Rojas, D. (2023). Monitoring via infrared spectrometry and rheometry of a vulcanization-like process of chewing gum waste. *Ingeniería e Investigación*, 43(2), e99467. DOI: <https://doi.org/10.15446/ing.investig.99467>



Attribution 4.0 International (CC BY 4.0) Share - Adapt

There are primary and secondary accelerators responsible for increasing the reaction speed in the vulcanization of rubbers, e.g., cyclohexyl benzothiazole sulfenamide (CBS) and tetramethylthiuram disulfide (TMTD). The former is a primary accelerator that, at normal vulcanization temperatures (408 – 413 K), increases the speed of the process; and the latter is a secondary accelerator that acts as a sulfur donor which favors the stabilization of the torque, generates a high cross-linking density, and provides vulcanized rubbers with a resistance to thermal degradation (Sae-oui *et al.*, 2007). Binary accelerator combinations have also been widely used, as they provide higher curing rates in rubber vulcanization (Kim *et al.*, 2011; Wang *et al.*, 2019).

This paper presents information on the laboratory-scale obtainment of a material from chewing gum waste subjected to a process similar to that of the sulfur vulcanization of natural rubber, and it provides some data on its preliminary characterization by ATR-FTIR, rheometry, Shore A hardness, and density measurements taken in order to determine the curing time, as well as to analyze, through the results of these experiments, the changes generated by the process in the chewing gum waste properties. It is considered that a treatment like this could help revalue this waste by finding an appropriate use for the produced material.

The evolution of the whole process was monitored via a series of mid-infrared ATR-FTIR (attenuated total reflectance with Fourier Transform) spectra of aliquots isolated from the reaction medium every 10 minutes for 4 hours, as well as through sequential measurements of torque during the process (from the raw material until the final product was obtained). The absorbance of the bands in all ATR-FTIR spectra were normalized with regard to the absorbance of the band at  $2\,953\text{ cm}^{-1}$ , as it was practically constant in all spectra. The fundamental bands of the ATR-FTIR spectra were analyzed in terms of their maximum absorbance wave number and intensity changes, as manifested by the normalized absorbance during the process, using a descriptive statistical analysis in order to get information about changes caused by this reaction in the functional groups present in the structure of the material.

## Methodology

All of the rubber vulcanization-like processes were carried out from raw material obtained via a collection campaign of chewing gum waste discarded from Colombian commercial brands, which was carried out at Universidad EAN (Bogotá, Colombia) at the beginning of 2019. The chewing gum wastes were sanitized with 1% sodium hypochlorite and by autoclaving (at an internal pressure of 98 to 103 kPa and a temperature of 373 K to 393 K), and they were dried properly before subjecting them to the vulcanization-like process.

The drying of the gum was carried out by making thin sheets in a roller mill with a thickness not greater than 0,3 mm and subjecting them to air drying for 6 hours. The kneading and formation of a new sheet was repeated to regenerate the area exposed to drying in order to foster the loss of water trapped between the polymer chains. The drying cycles were repeated until no changes were observed in the O-H stretching band ( $\nu_{\text{O-H}}$ ) of the ATR-FTIR spectrum. The base formulation for the rubber vulcanization-like process used in this study is summarized in Table 1.

**Table 1.** Base formulation of chewing gum waste compound (weight per 100 parts of chewing gum). Natural rubber was used for control.

| Compound   | Mix A (phr) | Control (phr) | Mix B** (phr) |
|--|-------------|---------------|---------------|
| Wasted chewing gum                                     | 100,0       | 0,0           | 100,0         |
| Natural rubber   | 0,0         | 100           | 0,0           |
| Stearic acid   | 1,0         | 1,0           | 1,0           |
| ZnO  | 5,0         | 5,0           | 5,0           |
| Carbon black N550                                      |             |               |               |
| type - STERLING® SO-1*                                 | 60,0        | 60,0          | 6,0           |
| Sulfur   | 3,0         | 3,0           | 3,0           |
| CBS (N-Cyclohexyl-2-benzothiazole Sulfonamide) Premix® | 1,0         | 1,0           | 0,0           |
| TMTD (Tetramethyl thiuram disulfide) Premix®           | 1,0         | 1,0           | 0,0           |
| Total  | 171,0       | 171,0         | 115,0         |

Source: Authors

\* Rubber® furnace industrial-grade carbon black, from Cabot Corporation

\*\* Mix B was the only one monitored via ATR-FTIR

## Sample preparation for rheometry

Mix A and B were prepared using a 300 mm laboratory mixer roll mill at a roll speed ratio of approximately 1 100 rpm and a roll temperature of 293-303 K. The processing time after the addition of each component of Mix A was approximately 2 minutes. Rheometric characteristics were evaluated using a Prescott MDR MINI Oscillating Disk Rheometer, in accordance with the ASTM-D5289 (2019) standard test method. The hardness of the samples was measured using the PTC 306 L equipment according to ASTM-D792 (2020), while density was measured according to ASTM-D2240 (2021).

Mix B was made without the addition of accelerators (CBS and TMTD) and with a lower amount of sulfur in order to slow down the process and monitor the changes of the functional groups present in the mix via ATR-FTIR, improving the quality of the baseline of the spectra. It was subjected to heating for 4 hours at a temperature of 413 K, and samples of the reaction medium were taken every 10 minutes for the subsequent acquisition of ATR-FTIR spectra.

## ATR-FTIR analysis

Each sample (aliquot isolated from the reaction medium) was cooled in liquid nitrogen to stop the reaction before acquiring its ATR-FTIR spectrum at room temperature with a Shimadzu IRTracer-10 spectrophotometer equipped with a DLATGS detector (deuterated L-alanine doped triglycine sulfate), a mid-infrared (IR) source, and a single-reflection attenuated total reflectance (ATR) zinc selenide (ZnSe) crystal. Each spectrum was collected by placing a portion of the material on the round crystal window. The ATR-FTIR spectrum of each sample was recorded in 32 scans in the range of  $340\text{ cm}^{-1}$  -  $4\,000\text{ cm}^{-1}$ , with a spectral resolution of  $2\text{ cm}^{-1}$ . This, with regard to a previous background spectrum acquired with a constant distance from the sample to the optic unit (guaranteed by the holding arm of the sample spacer device) in order to minimize any errors caused by non-uniform contacts when acquiring the spectra. The ATR-FTIR spectrum of each sample was recorded via the LabSolutions IR Data Collection software and analyzed in triplicate.

The entire vulcanization-like process of chewing gum waste was carried out in duplicate, starting from a variety of different chewing gum wastes. Thus, for this study, a total of 150 ATR-FTIR spectra were acquired, *i.e.*, three spectra for every aliquot isolated from the reaction medium throughout the process.

## Data processing

The baseline of each spectrum was adjusted with variable slope and offset, and an advanced smoothing with three algorithms (moving average, Savitsky-Golay, and percentile filter) was carried out. The spectrum was filtered by removing the cosmic spikes that can be present in all photoelectric readout systems as random unidirectional sharp spikes that distort spectra and may affect the results of later statistical analyses (Barton and Hennelly, 2019). An average ATR-FTIR spectrum of the  $n$ -replicates acquired of each aliquot isolated from the reaction medium throughout the process was calculated. All processing (including the conversion of spectrum data to .csv files) was made using the Spectragryph software (<https://www.ffmpeg2.de/spectragryph/index.html21/04/2023>). Statistical analyses were conducted in R version 4.0.3 with RStudio version 1.3.1093, Windows 10+ (64-bit).

## Descriptive statistical analysis of the ATR-FTIR spectrum

All of the ATR-FTIR spectra were normalized for the analysis, with the aim to make them comparable. 25 average spectra, each with 3 734 point data (wave number, absorbance), were studied. 13 bands present in all of the ATR-FTIR spectra were selected for the analysis. These bands were characterized by the wave number corresponding to its maximum absorbance and assigned according to previously published tables (Anderson *et al.*, 2004; Silverstein *et al.*, 1991; Stuart, 2004). It was assumed that each point data of a band (well-defined wave number, absorbance) in any spectrum correlates with that of the band located at the same wave number in any other spectrum belonging to the series of ATR-FTIR spectra under analysis (Smith, 2011).

The absorbance of the band at  $2\,953\text{ cm}^{-1}$  served as a reference to normalize the data of each spectrum, as it showed the least variation in all of the spectra acquired during the study. This normalization allowed comparing the spectra of the series, attenuating the effects caused by the penetration of the IR beam in the sample while acquiring each spectrum, thus avoiding interpretation bias in the results. For each of the 13 selected bands, the mean of the maximum absorbance wave number and its corresponding absorbance were calculated, as well as the dispersion range and the standard deviation of the mean. The normalization process was based on Equation (1), where  $a_{i,j}$  represents the absorbance of the band appearing at the  $j$ -th wave number in the  $i$ -th spectrum for  $i = 1, \dots, 25$  and  $j = 1, \dots, 3\,734$ ;  $\bar{a}_{2\,953\text{ cm}^{-1}}$  denotes the average absorbance of the band at  $\bar{\nu}: 2\,953\text{ cm}^{-1}$  in the total series of the spectra;  $a_{i,2\,953\text{ cm}^{-1}}$  corresponds to the absorbance of the band at  $\bar{\nu}: 2\,953\text{ cm}^{-1}$  for each  $i$ -th spectrum; and  $a_{i,j}^*$  represents the normalized absorbance for the corresponding band at the  $j$ -th wave number. The input for the statistical analysis was a  $25 \times 3\,734$  matrix of normalized absorbance values.

$$a_{i,j}^* = a_{i,j} \frac{\bar{a}_{2\,953\text{ cm}^{-1}}}{a_{i,2\,953\text{ cm}^{-1}}} \quad (1)$$

The Pearson correlation coefficient was calculated according to Equation (2) in order to show the probable relationships between bands attributed to certain functional groups and

particular bonds in the literature (Anderson *et al.*, 2004; Silverstein, *et al.*, 1991; Stuart, 2004).

$$r_{xy} = \frac{\sum_{i=1}^n x_i y_i - n \bar{x} \bar{y}}{(n-1) s_x s_y} \quad (2)$$

where  $x_i$  and  $y_i$  are the values of absorbance for the bands  $x$  and  $y$  at the  $i$ -th spectrum;  $n$  is the number of spectra;  $\bar{x}$  and  $\bar{y}$  are the mean of absorbance value for each band; and  $s_x$  and  $s_y$  are the corresponding standard deviations. This coefficient takes values between +1 and -1. Values close to +1 indicate a positive linear correlation (direct or increasing), and values close to 0 evidence no linear correlation. Those close to -1 are indicators of a negative linear correlation (inverse or decreasing). To evaluate whether the coefficient obtained was statistically significant, the hypothesis  $H_0: \rho = 0$  was evaluated with a significance of 5%. The *cor.test* function from the stats library of R was used for contrasting the hypothesis.

## Results and analysis

**Table 2.** Test on unvulcanized and vulcanized products

| Property  | Units                | Unvulcanized Product |                   | Vulcanized Product |                   |
|-----------|----------------------|----------------------|-------------------|--------------------|-------------------|
|           |                      | Natural Rubber       | Chewing gum waste | Natural rubber     | Chewing gum waste |
| Hardness* | Shore A              | 43                   | 20                | 70                 | 97                |
| Density** | (kg/m <sup>3</sup> ) | 930                  | 1 280             | 1 150              | 1 510             |

Source: Authors

\* Measurement uncertainty  $\pm 0,03$ . \*\* Measurement uncertainty  $\pm 0,5\text{ kg/m}^3$

At the industrial level, vulcanization has been extensively used for cross-linking natural rubber, and a vulcanization-like process has not been applied to chewing gum waste, which is typically disposed of as useless polluting trash. This report shows the results of applying said process on chewing gum waste, which was carried out under conditions similar to those of industrial rubber vulcanization and monitored via rheometry measurements and ATR-FTIR spectrometry from the raw material until the final product was obtained, including the aliquots isolated from the reaction medium every 10 minutes during the whole process. This was done in our laboratory under the expectation of obtaining a cross-linked product with different physical-chemical properties, perhaps suitable for a more profitable use than that of the chewing gum waste.

The measured elastic torsional ( $S'$ ) data in the rubber vulcanization processes provide indication of the cross-linking level achieved (*i.e.*, the sum of the chemical bonds involved in the cross-links). Figure 1 shows the rheometric monitoring of the rubber vulcanization-like process of the chewing gum waste at 413 K in Mix A. The curve in Figure 1 has a similar behavior to that of reversion in rubber vulcanization (Bornstein and Pazur, 2020), where a steep linear drop of torque precedes the reaction stage during precursor formation, in a way analogue to the first stage occurring with uncured rubber, which will be discussed later in the ATR-FTIR analysis section. After said drop, the  $S'$  value shows a fast rise, which can be associated with a cross-linking density increase, just up to a maximum value of 17,46 dNcm. Then,  $S'$  values show a slight drop, probably due to a reversion process, a term generally applied to the loss of network structures due to non-oxidative thermal


aging, as a result of an overly long vulcanization (Coran, 1964; Bornstein and Pazur, 2020).

The Mix A formulation was characterized by the addition of 3,0 phr of sulfur, a higher content of carbon black (60 phr), and the use of CBS and TMTD as accelerators. Based on the monitoring of torque during the process (Figure 1), a scorch time  $T_{S2}$  (at which cross-links begin to occur) equal to 1,96 min was determined, as well as the time at which the progress of the cross-linking in the vulcanization reached 90% of the maximum ( $T_{90}$ ), equal to 5,15 min ( $T_{90} = 3,74$  minutes for natural rubber).

The final material obtained via the vulcanization-like process of chewing gum waste using CBS and TMTD in Mix A (Table 1) was characterized in terms of density and Shore A hardness (Table 2). The density ( $1\,510 \pm 5\text{ kg/m}^3$ ) turned out to be approximately 1,18 times higher and the shore A hardness ( $97 \pm 0,3$ ) 77 units larger than those of the raw material (chewing gum waste). The Shore A hardness of the raw material ( $20 \pm 0,3$  units) classifies chewing gum waste as a soft material, while that of the material obtained with this treatment is characteristic of extra-hard materials.

All of these data evidence the feasibility of the rubber vulcanization-like process of chewing gum waste. Under conditions similar to those experienced by rubberin industrial vulcanization, this process is able to change the properties of chewing gum waste and transform it into a material with characteristics that could be adapted for convenient and cost-effective uses.

The Mix B formulation was characterized by lower contents of carbon black and sulfur. The vulcanization-like process of Mix B produced a material whose Shore A hardness ( $70 \pm 0,3$  units) classifies it as a medium-hardness material. The fact that this product has a lower hardness than the product obtained from Mix A can be attributed to the lower content of carbon black, which was used as a reinforcing material in Mix B (Sánchez *et al.*, 2020), and, by analogy with rubber vulcanization, to the use of the CBS and TMTD accelerators, which have shown some influence on the final properties of vulcanized rubber (Sae-oui *et al.*, 2007; Marković *et al.*, 2009; Formela *et al.*, 2015). The increased concentration of carbon black in Mix A formulation had a positive effect on the hardness and density of the final product, possibly because, as in the case of rubber, it acts as a support material to form the bonds with the material that is being vulcanized (Bueche, 1961; Janacek, 1962).

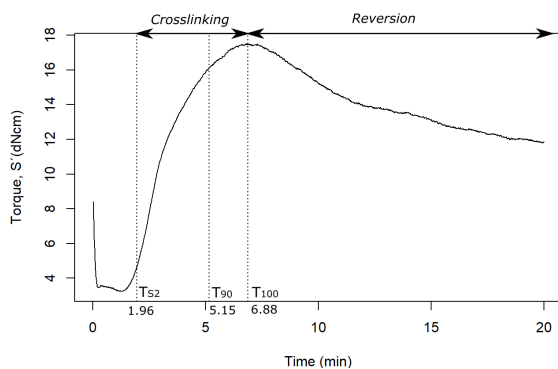

**Figure 1.** Rheometer curve for the vulcanization of chewing gum waste in Mix A at 413 K

Source: Authors

## Monitoring the process via ATR-FTIR

Figure 2 presents the ATR-FTIR spectra series of the raw material, the reactives, the prevulcanized material, and the 25 aliquots isolated from the reaction medium every 10 minutes during the vulcanization-like process of Mix B (Table 1), which were acquired at 413 K.

Seeking to minimize any distortions due to overlapping signals in the components of the ATR-FTIR spectra of these mixtures, this study considered the intensity of the bands, which proved to be more accurate than its integral when analyzing the behavior of the set of signals in the spectra. Table 3 shows the location (wave numbers) and the average with the dispersion of the absorbance for each spectral band of interest in this analysis. The band at  $\bar{\nu}$ :  $2\,953\text{ cm}^{-1}$  showed the least variation in the whole the set of spectra during the whole process; it had a dispersion of 0,04 units and a coefficient of variation of 13,39% around its average value. Therefore, the band at  $\bar{\nu}$ :  $2\,953\text{ cm}^{-1}$  was chosen as the reference to normalize the absorbance of all other bands of interest in each spectrum of the ATR-FTIR series of the samples (raw material, pre-vulcanized material, and aliquots). It is worth adding that the term *to normalize* means to represent each data from a sample of data (each ATR-FTIR spectrum of the series) by a ratio of proportion obtained as the quotient resulting from dividing it by another data belonging to the same sample, which is chosen as a common reference for all the data in the sample, in order to unify their scale and make them comparable to other equally normalized samples, *i.e.*, with respect to the same reference (the average absorbance of the band at  $2\,953\text{ cm}^{-1}$ ).

In order to obtain information on changes in the chemical composition during the vulcanization-like process of the chewing gum waste, the corresponding 13 bands of each spectrum (Table 3) were selected along with their already normalized average absorbances, considering the magnitude of the coefficients of variation found for their average values of normalized absorbance in the whole set of spectra for the aliquots isolated from the reaction medium during the process. These bands were assigned as indicated in the literature (Anderson *et al.*, 2004; Silverstein, 1991; Stuart, 2004), and their average absorbances were subjected to a statistical treatment, such as the one shown in Figure 3, looking for changes in the initial composition which could be interpreted as the occurrence of a vulcanization-like process of the chewing gum waste. Thus, changes in the carbonyl, methylene, and carboxylate groups were found and taken into consideration for the analysis.

It is very common to use the Pearson correlation coefficient to quantify a possible linear correlation between two sets of data (Zou *et al.*, 2003). This coefficient was used to analyze linearity of the absorbances of all the spectral bands chosen for this study (Jampafuang *et al.*, 2015; Šlouf *et al.*, 2018).

For this analysis, the data from the ATR-FTIR spectra set were represented in a 2D matrix (1 line = absorbance of the first band; 1 column = absorbance of second band), and the correlation matrix was computed for the eight spectral bands with the highest coefficient of variation during the process: the bands at  $\bar{\nu}$ :  $1\,700\text{ cm}^{-1}$  and  $\bar{\nu}$ :  $1\,732\text{ cm}^{-1}$  for the stretching of carbonyls ( $\nu_{C=O}$ ); the band at  $\bar{\nu}$ :  $1\,412\text{ cm}^{-1}$  for the bending of methylene and/or the methyl groups ( $\delta_{H-C-H}$ ,  $\delta_{H-C-C}$ , and  $\delta_{H-C-O}$ ); the bands at  $\bar{\nu}$ :  $1\,559\text{ cm}^{-1}$  and

**Table 3.** Assignment of the bands and descriptive statistics of the average absorbance local maximum data prior to normalization for the bands of interest in the whole set of ATR-FTIR spectra of the aliquots isolated from the reaction medium during the vulcanization-like process of chewing gum waste

| Wave number<br>( $\text{cm}^{-1}$ ) | Assignment   | Between acquisitions of same sample |      |       |      |                    |
|-------------------------------------|--|-------------------------------------|------|-------|------|--------------------|
|                                     |  | Absorbance                          |      | Range | Mean | Standard deviation |
|                                     |  | Min                                 | Max  |       |      |                    |
| 3 433                               | $\nu_{\text{O-H}}$ associated  | 0,01                                | 0,04 | 0,04  | 0,02 | 0,01               |
| 2 953                               | $\nu_{\text{C-H}}$ stretching  | 0,05                                | 0,09 | 0,04  | 0,08 | 0,01               |
| 2 916                               | -CH <sub>2</sub> - and -CH <sub>3</sub>  | 0,10                                | 0,18 | 0,09  | 0,16 | 0,02               |
| 2 848                               |  | 0,12                                | 0,22 | 0,11  | 0,19 | 0,03               |
| 1 732                               | $\nu_{\text{C=O}}$   | 0,06                                | 0,16 | 0,10  | 0,10 | 0,02               |
| 1 700                               |  | 0,01                                | 0,10 | 0,08  | 0,03 | 0,02               |
| 1 566                               | R - COO <sup>-</sup>   | 0,01                                | 0,06 | 0,05  | 0,04 | 0,01               |
| 1 542                               |  | 0,01                                | 0,10 | 0,09  | 0,06 | 0,02               |
| 1 412                               | -CH <sub>3</sub> and -CH <sub>2</sub> ,<br>-O - CO - CH <sub>3</sub><br>and -CH <sub>2</sub> - C = C < | 0,08                                | 0,23 | 0,15  | 0,15 | 0,03               |
| 1 234                               | -C - O-,<br>CH <sub>2</sub> - SH   | 0,03                                | 0,12 | 0,09  | 0,06 | 0,02               |
| 728                                 | long aliphatic chains<br>-(CH <sub>2</sub> ) <sub>n</sub> -; n > 4                                     | 0,01                                | 0,05 | 0,04  | 0,3  | 0,01               |
| 720                                 |  | 0,03                                | 0,07 | 0,04  | 0,05 | 0,01               |
| 712                                 |  | 0,03                                | 0,08 | 0,05  | 0,06 | 0,01               |

Source: Authors


$\bar{\nu}$ : 1 538  $\text{cm}^{-1}$  for the bending of ester carboxylate groups ( $\delta_{\text{O=C-O}}$ ); the band at  $\bar{\nu}$ : 1 232  $\text{cm}^{-1}$  for the stretching of C-O bonds in  $\text{sp}^2$  hybridized carbon ( $\nu_{\text{C-O}}$ ) or the stretching of  $\nu_{\text{C-S}}$  bonds ( $\nu_{\text{C-S}}$ ) in mercaptan-methylene fragments, -CH<sub>2</sub>-SH, which is most likely overlapped in this spectral region; and the bands at  $\bar{\nu}$ : 728  $\text{cm}^{-1}$  and  $\bar{\nu}$ : 712  $\text{cm}^{-1}$  for the rocking of CH<sub>2</sub> in aliphatic chains, -(CH<sub>2</sub>)<sub>n</sub>- with n > 4.

Figure 3 depicts the 2D matrix considered for the statistical treatment when correlating the average maximum of absorbances for nine bands located at a given wave number in each ATR-FTIR spectrum of the series, which were finally chosen due to their proven relevance for interpreting the results. The form and the intensity of such spectral bands are shown by the curves appearing in the cells of the diagonal of the matrix in Figure 3. The bands at  $\bar{\nu}$ : 1 732  $\text{cm}^{-1}$ ,  $\bar{\nu}$ : 1 700  $\text{cm}^{-1}$  ( $\nu_{\text{C=O}}$ ), and the band at  $\bar{\nu}$ : 1 234  $\text{cm}^{-1}$  ( $\nu_{\text{C-O}}$ ) frequently exhibited low absorbance values due to their asymmetric and variable forms (mostly with positive asymmetry). The other bands had a less pronounced yet similar tendency. For example, in Figure 3, an increasing linear relation is noticeable between the band at  $\bar{\nu}$ : 1 732  $\text{cm}^{-1}$  ( $\nu_{\text{C=O}}$ ) and the band at  $\bar{\nu}$ : 1 234  $\text{cm}^{-1}$  ( $\nu_{\text{C-O}}$ ), supported by a linear correlation coefficient of 0,974, with a p-value of less than 5%. This means that the higher the absorbance values of the band at  $\bar{\nu}$ : 1 732  $\text{cm}^{-1}$  ( $\nu_{\text{C=O}}$ ), the greater the absorbance values for the band at  $\bar{\nu}$ : 1 234  $\text{cm}^{-1}$  ( $\nu_{\text{C-O}}$ ).

Another possible increasing linear relation is that of the bands at  $\bar{\nu}$ : 1 412  $\text{cm}^{-1}$  ( $\delta_{\text{H-C-H}}$ ,  $\delta_{\text{H-C-C}}$ ,  $\delta_{\text{H-C-O}}$ ) and  $\bar{\nu}$ : 712  $\text{cm}^{-1}$  ( $\delta_{\text{H-C-H}}$ ), with a correlation coefficient of 0,684 and a lower p-value of 5%.

The absorbance values of the bands at  $\bar{\nu}$ : 1 542  $\text{cm}^{-1}$  and  $\bar{\nu}$ : 1 700  $\text{cm}^{-1}$  ( $\nu_{\text{C=O}}$ ) or those at  $\bar{\nu}$ : 1 566  $\text{cm}^{-1}$  ( $\nu_{\text{O=C-O}}$ ) and  $\bar{\nu}$ : 1 700  $\text{cm}^{-1}$  ( $\nu_{\text{C=O}}$ ) showed a linear decreasing relation supported by negative linear correlation coefficients of -0,665 and -0,631, respectively. Both had a lower p-value of 5%, indicating that these bands are attributable to independent phenomena occurring in functional groups

without common atoms or bonds, as well as in different structural fragments of the sample.

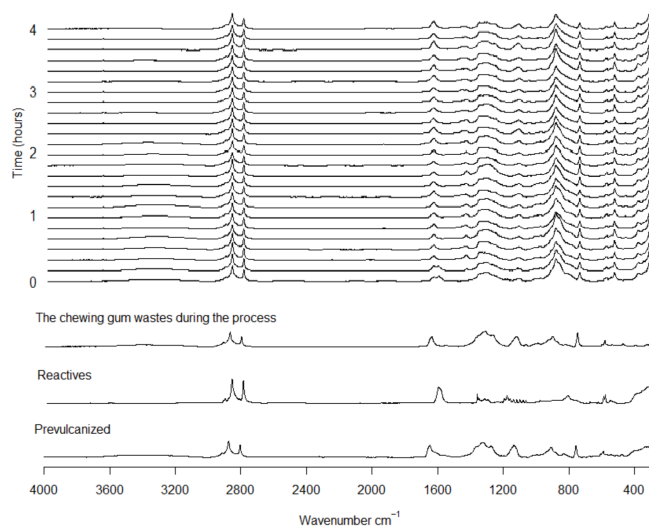


**Figure 2.** ATR-FTIR spectra acquired during the vulcanization-like process of the discarded chewing gum normalized at peak intensity (2 953  $\text{cm}^{-1}$ ) - Mix B at 413 K

Source: Authors

As mentioned above, these first results are only presented as a first approach, in order to collect evidence of the feasibility of the reaction of chewing gum waste under rubber vulcanization-like conditions, with the purpose of transforming these residues into materials with distinct properties, which could be suitable for profitable use. Therefore, these results do not pretend to clarify the mechanism involved in the chemical reactions occurring during the process; they aim to serve as a descriptive analysis of the changes observed, based on some similarities and differences with the processes recorded by the authors of previous studies on rubber vulcanization.

The most noticeable spectral features that were modified in the ATR-FTIR spectra of the materials isolated from the reaction medium during the treatment (Figure 2) can be thus described: the medium intensity of the band at  $\bar{\nu}$ : 3 433  $\text{cm}^{-1}$ , attributable to the stretching vibration of associated O-H ( $\nu_{\text{O-H}}$ ), was present in the spectrum of the chewing gum waste and in those of the aliquots initially isolated from the reaction mixture, but this intensity decreased slightly in the spectra of aliquots, with some grade of cross-linking (vulcanized samples). Its appearance in the spectrum can be explained by residues of sweetener and acids as original components of the chewing gums, by the product of partial deacetylation of its major constituent (the polyvinyl acetate, PVAc) (Rimez *et al.*, 2008), or by occluded water that was not removed by drying, as revealed by the band at  $\bar{\nu}$ : 1 640  $\text{cm}^{-1}$ , attributed to H-O-H bending ( $\delta_{\text{H-O-H}}$ ), in the spectrum of the chewing gum waste.

The bands at  $\bar{\nu}$ : 2 953  $\text{cm}^{-1}$ ,  $\bar{\nu}$ : 2 916  $\text{cm}^{-1}$ , and  $\bar{\nu}$ : 2 848  $\text{cm}^{-1}$ , due to C-H stretching vibrations on  $\text{sp}^3$  hybridized carbon atoms in aliphatic fragments ( $\nu_{\text{C-H}}$ ), correlate with the bands of bending in planes H-C-H of methylene groups ( $\delta_{\text{H-C-H}}$ ), or in planes H-C-C or H-C-O of methyl groups ( $\delta_{\text{H-C-C}}$ ,  $\delta_{\text{H-C-O}}$ ) that appear at  $\bar{\nu}$ : 1 450  $\text{cm}^{-1}$  and  $\bar{\nu}$ : 1 433  $\text{cm}^{-1}$ , and their changes in the ATR-FTIR spectra have been previously associated with the

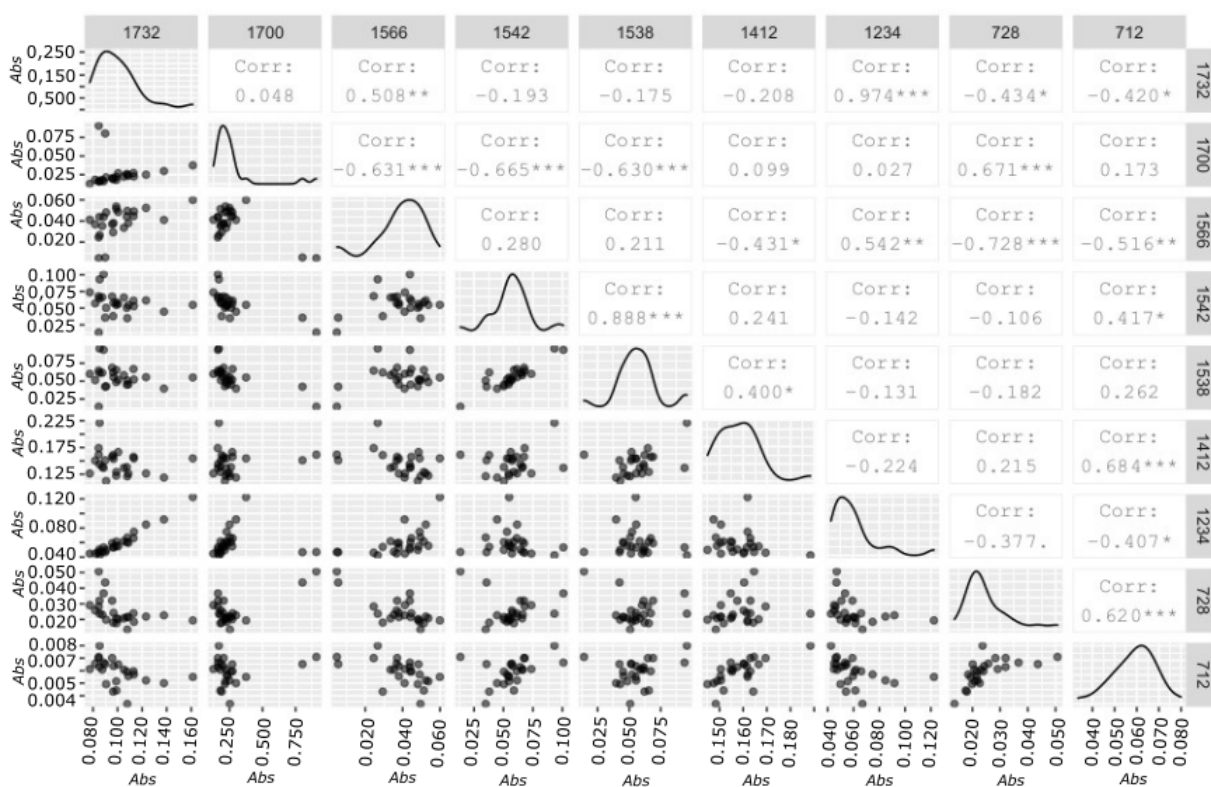

**Figure 3.** Linear correlation 2D matrix for the absorbance variation of the chosen bands of interest to analyze the set of ATR-FTIR standard reference spectra (normalized) of aliquots isolated from the reaction medium during the vulcanization-like process of chewing gum waste. Statistical significance level: \* 0.05, \*\* 0.01 and \*\*\* 0.001. The first line and the last column are wave numbers ( $\text{cm}^{-1}$ ).

**Source:** Authors

progressive cross-linking occurring in rubber vulcanization with sulfur (Koenig, 1975), as a result of the decrease in  $\alpha$ -methylene hydrogen contents caused by the vulcanization reaction, in which hydrogen, located in alpha, is abstracted to unsaturation as something concomitant to the formation of sulfur bridges (C-Sx-C). For the set of spectra acquired throughout this research, the variation coefficient of the average absorption in the band at  $\bar{\nu}$ : 1412  $\text{cm}^{-1}$  was 19,07%. At  $\bar{\nu}$ : 1475 – 1365  $\text{cm}^{-1}$ , besides the bands of bending in planes of the -CH<sub>3</sub> and -CH<sub>2</sub>- groups, those of bending in planes H-C-O of the -O-CO-CH<sub>3</sub> fragment appear overlapped and interfere with the analysis of their behavior throughout the process.

There are also three bands in the interval comprising  $\bar{\nu}$ : 735 – 700  $\text{cm}^{-1}$  which are attributable to the rocking or asymmetrical bending in planes H-C-H in aliphatic chains with four or more consecutive methylene groups. This set of bands, with maxima at  $\bar{\nu}$ : 728  $\text{cm}^{-1}$ , at  $\bar{\nu}$ : 720  $\text{cm}^{-1}$ , and at  $\bar{\nu}$ : 712  $\text{cm}^{-1}$ , are complementary to the two sets of signals described before. Its appearance in the spectra can be associated with the gum base and the presence of stearic acid. This analysis shows the band at  $\bar{\nu}$ : 712  $\text{cm}^{-1}$  correlated to that at  $\bar{\nu}$ : 1412  $\text{cm}^{-1}$  (0,684 Pearson correlation coefficient, 5% significance) while the band at  $\bar{\nu}$ : 728  $\text{cm}^{-1}$  is correlated to that at  $\bar{\nu}$ : 1700  $\text{cm}^{-1}$ , which is attributable to

stretching of carbonyl (with Pearson correlation coefficient of 0,671 and a significance of 5%).


When it comes to studying rubber vulcanization and taking into account the IR spectra acquired before and after the process, different approaches have been proposed. Shipman and Golub (1962) reported that the most prominent change in the infrared spectrum of rubber after vulcanization with sulfur is the appearance of a new absorption at  $\bar{\nu}$ : 961  $\text{cm}^{-1}$ . This signal was associated with a carbon-carbon double bond formation (-CH=CH-) by elimination (Shipman and Golub, 1975), i.e., one from the various possible reactions considered in rubber cross-linking. Nevertheless, this signal did not appear in any spectrum of the ATR-FTIR monitoring of the vulcanization-like process of chewing gum waste under similar conditions, albeit without the use of accelerators.

Additionally, this set of ATR-FTIR spectra allowed detecting some modifications undergone by the zinc oxide and stearic acid present in the reaction medium since the beginning of the process as precursors of zinc-derived accelerators in the vulcanization (Ikeda et al., 2009).

A critical step to attaining efficient curing is the formation of zinc stearate via the reaction of stearic acid and zinc oxide (Figure 4). In the vulcanization-like process of chewing gum waste, this was monitored based on the band at

$\bar{\nu}$ : 1 542  $\text{cm}^{-1}$ , attributable to the asymmetric stretching vibration of the carboxylate anion, which stands for the complete resonance in the C-O bonds of the carbonyl group due to coordination with the metal (Figure 4). During the first minutes of the process, this band showed an increase in absorbance (a sign of zinc stearate production), while the absorbance of the band at  $\bar{\nu}$ : 1 700  $\text{cm}^{-1}$ , attributable to the stretching of carbonyl ( $\nu_{\text{C=O}}$ ) in the carboxyl group of the acid, had a proportional decrease, a sign of stearic acid consumption (Figure 3).

In other words, the carbonyl absorption decrease (at  $\bar{\nu}$ : 1 700  $\text{cm}^{-1}$ ) was replaced by the increase of that of the band at  $\bar{\nu}$ : 1 542  $\text{cm}^{-1}$  appearing in the spectrum (this was supported by a Pearson correlation coefficient of -0,665). The band at  $\bar{\nu}$ : 1 542  $\text{cm}^{-1}$  appeared as a unique band in the spectra of aliquots isolated until 90 minutes after heating began. From that time onward, a second band appeared at  $\bar{\nu}$ : 1 566  $\text{cm}^{-1}$ , attributable to the anti-symmetric stretching of bands for the bidentate association with zinc ions, which has a Pearson correlation coefficient of -0,631 with the band at  $\bar{\nu}$ : 1 700  $\text{cm}^{-1}$ . A similar behavior was reported for rubber vulcanization (Musto *et al.*, 2013; Ikeda *et al.*, 2015).

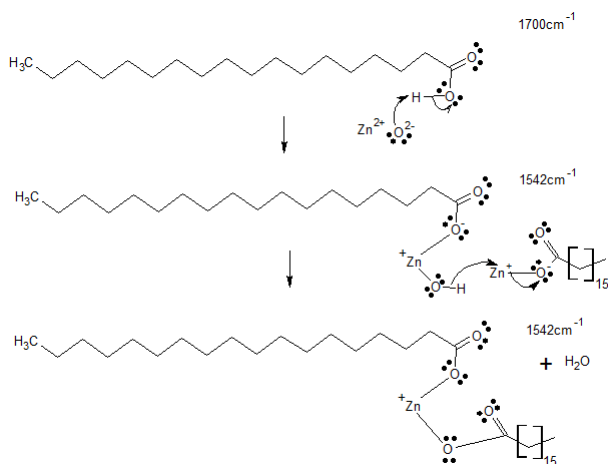

**Figure 4.** Reaction scheme for the zinc stearate formation related to ATR-FTIR signals recorded during the vulcanization-like process of chewing gum waste

**Source:** Authors

In the whole set of ATR-FTIR spectra for aliquots isolated from the reaction medium during the studied process, major variations were observed in the absorbance of the bands at  $\bar{\nu}$ : 1 700  $\text{cm}^{-1}$ , at  $\bar{\nu}$ : 1 566  $\text{cm}^{-1}$ , and at  $\bar{\nu}$ : 1 542  $\text{cm}^{-1}$  for the first monitoring intervals times (0-10 min); whereas the bands at  $\bar{\nu}$ : 1 732  $\text{cm}^{-1}$  and  $\bar{\nu}$ : 1 234  $\text{cm}^{-1}$  varied noticeably in the spectra of aliquots isolated at the end of the reaction (220-240 min). Both sets of bands are related to phenomena occurring in carboxylate or carboxyl functional groups, but the variations in the band at  $\bar{\nu}$ : 1 732  $\text{cm}^{-1}$  do not behave similarly to those of  $\bar{\nu}$ : 1 700  $\text{cm}^{-1}$ . This suggests that the band at  $\bar{\nu}$ : 1 732  $\text{cm}^{-1}$  might be a result of the overlapping between bands from the -COOH group of stearic acid associated with hydrogen bridges (Musto *et al.*, 2013) and those from carbonyl of the carboxylate groups of PVAc in the chewing gum waste, as evidenced by the appearance of said bands in the spectrum of the residues, as well as by their absence in the spectrum of the other reagents (Figure 2).

The absorbance of the band at  $\bar{\nu}$ : 1 732  $\text{cm}^{-1}$  ( $\nu_{\text{C=O}}$ ) varied just as that at  $\bar{\nu}$ : 1 234  $\text{cm}^{-1}$  ( $\nu_{\text{C=O}}$ ); it showed a significant drop in the spectra of aliquots isolated from the reaction medium during the monitoring time, as well as a Pearson correlation coefficient of 0,974 with a 5% significance, suggesting a progressive PVAc degradation under the oxidative conditions inherent to the process applied to chewing gum waste, which was statistically supported by a Pearson correlation coefficient of 0,974 and a 5% significance. This indicates the feasibility of the reaction of such residues under rubber vulcanization-like conditions.

## Conclusions

These findings are the first to show that, under conditions such as those of rubber vulcanization, chewing gum residues react to produce materials with different properties, thus evidencing the cross-linking of the lineal chains initially existing in their components, as it probably happens in the aforementioned process.

Monitoring via rheometric measurements and ATR-FTIR spectrometry of a vulcanization-like process involving chewing gum waste on a laboratory scale allowed determining the occurrence of cross-linking in a reaction time of 5, 15 minutes. A harder (Shore A hardness: 95 units) and denser (1510  $\text{kg}/\text{m}^3$ ) material than chewing gum wastes was obtained (Shore A hardness: 20 units and density: 1280  $\text{kg}/\text{m}^3$ ).

Monitoring via the ATR-FTIR spectra of the vulcanization-like process of chewing gum waste evidenced the occurrence of structural changes throughout the process, which was also proven by the distinct values of their corresponding rheometric properties, always indicating a progressive evolution in the reaction, similar to that of cross-linking in rubber vulcanization.

These initial findings suggest the possibility of reincorporating chewing gum waste into market value chains and promoting the search for profitable alternatives to treat this type of environmental contaminant. This work encourages readers to consider further research, the scaling of the process, and the characterization of the final product with more rheometric measurements such as the storage and loss modulus, together with viscosity parameters that could enrich the prospects of this research.

## Acknowledgements

This study was supported by Universidad EAN (Bogotá, Colombia) namely the Basic Sciences area of the Department of Engineering; and by Universidad Nacional de Colombia (Bogotá campus), represented by the APRENA research group of the Chemistry area, Department of Science. The authors declare their affiliation to one institution or the other, and they appreciate the support received from them.

## Acknowledgements

All authors: Conceptualization-Methodology-Software-Validation-Formal analysis-Investigation- Writing-Original Draft preparation, Writing, Reviewing, and Editing-Data Curation-Supervision-Project administration-Resources-Funding acquisition.



## References

- Anderson, R. J., Bendell, D. J., and Groundwater, P. W. (2004). *Organic spectroscopic analysis* (vol. 22). Royal Society of Chemistry.
- ASTM International (2019). *ASTM-D5289-19a: Standard test method for rubber property -Vulcanization using rotorless cure meters*. ASTM International. <https://doi.org/10.1520/D5289-19A>
- ASTM International (2020). *ASTM-D792-20: Standard test methods for density and specific gravity (relative density) of plastics by displacement*. ASTM International. <https://doi.org/10.1520/D0792-20>
- ASTM International (2021). *ASTM-D2240-15(2021): Standard test method for rubber property -Durometer hardness*. ASTM International. <https://doi.org/10.1520/D2240-15R21>
- Barton, S. J., and Hennelly, B. M. (2019). An algorithm for the removal of cosmic ray artifacts in spectral data sets. *Applied Spectroscopy*, 73(8), 893-901. <https://doi.org/10.1177/0003702819839098>
- BBC (2010). *Mayor to tackle London's gum litter problem*. [http://news.bbc.co.uk/local/london/hi/people\\_and\\_places/newsid\\_8804000/8804328.stm21/04/2023](http://news.bbc.co.uk/local/london/hi/people_and_places/newsid_8804000/8804328.stm21/04/2023)
- Bevilacqua, E. M. (1959). Vulcanization with TMTD. *Rubber Chemistry and Technology*, 32(3), 721-738. <https://doi.org/10.5254/1.3542441>
- Bornstein, D., and Pazur, R. J. (2020). The sulfur reversion process in natural rubber in terms of crosslink density and crosslink density distribution. *Polymer Testing*, 88, 106524. <https://doi.org/10.1016/j.polymeresting.2020.106524>
- Bueche, F. (1961). Mullins effect and rubber–filler interaction. *Journal of Applied Polymer Science*, 5(15), 271-281. <https://doi.org/10.1002/app.1961.070051504>
- Bullus, A. L. (2017). *Composition comprising chewing gum, method for producing the same and use thereof* (France, Patent WO2010046667A1).
- Carter, H. (2005). *Liverpool leads campaign for chewing gum tax*. <https://www.theguardian.com/uk/2005/apr/28/localgovernment.politics21/04/2023>
- Coran, A. Y. (1964). Vulcanization. Part VI. A model and treatment for scorch delay kinetics. *Rubber Chemistry and Technology*, 37(3), 689-697. <https://doi.org/10.3390/polym11122010>
- Flory, P. J. (1953). *Principles of polymer chemistry*. Cornell University Press.
- Formela, K., Wąsowicz, D., Formela, M., Hejna, A., and Haponiuk, J. (2015). Curing characteristics, mechanical and thermal properties of reclaimed ground tire rubber cured with various vulcanizing systems. *Iranian Polymer Journal*, 24(4), 289-297. <https://doi.org/10.1007/s13726-015-0320-9>
- Fritz, D. P., and Elias, R. J. (1980). *Low density chewing gum product and method of making the same* (US, Patent US4233319A).
- Hofko, B., Alavi, M. Z., Grothe, H., Jones, D., and Harvey, J. (2017). Repeatability and sensitivity of FTIR ATR spectral analysis methods for bituminous binders. *Materials and Structures*, 50, 187. <https://doi.org/10.1617/s11527-017-1059-x>
- Ikeda, Y., Higashitani, N., Hijikata, K., Kokubo, Y., Morita, Y., Shibayama, M., Osaka, N., Suzuki, T., Endo, H., and Kohjiya, S. (2009). Vulcanization: New focus on a traditional technology by small-angle neutron scattering. *Macromolecules*, 42(7), 2741-2748. <https://doi.org/10.1021/ma802730z>
- Ikeda, Y., Yasuda, Y., Ohashi, T., Yokohama, H., Minoda, S., Kobayashi, H., and Honma, T. (2015). Dinuclear bridging bidentate zinc/stearate complex in sulfur cross-linking of rubber. *Macromolecules*, 48(3), 462-475. <https://doi.org/10.1021/ma502063m>
- Jacobsen, J., Christrup, L. L., and Jensen, N. H. (2004). Medicated chewing gum. *American Journal of Drug Delivery*, 2(2), 75-88. <https://doi.org/10.2165/00137696-200402020-00001>
- Jampafuang, Y., Tongta, A., and Waiprib, Y. (2015). Impact of crystalline structural differences between  $\alpha$ - and  $\beta$ -chitosan on their nanoparticle formation via ionic gelation and superoxide radical scavenging activities. *Polymers*, 11(12), 1-16. <https://doi.org/10.3390/polym11122010>
- Janacek, J. (1962). Reactions of polymers in bulk. I. Influence of fillers on the degree of crosslinking of natural rubber. *Rubber Chemistry and Technology*, 35(3), 563-571. <https://doi.org/10.5254/1.3539930>
- Kim, S. M., Nam, C. S., and Kim, K.J. (2011). TMTD, MBTS, and CBS accelerator effects on a silica filled natural rubber compound upon vulcanization properties. *Applied Chemistry for Engineering*, 22(2), 144-148.
- Koenig, J. L. (1975). Application of Fourier Transform infrared spectroscopy to chemical systems. *Applied Spectroscopy*, 29(4), 293-308.
- Kruželák, J., Šýkora, R., and Hudec, I. (2017). Vulcanization of rubber compounds with peroxide curing systems. *Rubber Chemistry and Technology*, 90(1), 60-88. <https://doi.org/10.5254/rct.16.83758>
- Liu, H., and Jiang, Y. (2003). *Chewing gum waste eliminating method* (China, Patent CN1421282A).
- Logan, R. P., and Rudolfs, W. (1947). Treatment of wastes from natural gums in chewing gum manufacture. *Industrial and Engineering Chemistry*, 39(12), 1673-1675. <https://doi.org/10.1021/ie50456a032>
- Marković, G., Radovanović, B., Marinović-Cincović, M., and Budinski-Simendić, J. (2009). The effect of accelerators on curing characteristics and properties of natural rubber/chlorosulphonated polyethylene rubber blend. *Materials and Manufacturing Processes*, 24(10), 1224-1228. <https://doi.org/10.1080/10426910902967087>
- Musto, P., Larobina, D., Cotugno, S., Straffi, P., Di Florio, G., and Mensitieri, G. (2013). Confocal Raman imaging, FTIR spectroscopy and kinetic modelling of the zinc oxide/stearic acid reaction in a vulcanizing rubber. *Polymer*, 54(2), 685-693. <https://doi.org/10.1016/j.polymer.2012.12.021>

- Nieuwenhuizen, P.J. (2001). Zinc accelerator complexes: Versatile homogeneous catalysts in sulfur vulcanization. *Applied Catalysis A: General*, 207(1-2), 55-68. [https://doi.org/10.1016/S0926-860X\(00\)00613-X](https://doi.org/10.1016/S0926-860X(00)00613-X)
- Niyogi, D. U. K., and Varma, I. K. (2007). *Polymer additives and compounding: additives for rubbers*. Shri Ram Institute for Industrial Research.
- Oosthuizen, T., Howes, L. M., and White, R. (2022). Forensic science and environmental offences: Litter, DNA analysis and surveillance. *Forensic Science International: Animals and Environments*, 2, 100042. <https://doi.org/10.1016/j.fsiae.2022.100042>
- Palabiyik, I., Toker, O. S., Konar, N., Oner, B., and Demirci, A. S. (2018). Development of a natural chewing gum from plant based polymer. *Journal of Polymers and the Environment*, 26(5), 1969-1978. <https://doi.org/10.1007/s10924-017-1094-2>
- Potineni, R. V. (2007). *Mechanisms of flavor release and perception in sugar-free chewing gum* [Doctoral thesis, Pennsylvania State University]. <https://www.proquest.com/openview/b3e4c9d491c3fb0b9b7acc9f5096ac95/1?pq-origsite=gscholar&cbl=1875021/04/2023>
- Rimez, B., Rahier, H., Van Assche, G., Artoos, T., Biesemans, M., and Van Mele, B. (2008). The thermal degradation of poly (vinyl acetate) and poly (ethylene-co-vinyl acetate), Part I: Experimental study of the degradation mechanism. *Polymer Degradation and Stability*, 93(4), 800-810. <https://doi.org/10.1016/j.polymdegradstab.2008.01.010>
- Ribadeau-Dumas, G., and Mentink, L. (2004). *Environment-friendly chewing gum and method of its manufacture* (Mexico, Patent MXPA04000669).
- Roy, A. S. (2021). Improper disposal of non-biodegradable chewing gum is one of the biggest threats to our ecology: A review. *Current World Environment*, 16(3), 916-927. <http://dx.doi.org/10.12944/CWE.16.3.22>
- Rudgard, O. (2018). *Introduce a chewing gum tax to pay for cleaning up British streets, LGA says*. <https://www.telegraph.co.uk/news/2018/03/02/introduce-chewing-gum-tax-pay-cleaning-british-street-lga-says/21/04/2023>
- Saberi, F., Naderi, M., and Naeli, M. H. (2018). Production of Bio-chewing Gum Based on Saqqez as the Biopolymer: Its Biodegradability and Textural Properties. *Journal of Polymers and the Environment*, 26(9), 3889-3901. <https://doi.org/10.1007/s10924-018-1244-1>
- Sae-oui, P., Sirisinha, C., Thepsuwan, U., and Thapthong, P. (2007). Influence of accelerator type on properties of NR/EPDM blends. *Polymer Testing*, 26(8), 1062-1067. <https://doi.org/10.1016/j.polymertesting.2007.07.004>
- Sánchez, M. A. G., Giraldo-Vásquez, D. H., and Sánchez, R. M. (2020). Rheometric, transient, and cyclic tests to assess the viscoelastic behavior of natural rubber-based compounds used for rubber bearings. *Materials Today Communications*, 22, 100815. <https://doi.org/10.1016/j.mtcomm.2019.100815>
- Savitzky, A., and Golay, M. J. E. (1964). Smoothing and differentiation of data by simplified least squares procedures. *Analytical Chemistry*, 36(8), 1627-1639. <https://doi.org/10.1021/ac60214a047>
- Shelton, J. R., and McDonel, E. T. (1960). Investigation of radical and polar mechanisms in vulcanization reactions. *Rubber Chemistry and Technology*, 33(2), 342-356. <https://doi.org/10.5254/1.3542150>
- Shipman, J. J., and Golub, M. A. (1962). Infrared study of the reaction of polyisoprene and polybutadiene with sulfur by use of deuterated polymers. *Journal of Polymer Science*, 98(166), 1063-1082.
- Simonek, M. (2011). *Wrapping for used chewing gum* (US Patent 7.959.001).
- Silverstein, R. M., Bassler, G. V., and Morrill, T. C. (1991). *Spectrometric identification of organic compound*. John Wiley and Sons.
- Smith, B. C. (2011). *Fundamentals of Fourier Transform infrared spectroscopy*. CRC Press.
- Šlouf, M., Pilař, Jan., Dybal, J., Šloufová, I., Michálková, D., Lukešová, M., Zgadzai, O., Blank, A., and Filippov, S. K. (2018). UV degradation of styrene-butadiene rubber versus high density poly (ethylene) in marine conditions studied by infrared spectroscopy, micro indentation, and electron spin resonance imaging. *Polymer Degradation and Stability*, 156, 132-143. <https://doi.org/10.1016/j.polymdegradstab.2018.08.005>
- Sozzi, G., and Del Viscio, G. (2011). *Non sticky gum base for chewing gum* (US Patent 7.871.650).
- Stuart, B. H. (2004). *Infrared spectroscopy: Fundamentals and applications*. John Wiley and Sons.
- Sullivan, A.B., Hann, C.J. and Kuhls, G.H. (1991). *Vulcanization Chemistry Fate of Elemental Sulfur and Accelerator During Scorch Delay as Studied by Modern HPLC*. Papers of the American Chemical Society, Division of Rubber Chemistry.
- Takahashi, K., Fukazawa, M., Motohira, H., Ochiai, K., Nishikawa, H., and Miyata, T. (2003). A pilot study on antiplaque effects of mastic chewing gum in the oral cavity. *Journal of Periodontology*, 74(4), 501-505. <https://doi.org/10.1902/jop.2003.74.4.501>
- Thivya, P., Durgadevi, M., and Sinija, V.R.N. (2021). Biodegradable medicated chewing gum: A modernized system for delivering bioactive compounds. *Future Foods*, 4, 100054. <https://doi.org/10.1016/j.fufo.2021.100054>
- Tijani, A. O., Garg, J., Frempong, D., Verana, G., Kaur, J., Joga, R., Sabanis, C. D., Kumar, S., Kumar, N., and Puri, A. (2022). Sustained drug delivery strategies for treatment of common substance use disorders: Promises and challenges. *Journal of Controlled Release*, 348, 970-1003. <https://doi.org/10.1016/j.jconrel.2022.06.034>
- Wang, M., Zhu, J., Zhang, S., You, G. and Wu, S. (2019). Influencing factors for vulcanization induction period of accelerator/natural rubber composites: Molecular simulation and experimental study. *Polymer Testing*, 80, 106145. <https://doi.org/10.1016/j.polymertesting.2019.106145>
- Zou, K. H., Tuncali, K., and Silverman, S. G. (2003). Correlation and simple linear regression. *Radiology*, 227(3), 617-628. <https://doi.org/10.1148/radiol.2273011499>