

Synthetic fuel production from shredded scrap waste

Producción de combustibles sintéticos a partir de residuos de la fragmentación de chatarra

Produção de combustíveis sintéticos a partir de resíduos da fragmentação de sucata

Iván Ernesto Barragán-Gutiérrez*
Alfonso López-Díaz**
Wolfgang Krumm***

Fecha de recepción: 7 de abril de 2016

Fecha de aprobación: 20 de diciembre de 2016

Abstract

This technological innovation project involved material identification, and design, installation, implementation, and evaluation of a pilot plant with capacity of 10 t per batch to recover materials and produce synthetic fuels (oil, syngas and solid) from shredded scrap waste. The results showed the proper way to separate materials (metals, and organic and inert compounds), and to perform the pyrolysis process to produce gas, oil, and coke as synthetic fuels from organic waste. The process started with the physicochemical characterization of the waste, followed by the selection of separation, sorting and processing technologies, and the definition of pyrolysis process parameters. Finally, the synthetic fuels were characterized, and uses for the furnace billet, ladle preheating, internal combustion engines, and auto generation were suggested. The results showed 82 % recovery of magnetic and non-magnetic metals, and production of synthetic fuels with PCI between 20 650 and 36 900 kJ/kg.

Keywords: energy; scrap; scrap waste; synthetic fuels; waste treatment.

Resumen

Presenta los resultados de un proyecto de innovación tecnológica que consistió en identificar materiales y diseñar, montar, poner en marcha y evaluar una planta piloto, con capacidad de 10 toneladas por lote, para recuperar materiales de los residuos del proceso de fragmentación de chatarra y producir combustibles sintéticos líquidos, sólidos y gaseosos a partir de ellos. Los resultados indican la forma adecuada de separar los materiales (metales y compuestos orgánicos e inertes) y de desarrollar el proceso de pirólisis para producir gas, aceite y coque sintéticos como combustibles a partir de los residuos. Se parte de la caracterización físico-química de los residuos; luego, se seleccionan las tecnologías de separación, clasificación y procesamiento, y se definen los parámetros del proceso de pirólisis; finalmente, se realiza la caracterización de los combustibles sintéticos y se sugieren usos para su empleo en el horno de palanquilla, en el precalentamiento de cucharas, en motores de combustión interna y en la autogeneración de electricidad. Los resultados indican la recuperación del 82 % de los metales magnéticos y no magnéticos y la obtención de combustibles sintéticos con PCI entre 20.650 y 36.900 kJ/kg.

Palabras clave: chatarra; combustibles sintéticos; energía; residuos de chatarra; tratamiento de desechos.

* M. Sc. Siderúrgica Nacional SIDENAL S.A. (Sogamoso-Boyacá, Colombia).

** Ph. D. Universidad Tecnológica y Pedagógica de Colombia (Tunja-Boyacá, Colombia). alfonso.lopez@uptc.edu.co.

*** Ph. D. Universidad de Siegen (Siegen, Alemania). wk@enerma.de.

Resumo

Apresenta os resultados de um projeto de inovação tecnológica que consistiu em identificar materiais e desenhar, montar, pôr em marcha e avaliar uma planta piloto, com capacidade de 10 toneladas por lote, para recuperar materiais dos resíduos do processo de fragmentação de sucata e produzir combustíveis sintéticos líquidos, sólidos e gasosos a partir dos mesmos. Os resultados indicam a forma adequada de separar os materiais (metais e compostos orgânicos e inertes) e de desenvolver o processo de pirólise para produzir gás, azeite e coque sintéticos como combustíveis a partir dos resíduos. Parte-se da caracterização físico-química dos resíduos; depois, selecionam-se as tecnologias de separação, classificação e processamento, e definem-se os parâmetros do processo de pirólise; finalmente, realiza-se a caracterização dos combustíveis sintéticos e sugerem-se usos para sua utilização no forno de tarugos, no preaquecimento de painéis, em motores de combustão interna e na autogeração de eletricidade. Os resultados indicam a recuperação de 82 % dos metais magnéticos e não magnéticos e a obtenção de combustíveis sintéticos com PCI entre 20.650 e 36.900 kJ/kg.

Palavras chave: sucata; combustíveis sintéticos; energia; resíduos de sucata; tratamento de resíduos.

I. INTRODUCTION

Energy production from waste (Waste to Energy) has gained popularity thanks to the search for solutions that are sustainable for the environment, society and economy. Energetic valorization of waste allows decreasing greenhouse emissions and waste final disposal in sanitary landfills, and increasing material retrieval. The world siderurgic industry has identified practices to rationally and efficiently use energy, which is intensively use in this industry, and to take advantage of the co-products resulted from the preparation and transformation of raw material and supplies into finished steel products. The Ministry of Environment and Sustainable Development of Colombia has developed a siderurgic NAMAS (Nationally Appropriate Mitigation Action) [1] that includes activities such as using waste to produce fuels, like the project described in this paper.

SIDERÚRGICA NACIONAL SIDENAL S.A. is located in the industrial park of Sogamoso (Department of Boyacá). This siderurgic annually process 250 000 tons of steel, manufacturing products for construction, such as bars, profiles, rebars, and meshes. SIDENAL is a semi-integrated siderurgic that uses scrap as raw material, which is fused in an electric arc furnace.



FIG. 1. Pile of shredded scrap waste. Source: SIDENAL S.A.



FIG. 2. Material composing the waste. Source: SIDENAL S.A.

The company develops innovative projects aimed at improving competitiveness through energy efficiency and production increase. For this reason, the company signed an agreement with the *Universidad Pedagógica y Tecnológica de Colombia (UPTC)* through the *Instituto de Investigación e Innovación en Ciencia y Tecnología de los Materiales (INCITEMA)*, and hired the services of SPIN OFF ENERMA at the Siegen University (Germany) to model processes and analyze products. The project was conducted between 2012 and 2015, and was funded by COLCIENCIAS (invitation 548 of 2012), which gives tax benefits for investing in Sciences, Technology and Innovation.

Before loading up the scrap to the electric arc furnace, a 5000 HP METSO shredder with approximate capacity of 800 t/day was used to reduce the scrap size. Shredding produces 11 % of waste that is composed of 12 % of non-magnetic metal (stainless steel, magnesium alloy, brass, zamak, aluminum alloy, cupronickel, copper allow, and zinc alloy), 12 % of materials with organic compounds (elastomer, foam, plastic, fiber, rubber, and biomass), and 77 % of inert material (dirt, stone, and glass). 1400 t of waste are produced monthly, which motivated the study to recover materials, and assess their energetic value (Fig. 1 and 2).

This research aims to analyze the shredded scrap waste energetic transformation, and the material recovery through innovation: design, implementation, stabilization, and product analysis of a pilot plant of material separation and classification, and thermic

processing of organic compounds to produce synthetic fuels.

II. STATE OF THE ART

In order to produce scrap, reduction of its size is necessary, for which, usually, potent shredders and material separation and classification processes are used. Manufacturing plants that receive automobiles to be shredded have named the waste that is left after the ferrous material is separated as Auto Shredder Residues (ASR). Although shredded vehicles are only a fraction of the total scrap received by SIDENAL S.A., waste composition is highly similar to that reported in several studies on ASR treatment [2]. Other research groups have determined that the most suitable ASR treatment is the pyrolysis process due to its capability to recover materials, and transform the organic fraction into useful products for the siderurgic. In Colombia, projects regarding the ASR and its treatment by pyrolysis to produce fuels from solid organic residues are still lacking.

Pyrolysis plant suppliers recommend to begin with a pilot plant to scale to determine the design and development parameters of the definitive plant, as well as to validate the material's behavior, adoption, and production capability to recover fuels and other inorganic materials as indicated by Dr. Roy for the Canadian company PYROVAC [3], and for the German company SICON GmnH [4]. Additionally, Kubik [5] concluded that more applications of waste transformed by pyrolysis (according to the plant technology type), particularly in the cogeneration field, are expected. Finally, parametrization of the pilot pyrolysis plant control variables for the treatment of shredded organic residues in the siderurgic is fundamental to guarantee the stability and homogeneity of the obtained fuels [6].

III. FUNDAMENTAL CONCEPTS OF PYROLYSIS AND METAL SEPARATION BY EDDY PARASITIC CURRENTS

Pyrolysis is defined as a thermic degradation in absence of oxygen that transforms raw material into several reactive intermediates products: solid (carbon), liquid (high-molecular-weight compounds that condense when cooled off), and gas (low-molecular-weight gases). The pyrolysis process is complex because of the many factors that must be considered, for instance, raw material composition, and experimental conditions.

In general, two possible steps in any pyrolysis process are accepted: *i*) primary pyrolysis, which involves devolatilization of the material when different reaction zones, corresponding to the thermal decomposition of the main components, may appear; and *ii*) secondary pyrolysis, which involves secondary decomposition with reactions in a solid matrix, as well as secondary reactions between volatile compounds (homogeneous reactions), or between volatile compounds and carbon residues (heterogeneous reactions). The first stage mainly implies dehydration, dehydrogenation, decarboxylation, or decarbonylation reactions. The second stage includes processes like cracking (thermic or catalytic), where heavy compounds get broken and transformed into gases or coal dust. These heavy compounds may be transformed into gases such as CO, CO₂, CH₄ and H₂ as a result of reactions with reducing agents such as partial oxidation, or condensation and polymerization.

Another innovation of this project was the acquisition of an Eddy current (also called Foucault current) separator, which generates parasitic currents in non-magnetic metals that, in turns, create a magnetic field that facilitates current separation as described below.

Under certain assumptions (uniform material, uniform magnetic field, no skin effect, etc.), power loss, due to Foucault currents per unit of mass, of a thin film or wire may be calculated using equation (1) [7].

$$P = \frac{\pi^2 B_p^2 d^2 f^2}{6k\rho D}, \quad (1)$$

Where, P is the power loss per unit of mass (W/kg), B_p is the peak magnetic field (T), D is either the film thickness or the wire diameter (m), F is the frequency (Hz), K is a constant equal to 1 for a thin film, and equal to 2 for a thin wire, ρ is the material resistivity (Ω m), and D is the material density (kg/m³).

Parasitic currents induced in the non-magnetic metal fractions facilitate the separation of the metals from the scrap waste current, thus allowing the scrap waste recovery, and the cleaning of the material that will be processed in the pyrolysis plant.

IV. CONTENT OF THIS STUDY

A. Scrap waste characterization

Initially, sampling of the 76 000 tons of accumulated waste was designed and applied according to the ISO 2859-1:1999 standard. We selected 8 georeferenced locations, and stratified the inferior, medium, and superior levels of residue density and size for each one of them, based on the EPA practice recommendations [8]. The characterization of the scrap waste is shown in Tables 1 through 3.

TABLE 1
SCRAP WASTE DENSITY [9]

Stratum	Average density g/cm ³
Superior	0.78
Medium	0.79
Inferior	0.78

Despite the height of the waste pile, it is possible to observe that the material has uniform density, without any compaction effect, which ease the material analysis. Additionally, to characterize the particle size of the materials composing the pile of waste, three meshes were employed: ½", 2", and 6". A higher proportion of particle sizes below ½", and a lesser proportion of sizes above 6" were observed (Table 2).

TABLE 2
SCRAP WASTE SIZE [9]

Stratum	Granulometric classification - Weight (kg) retained in the mesh							
	≤1/2 "	%	{½", 2")	%	{2",6")	%	>6 "	%
Superior	1502	81	251	14	89	5	9	0
Medium	1038	71	359	24	66	4	8	1
Inferior	886	69	318	25	80	6	1	0

Finally, the energetic potential of the carbonaceous material in the pile of waste showed a calorific value

superior to 1210 kcal/kg, which indicates the utility to process it as fuel (Table 3).

TABLE 3
PROXIMATE ANALYSIS OF MATERIALS WITH SIZE BELOW ¼" [9]

DATE	SAMPLE IDENTIFICATION	FREE HUMIDITY	RESIDUAL HUMIDITY	ASH	VOLATILE M.	CALCINATION LOSS	CALORIFIC VALUE	SULFUR	
17/02/14	INERT	INFERIOR	1.51	2.4	78.35	24.76	21.65		
		MEDIUM	2.67	2.22	71.01	21.37	28.99		
		SUEPERIOR	2.57	2.07	72.50	20.79	27.5		
	SOLID WASTE	INFERIOR	5.35	2.75	80.82	20.75	19.18	1210	0.22
		MEDIUM	5.65	2.34	80.46	23.78	19.54	1337	0.17
		SUEPERIOR	9.05	2.81	80.11	24.54	19.89	12.42	0.23

B. Pyrolysis process

Based on the characterization of the materials composing the pile of waste, the material separation equipment (screening and Eddy currents) of the pilot plant was designed, selected, and installed. Once the materials were separated and classified, the organic fraction was processed in a pyrolysis plant that thermally depolymerized the carbonaceous material in the absence of oxygen, and at a pressure higher to

the atmospheric one. The pilot plant is composed of a rotating horizontal reactor, a solid-liquid separation system, a vertical capacitor bank to separate liquid-gas phases, an anti-explosion system with water traps, a gas burner/scrubber, a boiler to produce vapor, a cooling tower, storage ducts and tanks, a digital instrumentation and control board, a dual fuel system (gas-liquid), and an alarm system (Fig. 3 and 4).

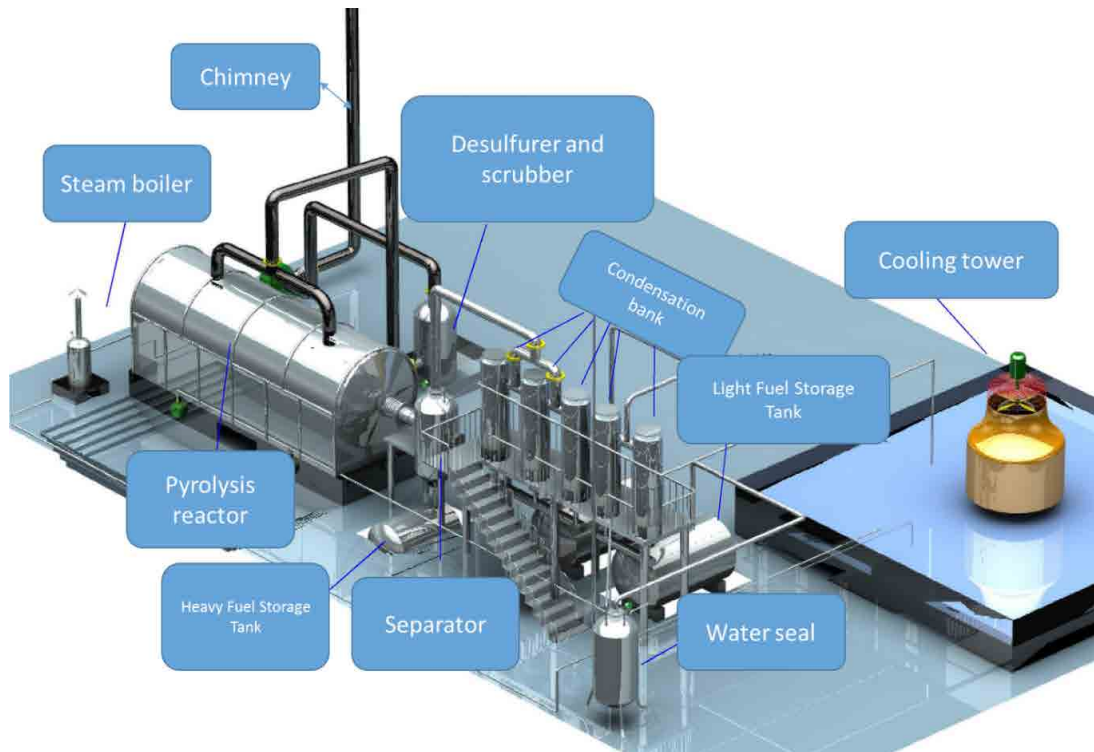


FIG. 3. Components of the pilot pyrolysis plant.



FIG. 4. Pyrolysis plant working and showing the synthesis gas emission.

For plant balance, we conducted simulations and thermodynamic analyses of mass, energy, and gases kinetics, with the goal of estimating the ideal operation conditions to achieve a maximum efficiency in the transformation into synthetic fuels (light and heavy fuels, gas, and pyrolytic coke) [10]. The optimal

operation curve for time and temperature, where the lowest fuel production was achieved (Fig. 5), allows to evaluate the temperature gradient, and the correlation between the pyrolysis reactor external and internal temperatures, as well as the gas temperature inside the scrubber.

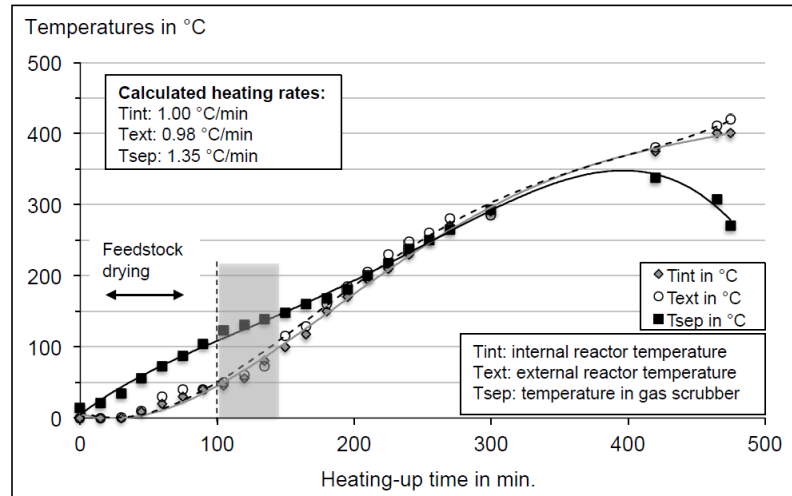


FIG. 5. Reactor heating curve [10].

The results of the plant mass balance showed that most of the transformed material in the pyrolysis reactor is pyrolytic char, followed by medium molecular weight synthetic oil (Table 4).

TABLE 4
PYROLYSIS PLANT MASS BALANCE [10]

Input and output fractions	Fraction mass (kg)	Product distribution X_m , in mass %
Feedstock input (m_s)	5000.0	
Char (m_{char})	2962.0	59.2
Metals (m_{metals})	77.0	1.5
HP Oil (m_{hpoil})	32.0	0.6
MP Oils (m_{mpoil})	1440.8	28.8
LP Oils (m_{lpoil})	23.8	0.5
Sum of measured fractions	1535.6	90.7
Steam evaporation during feedstock drying (90 % mass content)	265.4	5.2
Pyrolysis gas (residual mass)	202.1	4.0
Sum of all fractions	5000.00	100.0

C. Products of the scrap waste pyrolysis

The characterization of the synthetic fuels obtained at the scrap waste pilot plant showed that the pyrolytic char has an important energetic potential, and a high

fraction of ash that anticipates the necessity of an additional separation process to concentrate the carbon fraction indicated by the analysis (Table 5 and 6).

TABLE 5
SYNTHETIC COKE CHARACTERIZATION [10]

Parameter	SG	PC	Units
Moisture content (105 °C)	5.83	2.1	%
Dry residue (105 °C)	94.2	97.9	%
Ash (815 °C)	33.5	68.7	%
Carbon (dry solid fluid)	40.1	27.4	%
Carbon fixed (dry)	10.8	14.4	%
Volatiles (dry)	55.7	16.9	%
Nitrogen (dry solid fuel)	< 0.010	0.51	%
Hydrogen (dry solid fuel)	6.14	0.91	%
Gross caloric value (orig.)	18860	9500	kJ/kg
Gross caloric value (dry)	20030	9709	kJ/kg
Net caloric value (orig.)	18820	9267	kJ/kg
Net caloric value (dry)	18820	9524	kJ/kg
Total Bromine (dry solid fuel)	0.1	0.3	%
Total Chlorine (dry solid fuel)	1.79	3.51	%
Total Fluorine (dry solid fuel)	0.0043	0.11	%
Total Sulfur (dry solid fuel)	0.15	0.28	%
SG: Shredder granules			
PC: Pyrolysis char			

The analysis of the synthetic oil fuels produced in the pyrolysis process indicated that the medium molecular weight oil was not only the most produced, but also the one with the best energetic behavior (Table 6). Additionally, it is noteworthy the presence of compounds such as bromine, chlorine, fluorine, and sulfur (Table 6).

TABLE 6
SYNTHETIC OIL FUEL CHARACTERIZATION [10]

Parameter	HP Oil	MP Oil	LP Oil	Units
Appearance	homogeneous		2-phases	
Floating oil content	-	>99	60	%
Free water	-	<1	40	%
Solid phase		<1	<1	%
Consistency	Pasty	liquid	liquid	
Color	Black	black	brown/black	
Smell	Organic			
Moisture content	15.3	0.36	3.78 (oils)	%
Ash (815 °C)	14.5	4.83	4.1	%
Carbon (org.)	66.4	29.9	19.3	%
Carbon fixed	35.1	<1	<1	%
Volatile matter content (org.)	50.4	>95	>95	%
Nitrogen (org.)	<0.01	<0.1	<0.1	%

Hydrogen	7.2	6.53	7.52	%
Gross caloric value (orig.)	25200	33780	20650	kJ/kg
Gross caloric value (dry)	29750	33900	34400	kJ/kg
Net caloric value (orig.)				kJ/kg
	23590			
	32430			
	18710			
Net caloric value (dry)	28290	32560	32430	kJ/kg
Bromine (oil)	0.21	0.037	0.032	%
Chlorine (oil)	1.82	0.05	0.043	%
Fluorine (oil)	0.063	0.0082	0.013	%
Sulfur (oil)	0.38	0.22	0.26	%
LP: low density pyrolysis oil (LP Oil)				
MP: medium density pyrolysis oil (MP Oil)				
HP: high density pyrolysis oil (MP Oil)				

Emission analysis (Table 7 and 8) was conducted to verify that emissions were in compliance with the environmental normativity, particularly with resolution 909 of 2008.

TABLE 7
ISOKINETIC GAS MONITORING [11]

		UNIT	MP- SO _x - NO _x	DIOXINS and FURANS	HCl and HF
ORSAT					
Carbon dioxide	CO ₂	%	0.3	2.0	5.4
Oxygen	O ₂	%	20.4	17.3	11.2
Carbon monoxide	CO	%	0.0	0.0	0.0
Nitrogen	N ₂	%	79.3	80.7	83.4
GASES					
Humidity	H	%	12.1	6.6	8.2
Temperature	Ts	°C	53.0	37.4	45.9
Speed	Vs	m/s	3.06	2.97	3.69
Standard flow	Qst	m ³ /s	0.08	0.10	0.12

TABLE 8
EMISSION LEVELS [11]

FIXED SOURCES	POLLUTER	EMISSION mg/ m ³
Pyrolyzer	MP	5.6
	SO ₂	15.1
	NO ₂	48.4
	VOC _s	-*
	Dioxins and Furans	0.33195**
	Hcl	3.477
	HF	0.110

V. RESULTS

This study demonstrated that innovative technology of material recovery and energetic transformation into synthetic fuels from scrap waste, by means of pyrolysis allowed in SIDENAL:

- To monthly recover more than 960 tons of soil to be potentially used as an agricultural substrate or fertilizer.
- To monthly recover more than 210 tons of metal to recycle.
- To transform every month 330 tons of organic compounds into synthetic industrial fuels: 30 % oil, 60 % char, and 10 % gas.

The pilot plant allowed to develop the innovative technology to process shredded solid waste to move the project forward to a second phase, which initiated thanks to the benefits granted by the *Agencia Nacional de Licencias Ambientales (ANLA)*. The investments will take place throughout the upcoming years. In phase II, stored and fresh waste will be processed, with a capacity of 200 t/day.

The technology that will be used is highly reliable, and comes from German companies that comply with the strict European and North American environmental regulations for this kind of activities.

This project at this scale is a real referent to promote close cycle industries, and to recover materials from syderurgics and sanitary landfills.

VI. CONCLUSIONS

The synthetic fuel characterizations suggest to develop the following uses in SIDENAL:

- a. Fuel oil: Steel billet furnace. Mixed with the current fuel, and adjusting a filter system, 30 % of the fuel might be substituted with only one reactor of 10 tons.
- b. Gas: pyrolysis reactor realignment, adjusting burners, and a pressure regulation system for the supply system. Moreover, syngas might be used in a cogeneration system (electric-thermal), utilizing the heat residue to dry the material that entries the reactor.
- c. Coke or char: briquette to be used in cement industry, mixing it with fluff residues, for which an additional separation system is required.
- d. Inert material: mixed with whitewashing material that comes from white slag could be useful for soil remediation.

The study had the following conditions:

- a. The characterized material was sampled in the pile of waste by size and shape.
- b. Additional control variables such as flow, pressure, and gas analysis in real time were reported and monitored.
- c. Meshes of different sizes were used to sieve the residues in thinner fractions.

REFERENCES

- [1] Environmental business and technologies S.A.S., “Formulación de dos Acciones de Mitigación Nacionalmente Apropriadas el Sector Industrial - Subsector Siderúrgico (NAMAs),” EBT, Bogotá, 2015.
- [2] J. Madías, “Nuevos adelantos: Procesamiento de chatarra para acerías,” *Acero Latinoamericano*, vol. 527, pp. 48 - 56, Jul. 2011.
- [3] C. R., “Pathway to Large Scale Production of Customized Biochar A Keynote Speech,” in *4th IBI Congress*, Beijing, 2012.
- [4] SICON, “SICON,” 2012. [Online]. Available: <http://sicontechnology.com/>.
- [5] K. Kubik, “Theoretical thermodynamic analysis of car residues microwave pyrolysis products, using high-temperature steam for small scale electricity generation,” *Royal Institute of Tehcnology*, Stockholm, 2008.
- [6] C. Pasel and W. Wanzl, “Experimental investigations on reactor scale-up and optimisation of product quality in pyrolysis of shredder waste R,” *Fuel Processing Technology*, vol. 80 (1), pp. 47-67, 2003. DOI: [http://doi.org/10.1016/S0378-3820\(02\)00187-X](http://doi.org/10.1016/S0378-3820(02)00187-X).
- [7] NCERT, *Physics texbook*, 2014.
- [8] United States Environmental Protection Agency, *RCRA Waste Sampling Draft Technical Guidance Planning, Implementation and Assessment*, Washington, DC 20460: Office of Solid Waste U.S. Environmental Protection Agency, 2002.
- [9] INCITEMA, “Resultados plan de calidad para las pruebas de caracterización de residuos,” Tunja, Boyacá: Colombia, 2013.
- [10] ENERMA, *Final report SIDENAL Pyrolysis plant*, Siegen: ENERMA, 2015.
- [11] A&MA PLANETA AZUL, “Monitoreo emisiones en chimenea pirolizador,” Sogamoso Boyacá, 2014.