

# Study of the calcination process of two limonitic iron ores between 250 °C and 950 °C

Estudio del proceso de calcinación en dos minerales de hierro limoníticos entre 250 °C y 950 °C

Estudo do processo de calcinação em dois minerais de ferro limoníticos entre 250 °C e 950 °C

Fecha de recepción: 20 de septiembre de 2016

Fecha de aprobación: 20 de marzo de 2017

Lisbeth Longa-Avello\*  
Cristina Pereyra-Zerpa\*\*  
Julio Andrés Casal-Ramos\*\*\*  
Pedro Delvasto\*\*\*\*

## Abstract

The dehydration process of two limonitic ores from Venezuela was studied between 250 °C and 950 °C by means of thermogravimetry, infrared spectroscopy, and x-ray diffraction. These techniques indicated for both minerals that the goethite-to-hematite transformation occurred in the range of 250-350 °C. In addition, the x-ray diffraction showed a structural re-arrangement within the orebody above 350 °C, temperature above which only the hematite structure is recognizable. Finally, infrared spectroscopy revealed that such transformation implies the loss of structural OH- functional groups, characteristic of the limonite.

**Keywords:** Iron Ore; Limonite; Thermal Modification of Minerals.

## Resumen

Se estudió el proceso de deshidratación de dos minerales limoníticos de Venezuela entre 250 °C y 950 °C, usando termogravimetría, espectroscopia infrarroja y difracción de rayos x. Para ambos materiales, estas técnicas indicaron que la transformación de goethita a hematita ocurrió en el rango de 250 °C a 350 °C. Adicionalmente, la difracción de rayos X mostró un rearrreglo estructural dentro de la mena a una temperatura por encima de 350 °C; a temperaturas mayores, solo se reconoce la estructura de la hematita. Finalmente, la espectroscopia infrarroja reveló que la transformación de goethita a hematita implica la pérdida de grupos funcionales de OH- estructural característicos de la limonita.

**Palabras clave:** Limonita; Mineral de hierro; Modificación térmica de minerales.

\* Universidad Simón Bolívar (Caracas, Venezuela).

\*\* Universidad Simón Bolívar (Caracas, Venezuela).

\*\*\* M.Sc. Universidad Simón Bolívar (Caracas, Venezuela).

\*\*\*\* Ph. D. Universidad Industrial de Santander (Bucaramanga-Santander, Colombia). delvasto@uis.edu.co. ORCID: 0000-0001-5602-7921.

## Resumo

Estudou-se o processo de desidratação de dois minérios limoníticos da Venezuela entre 250 °C e 950 °C, usando termogravimetria, espectroscopia infravermelha e difração de raios x. Para ambos os materiais, estas técnicas indicaram que a transformação de goethita a hematita ocorreu no intervalo de 250 °C a 350 °C. Adicionalmente, a difração de raios X mostrou um rearranjo estrutural dentro do minério a uma temperatura por cima de 350 °C; a temperaturas maiores, só reconhece-se a estrutura da hematita. Finalmente, a espectroscopia infravermelha revelou que a transformação de goetite a hematita implica a perda de grupos funcionais de OH- estrutural característicos da limonita.

**Palavras chave:** Limonita; Mineral de ferro; Modificação térmica de minérios.

### Cómo citar este artículo:

L. Longa-Avello, C. Pereyra-Zerpa, J. A. Casal-Ramos, and P. Delvasto, "Study of the calcination process of two limonitic iron ores between 250 °C and 950 °C," *Rev. Fac. Ing.*, vol. 26 (44), pp. 33-45, May. 2017

## I. INTRODUCTION

Limonite is an iron oxide hydroxide, whose general chemical formula is  $\text{FeO}(\text{OH}) \cdot n\text{H}_2\text{O}$  [1, 2]; it has variable quantities of goethite ( $\text{FeOOH}$ ) and hematite ( $\text{Fe}_2\text{O}_3$ ), and may be accompanied by certain accessory minerals that contain silicon, aluminum, phosphorus, and nickel, among other elements. Despite being a highly hydrated iron oxide, the limonite may be considered attractive to obtain metallic iron after the application of a heat treatment of calcination that modifies the structural arrangement of the chemically bonded water and the OH- groups, allowing its transformation into hematite above a critical temperature [2, 3]. The determination of this temperature, and the knowledge of the mineralogical changes undergone by the limonitic ore during a calcination process are of vital importance for the continuous improvement of the mineral beneficiation, and the metallurgical processes in both iron [3] and nickel industries [4].

Many iron-ore producing countries have been forced to assess the feasibility of using hydrated oxides and iron oxy hydroxides (goethite and limonite) as an alternative resource to obtain reduced iron. To be used economically, these minerals require a special reduction process due to their low iron content [5]. Currently, many processes of mineral beneficiation have been devised for this type of ores. One of the current operational trends consists in increasing the temperature of the reduction zone, in order to attain a higher productivity, due to the thermodynamic improvement of the reaction conditions [6]. For this reason, it has been suggested to evaluate the possibility of applying a heat treatment prior to the reduction stage, in order to reduce the moisture content of the ore, as well as its chemically bound water content [7]; this procedure may also improve the reactivity characteristics of the ore, which can save processing time in the reduction stage. Another problem of limonitic ores is their strong tendency to present impurities; in fact, a typical case is the presence of phosphorous, which is a deleterious element, very difficult to control during the reduction and steelmaking stage. This feature strongly limits the use of phosphorous limonite ores to produce iron and steel. Nevertheless, these ores can be dephosphorized through a calcination process followed by leaching with acids or strong alkalis [3]. In this case, it is required to know how the solid is affected by the calcination

process, since its final structure will modify its specific surface area, which in turn, will sign the effective leaching of phosphorus, increasing the efficiency of the hydrometallurgical beneficiation process [3]. In summary, the advantages of applying a calcination treatment as a preliminary stage of the reduction process are based on improving the efficiency of the reduction process itself, and the possibility of reducing or eliminating the presence of undesirable elements in the reduction reactors. Additionally, the amount of ore entering the reactors during the production process would be reduced, facilitating, in such a way, the handling and transportation of materials within the facility.

Currently, the Venezuelan iron ore industry faces a critical situation, in which the premium quality minerals are running out, resulting in an enrichment of the exploitation mining fronts with low-grade limonitic fractions that also have higher phosphorus content. This situation is common in other parts of the world, such as Australia [7], and implies major challenges for the industry, in terms of mineral handling and further processing. For this reason, it is necessary to conduct an exploratory research to understand the behavior of this type of limonitic ores during calcination. Based on the afore-mentioned situation, this study was carried out with the aim of evaluating the effect of a heat treatment of calcination at different temperatures on the crystal structure of two limonitic iron ores from southern Venezuela. To reach this objective, we applied several analytical techniques, including thermogravimetry (TG), X-ray diffraction (XRD), and Fourier transform infrared spectroscopy (FTIR).

## II. EXPERIMENTAL METHODOLOGY

### A. Minerals tested

Two limonitic iron ores (locally known as “limonitic crusts”) were obtained from “Los Barrancos” and “Cerro Bolívar” iron ore deposits, both located in the Bolivar State, in southern Venezuela. Before all the tests were made, the ores were crushed to a particle size smaller than 90  $\mu\text{m}$  using an agate mortar.

### B. Experimental work

**1) Thermogravimetric analysis (TGA):** For the analysis, a CAHN/VENTRON thermobalance (precision 10 mg) was used. A  $100 \pm 10$  mg sample

of iron ore was placed in a 9-mm diameter platinum basket that was connected to the thermobalance through a quartz thread. The set was placed inside a GORDON® cylindrical convection oven, preheated to the required temperature. Voltage was measured and recorded every 1/15 seconds until it reached a constant value. With the aim of knowing the mass loss behavior of the mineral as a function of the temperature, this test was repeated at different temperatures from room temperature to 950 °C, using a heating rate of 10 °C/min.


**2) X-Ray diffraction analysis (XRD):** The X-Ray diffraction analysis was carried out on original condition samples (no heat treatment), and on treated samples in a muffle furnace during one hour at the following temperatures (°C): 250, 350 and 950. The diffractograms were obtained with a diffractometer Philips XPERT Pro, with a Co K $\alpha$  radiation (wave length  $\lambda=1.78897$  Å), in a range between  $5^{\circ}\leq 2\theta\leq 90^{\circ}$ . A voltage of 40 kV, a current of 20 mA, and a scanning rate of 0.02 2 $\theta$ /s were used. The different phases present in the sample were identified through a detailed comparison with the goethite and hematite files, contained in the database of the PDF-ICDD (Powder Diffraction File – International Centre for Diffraction Data).

**3) Fourier-Transform Infrared Spectroscopy Analysis (FTIR):** This analysis was carried out on both iron ores with and without heat treatment for one hour, in a temperature range between 250 °C and 950 °C (at 100 °C intervals). The FTIR spectra were obtained with a BRUKER TENSOR 7 spectrometer, and were recorded and standardized through baseline corrections and atmospheric compensation. The equipment was calibrated using a potassium bromide (KBr) pellet. Subsequently, sample pellets diluted in KBr were made using a small portion of sample (mass ratio 99:1).


### III. RESULTS AND DISCUSSION

#### A. TGA Analysis


We determined the mass loss during the calcination process of the studied minerals by means of a TGA analysis. The diagrams in figures 1 and 2 show that as the temperature increases, the percentage of mass loss progressively increases, with a greater mass loss observed at applying the calcination heat treatment at 950 °C. The dehydration of limonite involves the loss of free water, chemically bound water, and hydroxyl groups that form part of the goethite structure [8, 9], to finally obtain the hematite structure. This process is described by means of the global reaction shown in equation (1).




This dehydration process comprises three stages (Fig. 1 and 2): The first stage occurs at temperatures between 250 °C and 350 °C, and it is basically related to the moisture loss in the mineral; the second stage, in the temperature range of 450-550 °C, is related to the loss of chemically bound water; and the last stage, at 550 °C, is related to the loss of OH<sup>-</sup> groups of the goethite structure, forming hematite (Fe<sub>2</sub>O<sub>3</sub>), as shown in equation (2) [8, 9].



It is estimated that the loss of free water occurring during the first dehydration stage, due to the heat treatment at low temperatures, can be explained by the fact that this water is either absorbed on the surface or occluded into the microscopic pores of the iron ore microstructure [8, 9]. In addition, during the last stage of calcination, large amounts of OH<sup>-</sup> groups are emitted out as water vapor from the remnant goethite or from the initially formed hematite, the latter still containing hydroxyl groups in its structure [8-11]. Such functional groups would be combined as a result of the atomic movement induced by the high treatment temperatures. The slope changes observed in figure 3 are due to the different ways in which the water may be present in the samples.

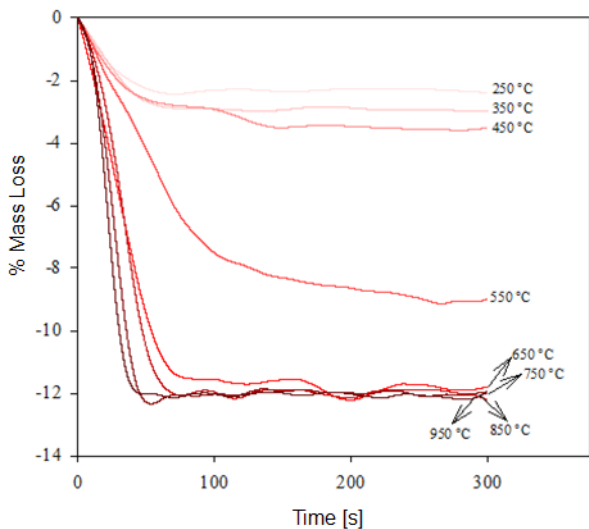

**FIG. 1.** Thermogravimetry of the “Los Barrancos” iron ore deposit, representing the mass loss of the samples in function of the time for the specified calcination temperature.

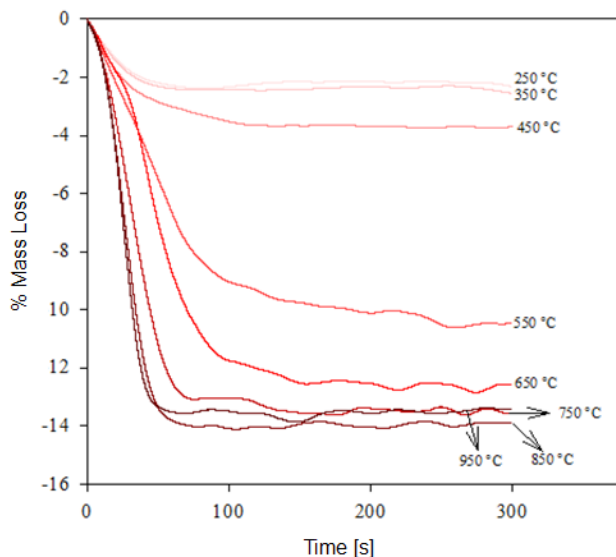


**FIG. 2.** Thermogravimetry of the “Cerro Bolivar” iron ore deposit, representing the mass loss of the samples in function of the time for the specified calcination temperature.

At the beginning of the dehydration process, *i.e.* at temperatures below 250 °C, the water absorbed by the mineral is rapidly removed [10]. Once this temperature is exceeded, goethite must have completed its phase transformation process, becoming hematite, which was proven through the XRD (Fig. 4 and 5) and FTIR

(Fig. 6 and 7) analyses. However, the structure of the newly-formed hematite still contains an excess of hydroxyl units [10]. For this reason, we did not observe a major change in the percentage of mass loss in any of the iron ores (Fig. 1 and 2), where the heat treatment was applied to 250 °C.

As the temperature rises, the reaction preferably starts in the places where the surface per unit volume is higher. Because the hematite has begun to emerge on the goethite surface, the process does not continue progressively, since this last phase is occluded by the newly-formed hematite, and therefore, it will be necessary to increase the temperature so that dehydration of the mineral continues [9]. Furthermore, as temperature increases, so does the pressure of the water contained inside the mineral, resulting in the formation of internal microporosities [10]. On that basis, since the diffusivity of  $Fe^{3+}$  and  $O^{2-}$  is rather slow [9], it can be assumed that this is the reason why we did not observe a major change in mass loss % for both minerals, in the range between 250 °C and 350 °C.

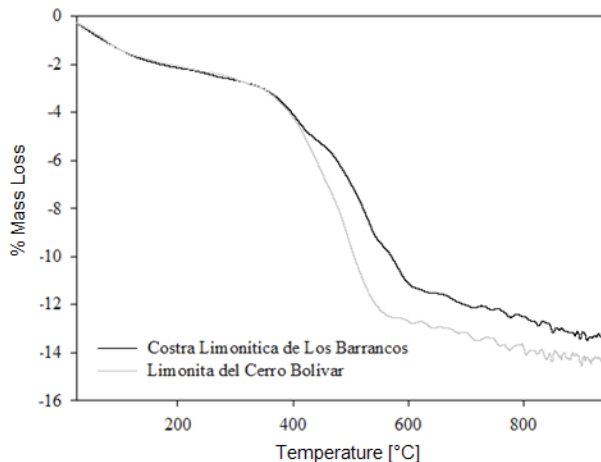

**FIG. 3.** Mass loss [%] of the samples in function of the temperature, determined by thermogravimetry.

As shown in Figure 3, a significant increase in the slope occurred at temperatures between 300 °C and 450 °C; this increase corresponds to the sustained increase in pressure of the water contained into the mineral micropores, which makes them keep growing and subsequently join together [10]. This behavior continues until around 650 °C, temperature at which the coalescence of micropores generates macroporosities, which will facilitate the complete removal of the remaining water within the mineral

particle [10, 12]. With the generation of this new area at high temperature, the diffusion effects begin to take preponderance and Fe atoms can migrate, starting to adopt the shared octahedral arrangement that leads to the more condensed crystallographic phase of the hematite [12].

When the heat treatment is carried out at about 700 °C, there is an even greater mobility of the atoms in the crystal lattice, which leads to a further increase in the diffusional phenomena, whose outcome is a higher mass decrease in both samples, due to atomic rearrangement [10]. At 950 °C, the atomic movement within the crystal structure finishes, and the formation of the hematite is completed, accompanied by a decrease in anisotropy and the generation of an ordered structure [9].

### B. X-Ray Diffraction Analysis

Both iron-ore samples were characterized by X-ray diffraction, in their original condition and after being treated at different temperatures. The two main crystalline phases revealed in the original state of the material corresponded to goethite (Gt) and hematite (Hm), as shown at the bottom of figures 4 and 5. Goethite has an orthorhombic structure (lattice parameters:  $a = 9.95 \text{ \AA}$ ,  $b = 3.01 \text{ \AA}$ ,  $c = 4.62 \text{ \AA}$ ), while the hematite has a rhombohedral hexagonal structure, similar to corundum (lattice parameters:  $a = 5.035 \text{ \AA}$ ,  $c = 13.752 \text{ \AA}$ ) [13].

Within the analyzed diffraction range, eight peaks associated with hematite, and eight with goethite were detected. It is presumed that goethite is present in higher proportion than hematite, because the peaks associated with goethite show a higher relative intensity.

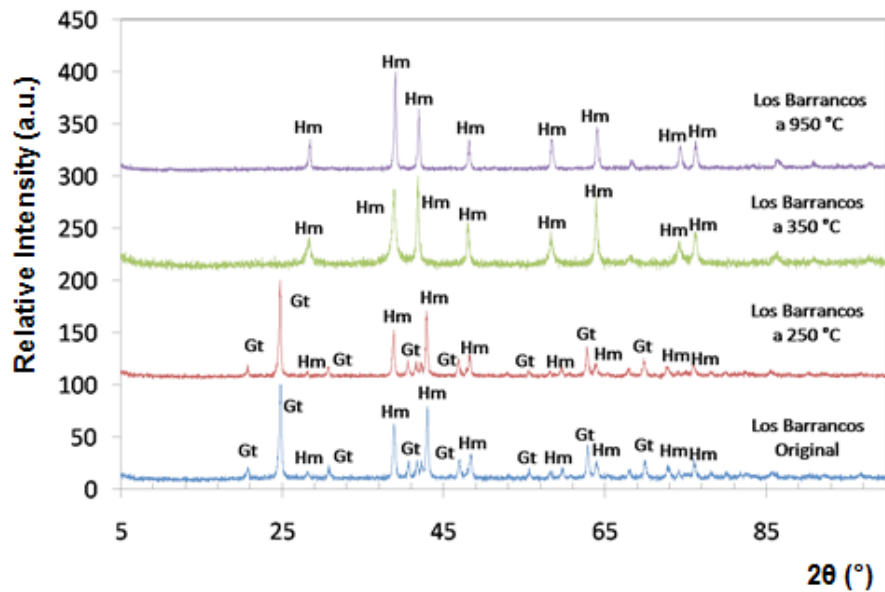


FIG. 4. Diffractograms of limonitic iron ore from “Los Barrancos” deposit, before heat treatment. Radiation  $K\alpha$ -Co (range 5°-90°).

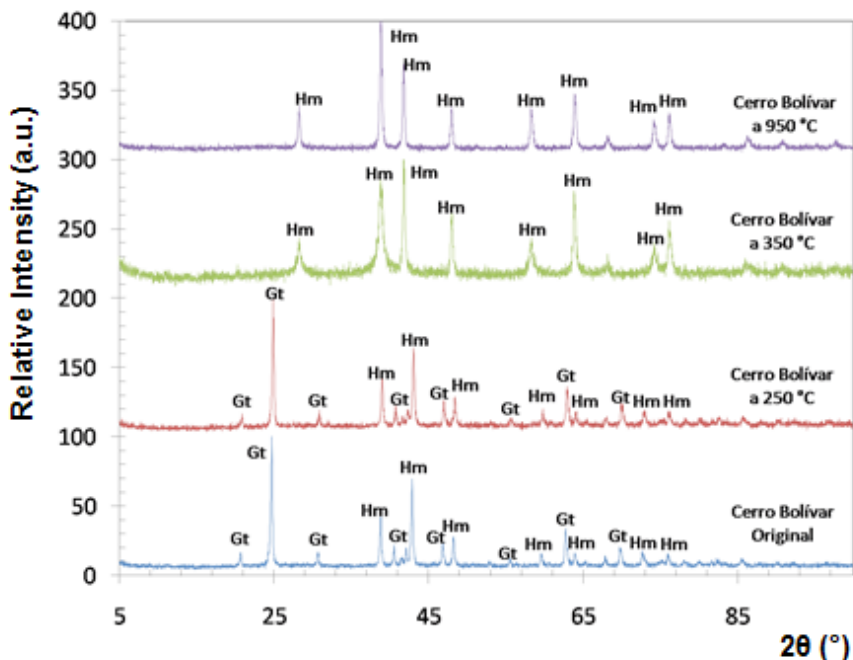


FIG. 5. Diffractograms of limonitic iron ore from “Cerro Bolívar” deposit, before heat treatment. Radiation  $K\alpha$ -Co (range  $5^\circ$ -  $90^\circ$ ).

The X-ray diffraction technique allowed to follow the changes that took place over the crystalline structure of limonitic minerals due to the increase in time and temperature of the heat treatment. Figures 4 and 5 show the diffractograms obtained for all temperatures during one hour of treatment. Between  $250^\circ\text{C}$  and  $350^\circ\text{C}$ , we observed a change in the diffraction peaks of the studied minerals, characterized by the disappearance of some of the peaks associated with goethite, which were present before the heat treatment and in the sample treated at  $250^\circ\text{C}$ . New peaks associated with hematite also appeared at temperatures above  $350^\circ\text{C}$ .

At room temperature and at  $250^\circ\text{C}$ , the peaks of goethite prevailed in the structure, whereas from  $350^\circ\text{C}$ , all peaks associated with goethite disappeared, and the hematite peaks were revealed, demonstrating that a re-arrangement occurred in the atomic positions of the goethite crystal lattice, thus being transformed into hematite. For both studied minerals, the transformation range was between  $250^\circ\text{C}$  and  $350^\circ\text{C}$ . This transformation is favored by the structural links existing between certain planes of the hematite and the goethite structures [14].

Several theories have been proposed to study the transformation of goethite to hematite at high temperatures. The heating causes dehydration of the goethite, resulting in slight modifications of its crystal structure. Transformation begins on the surface of the goethite, and then advances into the mineral, forming multiple microporosities, as it was deduced from the thermogravimetric analysis. Transformation may involve one or two intermediate stages of hematite [15]. The first stage (protohematite) is formed as a consequence of heating between  $250^\circ\text{C}$  and  $400^\circ\text{C}$ , while the second stage (hydrohematite) appears at heating temperatures above  $430^\circ\text{C}$ . Above  $800^\circ\text{C}$ , the structure of the relatively ordered hematite is obtained [16]. Some authors revealed that one of the main characteristics of the intermediate phases is the great similarity of their maximum diffraction peaks with those of the hematite [11, 15]. In this sense, Schwertmann [8] found that the different forms of hematite formed during the dehydration of goethite have a defective structure, which is characterized by the widening of the diffraction peaks. However, although the existence of such intermediate stages is not part of the scope of this paper, it is evident that many investigations support that a transformation of goethite to hematite occurs during heating at elevated temperatures.

### C. Fourier-Transform Infrared Spectroscopy Analysis (FTIR)

Analysis by Fourier-Transform infrared spectroscopy allowed studying the behavior of the functional groups present in the mineral. Figure 6 shows the infrared spectrum of limonitic iron ore, from the “Los Barrancos” deposit, with no heat treatment. In the spectrum, seven predominant bands can be noted: Four of them associated with stretching and strain vibrations of hydroxyl groups (A, D, E), two of them associated with water bending vibrations (B, C), and the last two bands related to the vibration of the Fe-O bond in the crystal arrangement of goethite and hematite (F, G) [16]. Figure 7 shows the bands for the limonitic iron ore from the “Cerro Bolívar” deposit, which were identified by the same letters, but with an apostrophe symbol (').

As mentioned above, it is very common for goethite to exhibit an excess of hydroxyl groups within its crystalline structure. Therefore, the structure of this mineral favors the presence of the OH vibrations in the FTIR spectrum. Its structure is composed of a compact hexagonal arrangement of oxygen atoms,

like most of the iron oxides and oxyhydroxides [8, 14]. The location of each atom within the mineral crystal lattice favors the formation of hydrogen bonds in two different directions, facilitating the presence of some hydroxyl groups in the structure [14]. For this reason, the infrared spectra of limonite show the stretching and strain vibrations of hydroxyl groups, which basically depend on the direction and strength of the atomic bond that characterizes these groups.

By way of comparison, it is observed that the bands associated with goethite, those related to water and OH groups vibrations, have a higher intensity in the case of the “Cerro Bolívar” ore (Fig. 7). On that basis, the assumption made earlier about the presence of more hydroxyl groups in this mineral can be verified, since it is expected that the transmittance intensity in that region of the spectrum is proportional to the concentration of functional groups within the structure [12]. It should also be noted that the spectra shown in figures 6 and 7 exhibit subtle spectral perturbations in the region between 1080  $\text{cm}^{-1}$  and 1125  $\text{cm}^{-1}$ , forming shoulders (Fig. 6) or small peaks (Fig. 7), which correspond to vibrations of Si-O bonds, indicating the minority presence of quartz or silicates within the natural goethite [18].

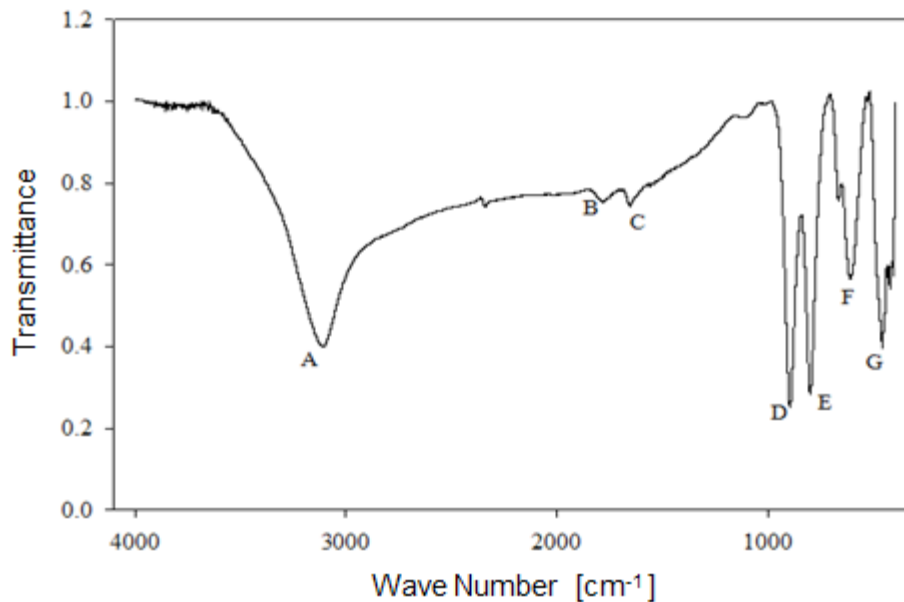


FIG. 6. Infrared spectrum of iron ore from “Los Barrancos” deposit before heat treatment.



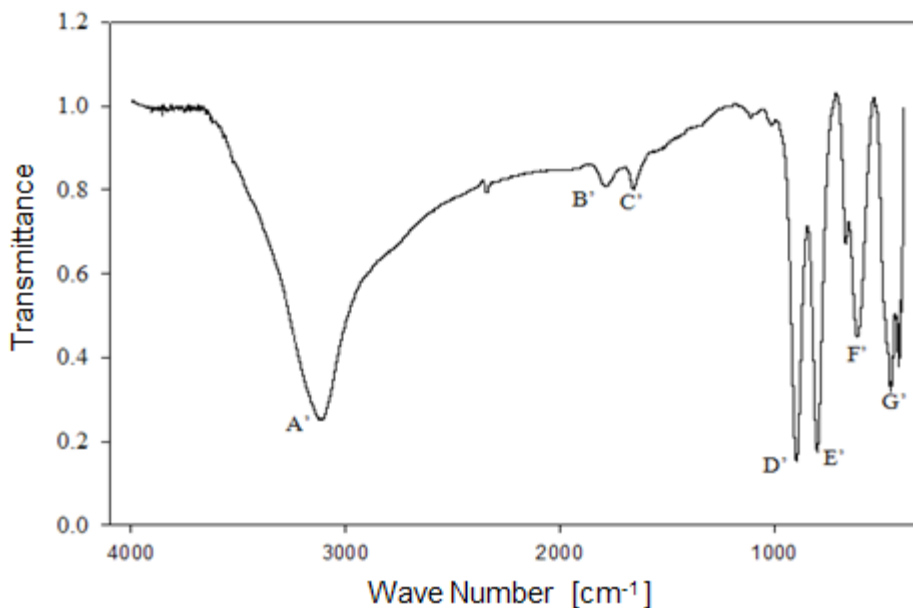


FIG. 7. Infrared spectrum of iron ore from “Cerro Bolívar” deposit before heat treatment.

On a preliminary basis, both iron ores present a similar dehydration process (Fig. 8 and 9), going through the same structural changes as the calcination temperature increases. The hematite formed from the goethite can inherit both the excess hydroxyl units and the structural characteristics of the initial goethite, as a consequence of heat treatment at low temperatures (around 300 °C), which help to distinguish the dehydroxylation process that is carried out during the thermal transformation [14]. In the following sections, we analyze in detail the behavior of the hydroxyl units in relation to the changes on the position and intensity of the FTIR spectral bands, during the thermal transformation of goethite to hematite observed in both limonite crusts obtained from the Venezuelan “Los Barrancos” and “Cerro Bolívar” iron-ore deposits.

**1) Stretching vibration of O-H groups:** The first spectral band detected in the ore from “Los Barrancos” deposit is located in a frequency range of 3588  $\text{cm}^{-1}$  to 2861  $\text{cm}^{-1}$ , while for the ore from “Cerro Bolívar” deposit, is between 3603  $\text{cm}^{-1}$  and 2765  $\text{cm}^{-1}$ . Both values are associated with stretching vibrations of the O-H bonds [17]. This band is very sensitive to the dehydroxylation temperature, and is one of the most important bands to be considered for the characterization of the thermal transformation process of goethite [14].

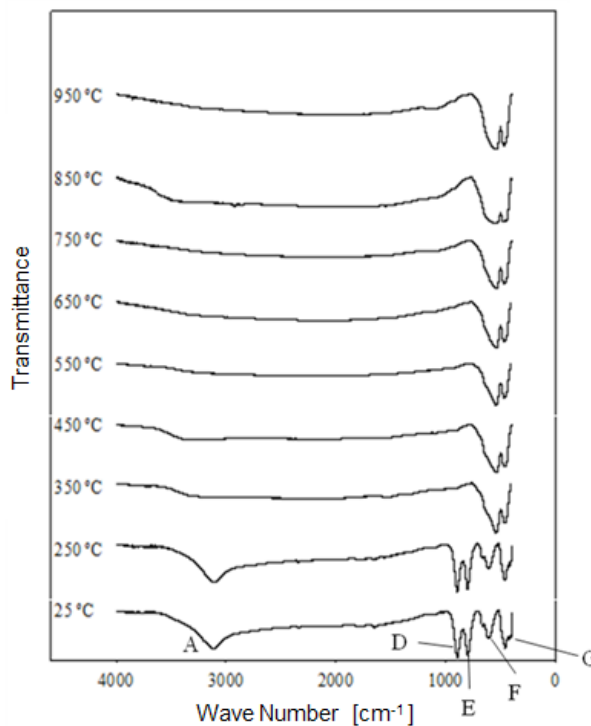


FIG. 8. Modification of the infrared spectrum of iron ore from “Los Barrancos” deposit, after being heat treated at different temperatures for one hour. 25 °C refers to the sample without heat treatment.

The position of this center band moves toward higher wave numbers as the calcination temperature increases until reaching 350 °C, since at temperatures above this value, the band stops showing peak shape to become a small shoulder that disappears above 450 °C, in the case of the “Los Barrancos” ore (Fig. 8), and above 650 °C, in the case of the “Cerro Bolívar” ore (Fig. 9). The first displacement of this band occurs at 250 °C, suggesting the beginning of the structure alteration (from goethite to hematite), and as the band moves further, the energy of the hydrogen bonds decreases [16], due to the increase in the angle formed by the atoms in the O-H...O bond inside of the atomic arrangement of the mineral [13]. This occurs because some of the atoms of the crystal lattice are attracted to neighboring OH ions, which results in a weakening of the hydrogen bond that connects the OH ions to the crystal lattice [16].

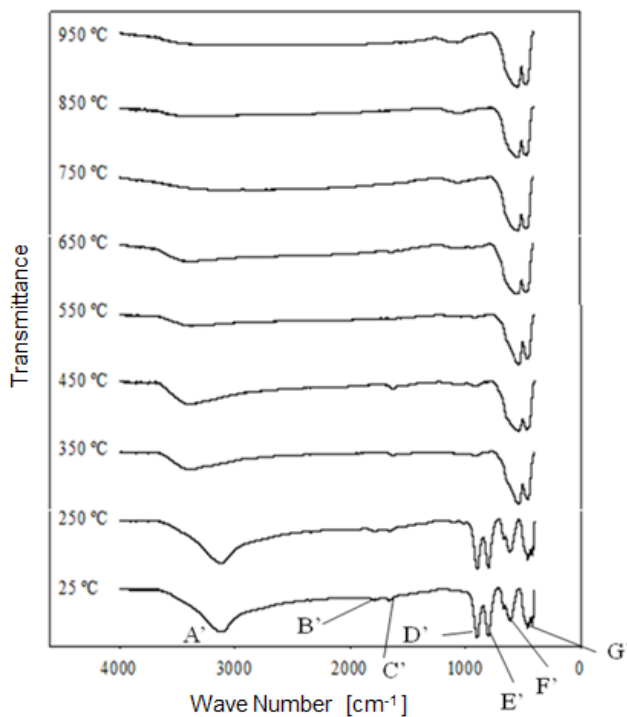


FIG. 9. Modification of the infrared spectrum of iron ore from “Cerro Bolívar” deposit, after being heat treated at different temperatures for one hour. 25 °C refers to the sample without heat treatment.

Between room temperature and 350 °C, in addition to the band displacement, there is a decrease in its intensity and bandwidth, which is a characteristic change that occurs when the hematite structure has

been completely formed [14]. However, this structure will retain an excess of OH groups, which generates a shoulder-shaped signal in this area of the spectrum that will not disappear until higher calcination temperatures are reached [14].

**2) Bending vibrations of the O-H groups:** The region between 1840  $\text{cm}^{-1}$  and 1615  $\text{cm}^{-1}$  (Fig. 8 and 9) shows two small bending bands associated with water, which are designated as  $\delta'(\text{OH})$  and  $\gamma'(\text{OH})$ . The lowest intensity observed in the bending bands is due to the fact that they have low sensitivity when are irradiated using infrared light [17]. On the other hand, the behavior of these bands during the dehydration process is equivalent to that shown by stretching and strain vibrations of the hydroxyl groups [14, 17]. Similarly, such bending bands are no longer present in the infrared spectra after calcination at 350 °C (Fig. 8 and 9).

**3. Deformation vibrations of the O-H groups:** The spectrum range between 978  $\text{cm}^{-1}$  and 852  $\text{cm}^{-1}$  shows two very marked bands that correspond to the deformation of the hydroxyl groups, and are called  $\delta(\text{OH})$  and  $\gamma(\text{OH})$ . The division of these bands is the result of the two different ways in which hydroxyl groups that are not part of the mineral stoichiometry may be deformed [17]. These bands, called D, E and D', E' respectively, have a shape similar to a “W” (Fig. 6 and 7), which is characteristic of goethite [12, 18]. The first one, the d(OH) band, is attributed to the atomic vibration in the mirror plane of the goethite (plane a-b), while the second one, the g(OH) band, is essentially related to the vibrations occurring outside of this plane [17]. The axes corresponding to the goethite structure are presented in figures 10, 11, and 12.

The resulted spectra show that these bands exist in the original state of the ore, and at the dehydroxylation temperature of 250 °C (Fig. 8 and 9). In addition, there is no significant change in the displacement of the band centers, which is related to the fact that there is no change in the distance or bonding energy of the functional groups, compared to the bands associated with stretching vibrations [17]. On the other hand, the early disappearance of these bands with respect to the others is due to the fact that the hydroxyl groups can be released easily from the goethite planes, since its structure is usually more defective; these structural defects contain more OH groups, which favors the release of hydroxyls during calcination [17].

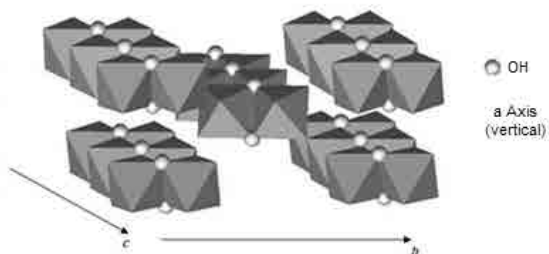


FIG. 10. Axes a, b, and c of the goethite [8]. Double octahedron chains are indicated. The unmarked vertices of the octahedron correspond to oxygen

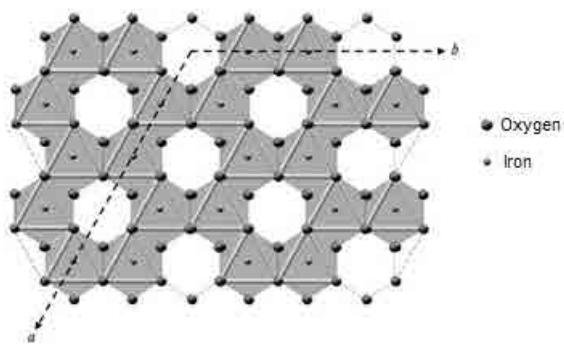


FIG. 11. Axes a and b of the hematite [8]. An octahedral vacancy is indicated for every two octahedrons of Fe<sup>3+</sup> in the center

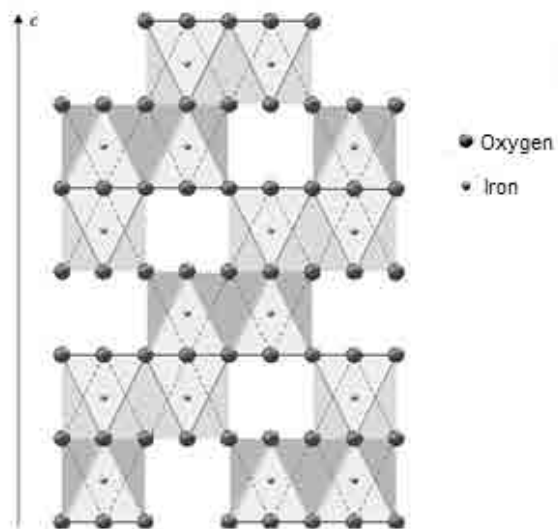


FIG. 12. The c axis of the hematite [8]. The position of the octahedrons is indicated

**4) Own vibrations of hematite:** The characteristic bands of hematite, between 650 cm<sup>-1</sup> and 406 cm<sup>-1</sup>, are related to the Fe-O vibration within the crystal structure of iron oxides and oxyhydroxides. In the studied ores, these bands were observed at lower frequencies. The first ones that appeared in the spectra are attributed to the vibration of the Fe-O bond in the a-plane of the hematite, while the others are associated with the vibrations of such bond in the plane c of the hematite (Fig. 11 and 12).

In general, the bands associated with plane a are not very defined in the goethite infrared spectrum [12]. However, their appearance in the spectrum from the untreated samples is attributed to the fact that the studied iron ores are composed of a mixture of goethite and hematite (Fig. 4 and 5). The largest change observed in the spectra of figures 8 and 9 occurred between 250 °C and 350 °C, which corroborates the explanation that the above range corresponds to the structural transition temperature [12, 14], during which goethite is converted into hematite. Additionally, in this area of the spectrum, a displacement to lower frequencies of the band related to the hematite plane c was observed; such a displacement occurred due to the appearance of a new hematite phase after calcination [14]. For both limonitic iron ores, above 350 °C, the band center associated with the planes a and c of the hematite remained in the same position as the treatment temperature increased, which indicates that there is no change in the Fe-O bond distance in the newly formed hematite structure [17].

#### IV. CONCLUSIONS

Limonitic iron ores of the “Los Barrancos” and “Cerro Bolívar” deposits exhibited a decrease in mass due to the loss of both free and structural water (chemically bound or in the form of OH groups), after being submitted to a calcination heat treatment at different temperatures between 250 °C and 950 °C.

After characterizing samples using X-Ray diffraction, it was found that a modification of the mineral structure occurs between 250 °C and 350 °C. The structure, which was constituted of two mineralogical phases (goethite and hematite), was completely transformed into hematite as a result of the calcination process at temperatures above 350 °C.

The results obtained using FTIR spectroscopy showed a similar range of transformation to that obtained by X-Ray diffraction. At temperatures above 350°C, a modification occurred in the infrared spectra, exhibiting the disappearance of the stretching and deformation bands of the OH groups, the disappearance of the water bending bands, and the displacement of Fe-O vibrations (of the hematite axis c) toward lower frequencies. However, despite the transformation of phases to hematite, the transformed ore still maintained a certain amount of OH groups, even at higher calcination temperatures.

Obviously, such structural modifications facilitate the mass loss manifested during the calcination process. In this respect, one advantage is that the mass loss occurred during calcination of iron ores prior to the reduction process could reduce the amount of charge introduced into reactors during the production process, and could facilitate the production of a more reactive ore during the reduction process.

### ACKNOWLEDGEMENTS

The authors wish to thank M. Sc. Mariángel Berroterán for creating the illustrations shown in figures 10, 11, and 12.

### AUTHORS' CONTRIBUTIONS

Pedro Delvasto conceived the work and designed the experiments, drafted and revised the manuscript, and prepared the final version. Lisbeth Longa Avello worked on the FTIR and DRX data acquisition and analysis, as well as in revising the manuscript on its final version. Cristina Pereyra Zerpa was responsible for the thermogravimetric analyses. Julio Andrés Casal Ramos worked on XRD data acquisition and analysis, and revising the manuscript.

### REFERENCES

[1] H. Kokal, M. Singh, and V. Naydyonov, "Removal of phosphorus from Lisakovsky by roast-leach process," in *Electrometallurgy and Environmental Hydrometallurgy*, C. Young et al., Eds. Hoboken, NJ, USA: The Minerals, Metals and Materials Society, 2003, vol. 2. DOI: <http://doi.org/10.1002/9781118804407.ch33>.

[2] P. Palacios, A. Bustamante, P. Romero-Gómez, and J. González, "Kinetic study of the thermal

transformation of limonite to hematite by X-ray diffraction,  $\mu$ -Raman and Mössbauer spectroscopy," *Hyperfine Interact*, vol. 203 (1-3), pp. 113-118, Nov. 2011. DOI: <http://doi.org/10.1007/s10751-011-0352-2>.

[3] K. Ionkov, S. Gaydardzhiev, D. Bastin, A. Correa, and M. Lacoste, "Removal of phosphorous through roasting of oolitic iron ore with alkaline earth additives," in *XXVI International Mineral Processing Congress*, pp. 2194-2205, 2012.

[4] J. Li, K. Bunney, H. Watling, and D. Robinson, "Thermal pre-treatment of refractory limonite ores to enhance the extraction of nickel and cobalt under heap leaching conditions," *Minerals Engineering*, vol. 41, pp. 71-78, Feb. 2013. DOI: <http://doi.org/10.1016/j.mineng.2012.11.002>.

[5] E. Núñez, E. Jaimes, and J. Castillo, "Reducibility and mineralogy types of the fine iron ore for fluid bed direct reduction process," in *5th IAS Ironmaking Conference*, pp. 267-276, 2005.

[6] E. Gariglio, D. Oliveira, W. Mafra, C. Silva, and D. Correa, "Evaluation of iron ore value in use for DR/EAF processes – CVRD experience," in *5th IAS Ironmaking Conference*, pp. 277-285, 2005.

[7] K. Jang, V. Nunna, S. Hapugoda, A. Nguyen, and W. Bruckard, "Chemical and mineral transformation of a low grade goethite ore by dehydroxylation, reduction roasting and magnetic separation," *Minerals Engineering*, vol. 60, pp. 14-22, Jun. 2014. DOI: <http://doi.org/10.1016/j.mineng.2014.01.021>.

[8] R. Cornell, and U. Schwertmann, *The Iron Oxides: Structure, Properties, Reactions, Occurrences and Uses*, 2nd ed. Weinheim, Germany: WILEY-VCH Verlag GmbH & Co, 2003. DOI: <http://doi.org/10.1002/3527602097>.

[9] I. Mitov, D. Paneva, and B. Kunev, "Comparative study of the thermal decomposition of iron oxyhydroxides," *Thermochimica Acta*, vol. 386 (2), pp. 179-188, Apr. 2002. DOI: [http://doi.org/10.1016/S0040-6031\(01\)00808-5](http://doi.org/10.1016/S0040-6031(01)00808-5).

[10] F. Honglei, S. Baozhen, and L. Qiaoxia, "Thermal behavior of goethite during transformation to hematite," *Materials Chemistry and Physics*, vol. 98 (1), pp. 148-153, Jul. 2006. DOI: <http://doi.org/10.1016/j.matchemphys.2005.09.005>.

[11] V. Balek, and J. Subrt, "Thermal behaviour of iron(III) oxide hydroxides," *Pure and Applied Chemistry*, vol. 67 (11), pp. 1839-1842, Jan. 1995. DOI: <http://doi.org/10.1351/pac199567111839>.

[12] J. Boily, J. Szanyi, and A. Felmy, "A combined FTIR and TPD study on the bulk and surface dehydroxylation and decarbonation of synthetic goethite," *Geochimica et Cosmochimica Acta*, vol. 70 (14), pp. 3613-3624, Jul. 2006. DOI: <http://doi.org/10.1016/j.gca.2006.05.013>.

[13] Y. Cudennec, and A. Lecerf, "Topotactic transformations of goethite and lepidocrocite into hematite and maghemite," *Solid State Sciences*, vol. 7 (5), pp. 520-529, May. 2005. DOI: <http://doi.org/10.1016/j.solidstatedsciences.2005.02.002>.

- [14] H. Ruan, R. Frost, and J. Klopogge, "The behavior of hydroxyl units of synthetic goethite and its dehydroxylated product hematite," *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy*, vol. 57 (13), pp. 2575-2586, Nov. 2001. DOI: [http://doi.org/10.1016/S1386-1425\(01\)00445-0](http://doi.org/10.1016/S1386-1425(01)00445-0).
- [15] M. Landers, and R. Gilkes, "Dehydroxylation and dissolution of nickeliferous goethite in New Caledonian lateritic Ni ore," *Applied Clay Science*, vol. 35 (3-4), pp. 162-172, Feb. 2007. DOI: <http://doi.org/10.1016/j.clay.2006.08.012>.
- [16] E. Wolska, "Relations between the existence of hydroxyl ions in the anionic sublattice of hematite and its infrared and X-ray characteristics," *Solid State Ionics*, vol. 28-30 (2), pp. 1349-1351, Sep. 1988. DOI: [http://doi.org/10.1016/0167-2738\(88\)90385-2](http://doi.org/10.1016/0167-2738(88)90385-2).
- [17] H. Ruan, R. Frost, J. Klopogge, and L. Duong, "Infrared spectroscopy of goethite dehydroxylation: III. FT-IR microscopy of in situ study of the thermal transformation of goethite to hematite," *Spectrochim Acta A Mol Biomol Spectrosc*, vol. 58 (5), pp. 967-981, Mar. 2002. DOI: [http://doi.org/10.1016/S1386-1425\(01\)00574-1](http://doi.org/10.1016/S1386-1425(01)00574-1).
- [18] P. Prasad, K. Shiva Prasad, V. Krishna Chaitanya, E.V.S.S.K. Babu, B. Sreedhar, and S. Ramana Murthy, "In situ FTIR study on the dehydration of natural goethite," *Journal of Asian Earth Sciences*, vol. 27 (4), pp. 503-511, Sep. 2006. DOI: <http://doi.org/10.1016/j.jseaes.2005.05.005>.