

BASIC RESEARCH

DOI:

Received:
20-VIII-2019

Effect of Polishing Systems on Fluoride Release and Surface Roughness of Different Restorative Materials

Accepted:
13-IX-2019

Published Online:
27-IX-2019

El efecto de los sistemas de pulido en la liberación de flúor y rugosidad de diferentes materiales restauradores

Soner Şişmanoğlu DDS, PhD¹; Burak Gümüştas DDS, PhD²;
Zuhal Yıldırım-Bilmez DDS, PhD³

1. Department of Restorative Dentistry, Faculty of Dentistry, Altınbaş University, Istanbul, Turkey.
2. Department of Restorative Dentistry, Faculty of Dentistry, Istanbul Medipol University, Istanbul, Turkey.
3. Department of Restorative Dentistry, Faculty of Dentistry, Hatay Mustafa Kemal University, Istanbul, Turkey.

Correspondence to: Dr. Soner Şişmanoğlu - soner.s@hotmail.com

ABSTRACT: Secondary caries is an important factor in the replacement of the restorations, and it is thought that fluoride-releasing materials may prevent this problem. Furthermore, the fluoride release of the materials may be increased by polishing process. Available knowledge about the effect of polishing systems (PS) on the fluoride release of materials is limited. Therefore, this study was conducted to evaluate the effect of PS on the fluoride release of fluoride-containing materials. Restorative materials were divided into 6 groups: Fuji IX GP, Fuji II, Dyract XP, Beautifil II, Beautifil-Bulk, and Filtek Ultimate. Each group was also divided into four subgroups: Mylar strip, Sof-Lex Discs, Sof-Lex Diamond, and OneGloss. Fluoride release was determined using a fluoride ion-selective electrode. Surface roughness was evaluated with a profilometer. Two-way repeated measure and one-way ANOVA tests were used for statistical analysis. The initial rapid fluoride release was observed only in Fuji IX. The PS increased the fluoride release of Fuji IX and Fuji II and Dyract XP materials while reducing the fluoride release of resin-based materials. The highest surface roughness values were obtained with OneGloss. Further, a significant relationship between fluoride release and surface roughness was found. The polishing provides an increase in fluoride release, especially in glass-ionomer-based materials. This article revealed that there is a relationship between fluoride release and surface roughness. Proper PS must be chosen according to the material to provide the best clinical benefits in terms of fluoride release and surface roughness.

KEYWORDS: Compomers; Composite resins; Dental materials; Fluorides; Glass ionomer cements.

RESUMEN: La caries secundaria es un factor importante para el reemplazo de restauraciones y se considera que los materiales que liberan flúor pueden prevenir este problema. Además, la liberación de fluoruro de estos materiales podría incrementarse mediante el proceso de pulido. El conocimiento disponible sobre el efecto de los sistemas de pulido (SP) en la liberación de fluoruro de los materiales es limitado. Por lo tanto, este estudio se realizó para evaluar el efecto de los SP sobre la liberación de fluoruro de materiales que contienen fluoruro. Los materiales de restauración se dividieron en 6 grupos: Fuji IX GP, Fuji II, Dyract XP, Beautifil II, Beautifil-Bulk y Filtek Ultimate. Cada grupo también se dividió en cuatro subgrupos: Banda Mylar, Discos Sof-Lex, Sof-Lex Diamond y OneGloss. La liberación de fluoruro se determinó usando un electrodo selectivo de iones fluoruro. La rugosidad de la superficie se evaluó con un perfilómetro. Se utilizaron medidas repetidas bidireccionales y pruebas ANOVA de una vía para el análisis estadístico. La liberación inicial rápida de fluoruro se observó solo en Fuji IX. El SP aumentó la liberación de fluoruro de los materiales Fuji IX y Fuji II y Dyract XP al tiempo que redujo la liberación de fluoruro de los materiales a base de resina. Los valores más altos de rugosidad de la superficie se obtuvieron con OneGloss. Además, se encontró una relación significativa entre la liberación de fluoruro y la rugosidad de la superficie. El pulido proporciona un aumento en la liberación de fluoruro, especialmente en materiales a base de ionómero de vidrio. Este artículo reveló que existe una relación entre la liberación de fluoruro y la rugosidad de la superficie. El SP adecuado debe elegirse de acuerdo con el material para proporcionar los mejores beneficios clínicos en términos de liberación de fluoruro y rugosidad de la superficie.

PALABRAS CLAVE: Compómeros; Resinas compuestas; Materiales dentales; Fluoruros; Cementos de ionómero de vidrio.

INTRODUCTION

Glass-ionomer cements (GICs), also known as polyalkenoate cements, take their names from an acid base reaction between fluoride-containing aluminosilicate glass and polyalkenoic acid (1). They have been widely used and continuously developed since they emerged. The most important features of this material are that they provide moisture tolerance, have a coefficient of thermal expansion similar to dentin and have fluoride release, consequently anticariogenic properties (2). Some studies have reported that fluoride release from GICs makes demineralization of the surrounding dentin or enamel slower and may support the remineralization of lesions near the restoration wall (3,4). The calcium fluoroaluminosilicate

glass of GICs reacts with a polyacid to release the fluoride ions. This release constitutes the protective and therapeutic effect of GICs and cause no adverse effects on the physical properties of the material (5). However, sensitivity to early moisture contamination, inadequate compressive strength, low wear resistance and fracture toughness are disadvantages of GICs (6,7). Furthermore, there are some studies suggesting that insufficient physical properties of the GICs are associated with an increased fluoride release (8). Therefore, it is still ongoing to investigate materials that maintain both physical properties and that can make a long-term fluoride release (9).

The most important factor in the failure and replacement of restorations is secondary caries

(10,11). It is thought that restorative materials that release fluoride may prevent or reduce this problem (12). In recent years, the use of fluoride-releasing materials has rapidly increased for the restoration of cavities and core build-ups (13). Other fluoride-releasing restorative materials than glass-ionomer are: resin-modified GICs, polyacid-modified composite resins (compomers), giomers, fluoride-containing composite resins and fluoride-releasing resin cements. These resin-based restorative materials have different fluoride sources (14,15), varying depending on the composition, solubility and permeability of the resin matrix in resin-based materials, as well as the source and concentration of the fluoride (15,16). On the other hand, finishing and polishing procedures are essential for the clinical success of restorations (17). The aesthetics and longevity of dental restorations are closely related to the quality of surface integrity and smoothness. The increased surface roughness may facilitate biofilm formation (18). In addition, a positive correlation was observed between surface roughness and bacteria adhesion (19) that support periodontal diseases, secondary caries, surface staining and disturbances due to the retention of bacterial plaques. (20,21). Furthermore, fluoride release may be increased by finishing and polishing of the outermost layer of the compomers (23). However, there are limited numbers of studies on the effects of polishing systems on the fluoride release of fluoride-containing materials (23,24). Therefore, the aim of this study is to evaluate the effects of two polishing systems on the fluoride release ability during a 28-day period and surface roughness of different restorative materials. The null hypothesis of this in vitro study is that the polishing system has no statistically significant effect on the amount of fluoride release.

MATERIALS AND METHODS

SPECIMEN PREPARATION

Six different restorative materials were included in this in vitro study. The compositions and manufacturers of the tested materials are given in Table 1. Disc shaped specimens were prepared for each restorative material tested (N=408). The specimens were prepared 5 mm in diameter and 2 mm thick for fluoride release tests (n=168) and 8 mm in diameter and 2 mm thick for the surface roughness tests (n=240). The test materials were loaded into a standard Teflon® mold and pressed between two opposing Mylar strips; they were then covered with a 1 mm thick glass slide to remove excess material and to obtain a smooth material surface. The conventional GIC specimens were allowed to auto-polymerize for 10 minutes. All other restoratives were light cured (1750 mW/cm², Elipar Deep Cure, 3M ESPE) according to manufacturers' instructions. After the completion of the setting, the specimens were removed from the molds. The specimens used for the surface roughness test were kept in deionized water at 37°C for 24 hours before the polishing.

The prepared specimens were randomly divided into four subgroups according to the polishing system employed (Table 2). Mylar strip used as a control group. The specimens in the treatment group were wet-ground with 1200-grit silicon carbide paper for 60 seconds using a polishing machine (MetaServ, Buehler, IL, USA) at 600 rpm under water-cooling to standardize samples before the polishing process, and then the specimens were polished with low-speed handpiece as described in Table 2.

MEASUREMENT OF FLUORIDE RELEASE

All specimens were transferred to polyethylene vials containing 3 ml of deionized water, separately ($n=7$). The solutions were kept in incubator at 37°C and thoroughly shaken at the time of the readings. The first measurement of the fluoride concentration was performed at 24 hours after the specimen preparation. After the reading, each sample was rinsed with 1 mL of deionized water and transferred to a new vial filled with 3 mL of fresh deionized water. Following the first measurement, fluoride measurement was repeated on days 2,3,4,5,6, 7,14,21 and 28. The fluoride concentration in these samples was analyzed using a fluoride ion selective electrode (9609 BN, Orion Research). The instrument (Orion 720A+) calibrated in accordance with the manufacturer's recommendations using six standard fluoride solutions containing 0.20, 1.00, 2.00, 10.00, 20.00 and 100 ppm F, respectively. Before measurement, 0.4 ml of TISAB III (940911, Orion Research) was added to each solution to provide constant background ionic strength. Then, the concentration of the specimens was calculated in parts per million (ppm) for comparison.

MEASUREMENT OF SURFACE ROUGHNESS

The surface was evaluated using a surface analyzer (Surtronic 25, Taylor Hobson Limited, UK) to obtain average surface roughness. Each sample was measured at three indiscriminate areas and averaged to generate average roughness value ($n=10$), and were recorded in Ra, μm .

STATISTICAL ANALYSIS

The means and standard deviations of the fluoride release and the Ra values were determined. Since the objective of this in vitro study not to make comparisons among different restorative materials, the fluoride release values of different materials were not compared with each other.

The fluoride release of the first week and weekly fluoride release was separately analyzed by two-way repeated measures ANOVA (factors: polishing and time). Surface roughness values were analyzed using one-way analysis of variance (ANOVA). Multiple comparisons were performed by the Tukey HSD test. The mean cumulative fluoride release within the 28 days for each material and the corresponding mean surface roughness were compared with the Spearman correlation test. All tests were performed by a statistical program (Prism 7, GraphPad Software, San Diego, CA, USA). Statistical differences at the $p<0.05$ level were considered statistically significant.

RESULTS

The fluoride release of materials and their comparisons according to the polishing system and to each other are presented in Table 3. The highest amounts were detected during the first days, tending to decrease with time (Figures 1-6). When the first seven-day release values are examined, it is observed that different polishing methods have a significant effect on the amount of fluoride release ($p>0.05$). The polishing process increased the fluoride release of Fuji IX GP and Fuji II LC and Dyract XP materials while reducing the fluoride release of resin-based materials such as Beautifil II, Beautifil-Bulk and Filtek Ultimate ($p>0.05$). For the first three days, the fluoride release values of Fuji IX GP were almost doubled by the use of the polishing system.

A significant decrease was observed in the fluoride release of Fuji IX GP, Fuji II LC and Dyract XP materials after the first week, while the decrease in fluoride release of other materials was significant after the second week ($p>0.05$) (Table 3). Two-way repeated measures ANOVA revealed that time and polishing were statistically significant factors in fluoride release for all tested materials ($p>0.05$). Fluoride release of Fuji IX GP, Fuji II LC and Dyract

XP materials reached a constant threshold after the second week and no statistically significant difference was found between the third and fourth weeks ($p > 0.05$). When the fluoride release was evaluated cumulatively, Fuji IV GP released more fluoride than other materials, while the least fluoride release was observed in Filtek Ultimate ($p < 0.05$).

SURFACE ROUGHNESS

Mean Ra values and standard deviations of six different restorative materials after different polishing systems are displayed in Table 4. Sof-Lex Discs polishing system in Fuji IX GP and Beautifil-

Bulk groups produced less roughness than other polishing systems ($p < 0.05$). In the Fuji II LC, Dyract XP, Beautifil II and Filtek Ultimate groups, there was no significant difference between Sof-Lex Discs and Sof-Lex Diamond. The highest surface roughness values of all other materials were obtained with OneGloss polishing system. There were no statistically significant differences between Sof-Lex Diamond and OneGloss for all groups, ($p > 0.05$) except for Fuji IV.

The Pearson's correlation coefficient of 0.745 indicates a strong positive correlation between 28-day cumulative fluoride release and surface roughness ($r = 0,745$; $p < 0.05$).

Table 1. Material type, composition and manufacturer of the materials used.

Material	Type	Composition and inorganic filler ratio
Fuji IX GP GC Tokyo, JAPAN	GIC	Polyacrylic acid, fluoroaluminosilicate glass, polybasic carboxylic acid. Particle size: 10 µm. (70–80%).
Fuji II LC, GC Tokyo, JAPAN	Resin-modified GIC	Alumino-fluorosilicate glass, polyacrylic acid, 2- hydroxyethylmethacrylate, 2,2,4-trimethyl hexamethylenedicarbonate, triethylene glycol dimethacrylate. Particle size: 5.9 µm.
Dyract XP, Dentsply, DeTrey, Konstanz, Germany.	Polyacid-modified composite resin (compomer)	UDMA, carboxylic acid modified dimethacrylate, TEGDMA, trimethacrylate resin (TMPTMA), dimethacrylate resins, camphorquinone, ethyl-4 (dimethylamino) benzoate, butylated hydroxy toluene (BHT), strontium-alumino-sodium-fluoro phosphor-silicate glass, highly dispersed silicon dioxide, strontium fluoride, iron oxide pigments and titanium oxide pigments. Particle size: 0.8 µm. (73 wt.%, 47 vol%).
Beautifil II, Shofu, Kyoto, JAPAN	Giomer	BISGMA, TEGDMA, inorganic glass filler, aluminium oxide, silica, prereacted glass-ionomer filler, camphoroquinone. Particle size: 0.8 µm, (83 wt.% 68.6 vol%).
Beautifil-Bulk, Shofu, Kyoto, JAPAN	Giomer	Bis-GMA, UDMA, Bis-MPEPP, TEGDMA, S-PRG filler based on fluoroboroaluminosilicate glass, polymerization initiator. (87.0 wt.%, 74.5 vol%).
Filtek Ultimate, 3M ESPE, St Paul, MN, USA	Nanofill composite	Bis-GMA, UDMA, TEGDMA, poly(ethylene glycol) dimethacrylate (PEGDMA), Bis-EMA. (72.5 wt.%, 55.6 vol%). Particle size: 20 nm silica particles, 4 - 11 nm zirconium particles.

Bis-EMA: ethoxylated bisphenol-A dimethacrylate, Bis-GMA: Bisphenol A-glycidyl methacrylate, Bis-MPEPP: 2, 2'-Bis (4-Methacryloxy Polyethoxyphenyl), TEGDMA: Triethylene glycol dimethacrylate, UDMA: Urethane dimethacrylate, wt.%: weight percentage, vol%: volume percentage.

Table 2. Composition and application method of the polishing systems used.

Polishing System	Composition	Application Method
OneGloss, Shofu Inc., Kyoto, JAPAN.	One-step olyvinylsiloxane finisher and polisher are mounted on mandrels (Al ₂ O ₃ , SiO ₂)	OneGloss midi-points (ISO #060) were applied with light pressure on the discs for 20 s at low speed (10,000 rpm). The surfaces were then rinsed for 10 s.
Sof-Lex Discs, 3M ESPE, St. Paul, MN, USA.	Aluminum oxide-coated disc. Medium 40 µm, Fine 24 µm, Ultrafine 8 µm.	The specimens were wet-polished with medium, fine and super-fine grits for 20 s at low speed (10,000 rpm).
Sof-Lex Diamond, 3M ESPE, St. Paul, MN, USA.	Elastomer impregnated with aluminum oxide particles (25–29 µm).	Firstly, Sof-Lex medium discs were applied the surfaces of specimens. A beige Sof-Lex Diamond finishing wheel was applied with light pressure for 20 s at low speed (10,000 rpm). Then, a white Sof-Lex Diamond polishing wheel was applied with light pressure for 20 s at low speed (10,000 rpm). The surfaces were rinsed for 10 s after each wheel used.

Table 3. Fluoride release patterns of test materials (ppm ± SD).

	Week 1	Week 2	Week 3	Week 4
Fuji IX GP				
Mylar Band	24.32 ± 6.13 ^{aA}	5.37 ± 0.52 ^{aB}	1.81 ± 0.18 ^{ac}	1.58 ± 0.17 ^{ac}
S-Lex Disc	39.66 ± 3.20 ^{bA}	6.41 ± 0.48 ^{abB}	2.01 ± 0.36 ^{abc}	1.78 ± 0.22 ^{ac}
S-Lex Diamond	39.94 ± 2.18 ^{bA}	7.48 ± 1.67 ^{bB}	2.22 ± 0.24 ^{bcc}	2.19 ± 0.40 ^{bc}
One Gloss	43.81 ± 1.89 ^{bA}	7.64 ± 1.69 ^{bB}	2.40 ± 0.21 ^{cc}	2.26 ± 0.09 ^{bc}
Fuji II LC				
Mylar Band	20.82 ± 0.83 ^{aA}	5.68 ± 0.31 ^{aB}	3.28 ± 1.07 ^{ac}	3.31 ± 0.20 ^{ac}
S-Lex Discs	26.83 ± 0.93 ^{bA}	6.83 ± 0.37 ^{bB}	4.43 ± 0.20 ^{bc}	3.68 ± 0.16 ^{abc}
S-Lex Diamond	29.18 ± 1.57 ^{cA}	6.89 ± 0.26 ^{bB}	4.49 ± 0.21 ^{bcc}	4.50 ± 1.45 ^{bc}
One Gloss	31.56 ± 1.22 ^{dA}	7.88 ± 0.38 ^{cB}	4.49 ± 0.21 ^{cc}	4.22 ± 0.21 ^{abc}
Dyract XP				
Mylar Band	10.40 ± 0.56 ^{aA}	4.01 ± 0.40 ^{aB}	1.62 ± 0.10 ^{ac}	1.95 ± 0.14 ^{aD}
S-Lex Discs	12.80 ± 0.72 ^{bA}	4.24 ± 0.72 ^{baB}	1.05 ± 0.18 ^{ac}	0.68 ± 0.11 ^{bD}
S-Lex Diamond	13.70 ± 0.71 ^{cA}	3.43 ± 0.33 ^{cB}	1.04 ± 0.14 ^{ac}	0.40 ± 0.11 ^{bD}
One Gloss	15.70 ± 0.99 ^{dA}	4.80 ± 0.47 ^{bB}	1.20 ± 0.15 ^{ac}	0.46 ± 0.08 ^{bD}
Beautifil II				
Mylar Band	6.70 ± 0.36 ^{aA}	6.69 ± 0.38 ^{aA}	3.83 ± 0.26 ^{aB}	2.99 ± 0.17 ^{ac}
S-Lex Discs	4.07 ± 0.34 ^{bA}	1.90 ± 0.30 ^{bB}	2.64 ± 0.28 ^{bc}	1.85 ± 0.16 ^{bb}
S-Lex Diamond	3.83 ± 0.38 ^{bcA}	1.49 ± 0.30 ^{bcB}	2.11 ± 0.38 ^{cc}	1.71 ± 0.15 ^{bb}
One Gloss	3.42 ± 0.14 ^{cA}	1.24 ± 0.14 ^{cB}	1.91 ± 0.07 ^{cc}	1.50 ± 0.05 ^{cB}
Beauti Bulk				
Mylar Band	5.88 ± 0.31 ^{aA}	5.79 ± 0.57 ^{aA}	3.30 ± 0.38 ^{aB}	2.82 ± 0.17 ^{ac}
S-Lex Discs	3.60 ± 0.23 ^{bA}	2.47 ± 0.24 ^{bB}	2.36 ± 0.22 ^{bb}	1.72 ± 0.12 ^{bc}
S-Lex Diamond	3.30 ± 0.20 ^{bA}	1.82 ± 0.22 ^{cB}	1.79 ± 0.09 ^{cB}	1.55 ± 0.04 ^{cc}
One Gloss	2.75 ± 0.15 ^{cA}	1.57 ± 0.18 ^{cB}	1.47 ± 0.05 ^{cB}	1.28 ± 0.03 ^{dcB}
F. Ultimate				
Mylar Band	2.95 ± 0.24 ^{aA}	2.85 ± 0.23 ^{aA}	1.73 ± 0.14 ^{aB}	0.60 ± 0.13 ^{ac}
S-Lex Discs	1.73 ± 0.11 ^{bA}	1.25 ± 0.14 ^{bB}	1.17 ± 0.08 ^{bb}	0.35 ± 0.03 ^{bc}
S-Lex Diamond	1.57 ± 0.08 ^{bcA}	0.98 ± 0.04 ^{cB}	0.92 ± 0.05 ^{cB}	0.31 ± 0.03 ^{bc}
One Gloss	1.40 ± 0.04 ^{cA}	0.87 ± 0.04 ^{cB}	0.80 ± 0.06 ^{cB}	0.28 ± 0.02 ^{bc}

*Different superscript: lowercase for each column and uppercase for each row imply significant difference according to the two-way repeated measures ANOVA and Tukey HSD ($p < 0.05$).

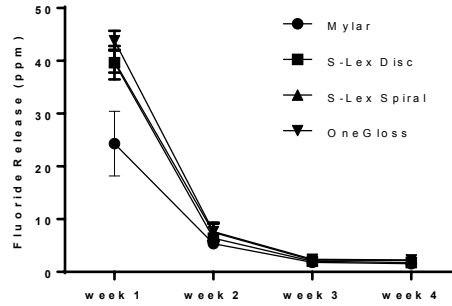
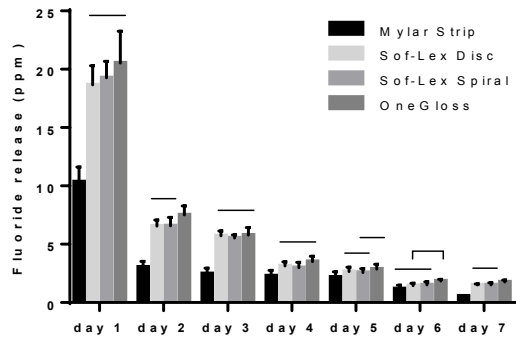


Figure 1. Mean fluoride release (ppm) of Fuji IV GP.

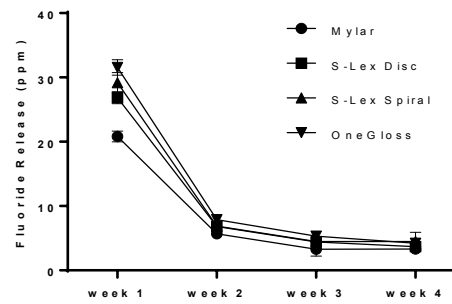
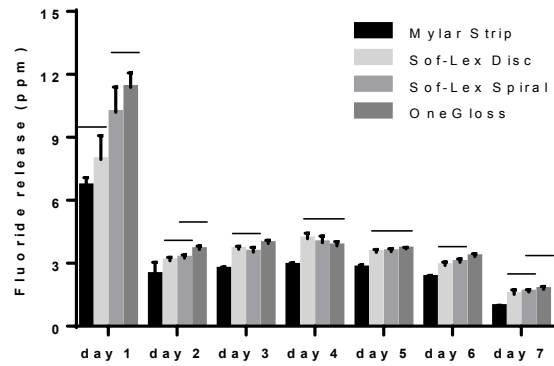


Figure 2. Mean fluoride release (ppm) of Fuji II LC.

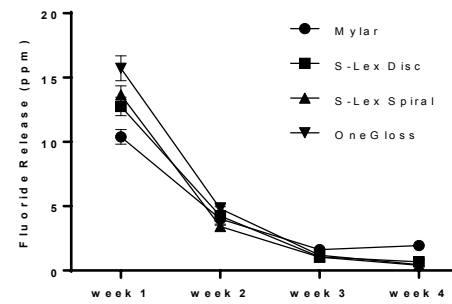
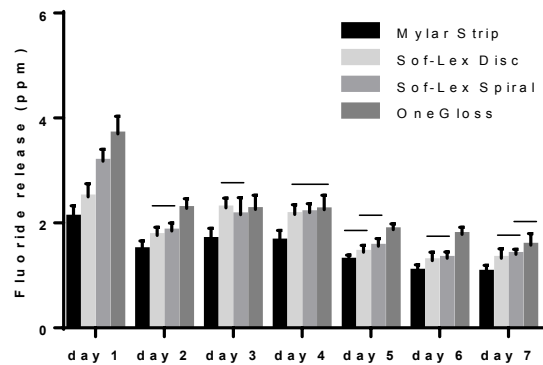


Figure 3. Mean fluoride release (ppm) of Dyract XP.

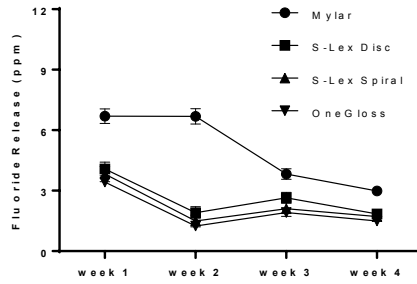
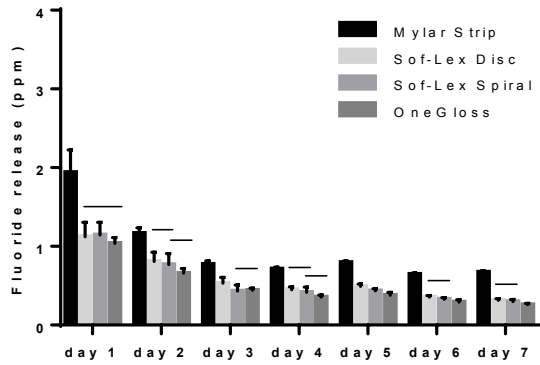


Figure 4. Mean fluoride release (ppm) of Beautifil II.

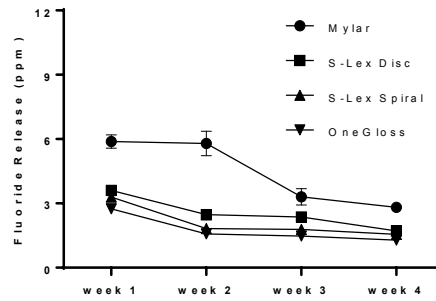
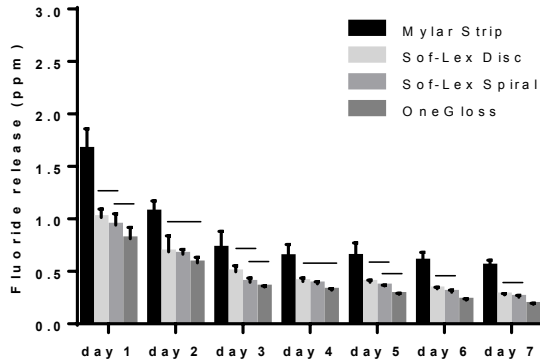


Figure 5. Mean fluoride release (ppm) of Beautifil Bulk.

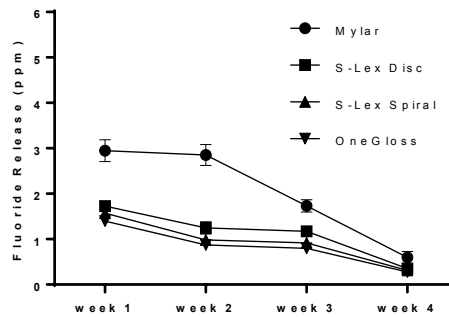
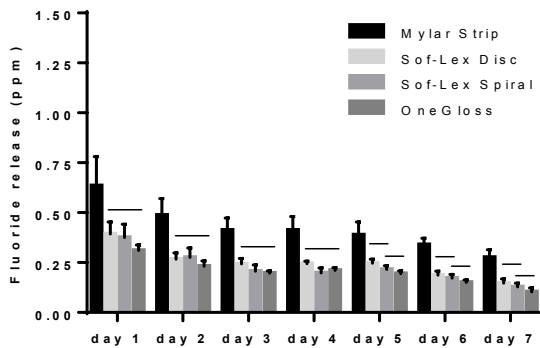


Figure 6. Mean fluoride release (ppm) of Filtek Ultimate.

Table 4. Surface roughness (Ra) values of the test materials ($\mu\text{m} \pm \text{SD}$).

	Mylar Band	S-Lex Discs	S-Lex Diamond	One Gloss
Fuji IX GP	0.131 \pm 0.011 ^{aA}	0.386 \pm 0.048 ^{aB}	0.438 \pm 0.045 ^{ac}	0.476 \pm 0.047 ^{ac}
Fuji II LC	0.066 \pm 0.012 ^{bA}	0.201 \pm 0.021 ^{bB}	0.218 \pm 0.024 ^{bB}	0.267 \pm 0,017 ^{bc}
Dyract XP	0,04 \pm 0,005 ^{cdA}	0,175 \pm 0,034 ^{bB}	0,158 \pm 0,013 ^{cdB}	0,206 \pm 0,018 ^{cc}
Beautifil II	0,029 \pm 0,004 ^{cA}	0,121 \pm 0,013 ^{cB}	0,125 \pm 0,010 ^{cB}	0,152 \pm 0,006 ^{dc}
Beauti Bulk	0,034 \pm 0,007 ^{cdA}	0,125 \pm 0,010 ^{cB}	0,141 \pm 0,004 ^{cdc}	0,166 \pm 0,010 ^{dd}
F. Ultimate	0,025 \pm 0,003 ^{cA}	0,080 \pm 0,006 ^{dB}	0,082 \pm 0,008 ^{dB}	0,153 \pm 0.028 ^{dc}

*Different superscript (lowercase for each column and uppercase for each row) imply significant difference according to one-way ANOVA and Tukey HSD ($p < 0.05$).

DISCUSSION

Finishing and polishing procedures are essential for the clinical success of restorations (17). Therefore, in our study, we aimed to evaluate the effects of different polishing systems on the fluoride release during the first week and weekly for 1 month. Surface roughness values were also analyzed. Considering the results of the study, both hypotheses of the authors were rejected. Both the restorative materials and the polishing systems used have affected surface roughness and fluoride release. In addition, a strong positive correlation between surface roughness and fluoride release was observed ($r=0,745$; $p < 0.05$).

The GICs show a rapid fluoride release as a result of the acid base reaction. This rapid fluoride release so called "burst effect" occurs on the surface of the material and markedly reduced after the first week. In many studies, particularly after the second week, the rate of fluoride release is slowed so that there is virtually no difference in fluoride elution between days (8,24-26). This "burst effect" phenomenon and subsequent threshold of constant fluoride release level was also consistent with the present study.

The fluoride elution of resin-modified GICs depends not only on the source of fluoride, but also on the type of resin monomer used (25,27,28). The setting of these materials initially begins with light-

activated polymerization and is followed by the acid base reaction in association with the sorption of water. Fuji II LC contains HEMA hydrophilic monomer, which could increase the water sorption to allow fluoride ion diffusion (29). Similarly, in our study, the more fluoride release was observed in the traditional GIC material in the first week, whereas in the following weeks a greater amount of fluoride was released in the resin-modified GIC material. This can be also attributed to the acid base reaction and hydrogel thickening resulting from the water absorption indicated in another study (30).

The amount of fluoride released from the compomer material is less than that of both conventional and resin-modified GIC in accordance with previous studies (29-31). Dyract XP produced a higher amount of fluoride release than resin-based composites. According to manufacturer information, Dyract XP contains strontium fluoride. In some studies, it was demonstrated that glass fillers and ytterbium trifluoride exhibited a superior fluoride release compared to strontium fluoride (28,31). The fluoride glass in the giomer has almost no glass-ionomer matrix, and there is a significant lack of acid base reaction since it has been pre-reacted. In contrast, the acid base reaction in compomers occurs due to the water absorption. The authors thought that this variation may be the reason for the difference of fluoride release between these two materials. Mousavinasab and

Meyers (25), similar to our study, reported that the fluoride release of giomers was lesser than the compomer material. However, in another study, the investigators did not find a significant difference between the fluoride release of giomers and compomers (24).

The smoothest surfaces are generally obtained by using the Mylar strip (24,32,33). Even if it has been applied successfully, it may be necessary to carry out finishing procedures in order to remove excess material or to obtain a good occlusal relationship. For this reason, in order to provide a standardization, the surface of the materials was polished using a 1200-grit silicon carbide paper with a polishing machine prior to polishing application to simulate finishing procedures(24,34). In our study, the smoothest surfaces were obtained in the Mylar strip group in accordance with many studies (24,32,33). The surface roughness of the materials was significantly increased with the application of polishing system ($p < 0.05$). The surface roughness of the resin-based materials is significantly lower than the GIC material ($p < 0.05$). On the other hand, there was no significant difference between the surface roughness of Beautifil II, Beautifil-Bulk and Filtek Ultimate materials in Mylar strip and OneGloss subgroups ($p > 0.05$). In giomers, Sof-Lex Discs and Diamond systems were showed no statistically significant difference in surface roughness ($p > 0.05$), while Filtek Ultimate showed a better polishability ($p < 0.05$).

As a result of the studies, a surface roughness of $0.2 \mu\text{m}$ is accepted as a threshold value for bacterial retention (35). In our study, the resin-based materials remained below this threshold. Only Dyract XP produced a surface roughness of $0.206 \mu\text{m}$ when polished with OneGloss. On the other hand, GIC-based materials have a surface roughness above $0.2 \mu\text{m}$ with all polishing systems. The lowest surface roughness in GIC-based materials was obtained with the Sof-Lex

Discs system. The flexible structure and the planar motion of these discs may be associated with low surface roughness values.

The effect of finishing and polishing systems on the fluoride release of restoration materials has so far been the subject of several studies (23,24,36). One of these studies stated that removal of the surface of the materials by air-abrasion increases the elution of fluoride. In the same study, this increase was related to the increase in surface roughness (23). In another study, it was found that different finishing and polishing systems were effective on fluoride release but no correlation was found (24). A positive correlation between surface roughness and fluoride release of materials was found in the present study. A significant increase was observed in the fluoride release of the material with the increase in surface roughness of GIC-based materials. The alterations in the surface of the material together with the polishing may have facilitated the penetration of the water required for the acid base reaction. On the other hand, polishing of resin-based materials (excluding compomer) reduced the fluoride release in accordance with the previous study (24).

Based on the results, it may be concluded that the polishing significantly increases the amount of fluoride release of restorative materials depending on the material type. Furthermore, a positive correlation was found between the surface roughness and fluoride release of the materials tested. However, it is important to remember that the correlation is not causality when interpreting the correlation. There may or may not be a causal link between the two related variables. Also, if there is a correlation, this may be indirect. The smoothest surfaces were obtained with Sof-Lex discs. Sof-Lex Diamond system may be used especially for surfaces where the discs are difficult to use due to the anatomy of the teeth in the posterior region. GIC-based materials have more fluoride release than resin-based materials when polished.

CONFLICT OF INTEREST

The authors have no conflict of interest relevant to this article.

REFERENCES

1. Karantakis P., Helvatjoglou-Antoniades M., Theodoridou-Pahini S., Papadogiannis Y. Fluoride release from three glass ionomers, a compomer, and a composite resin in water, artificial saliva, and lactic acid. *Oper Dent.* 2000; 25 (1): 20-5.
2. Kent B. E., Lewis B. G., Wilson A. D. Glass Ionomer Cement Formulations: I. The Preparation of Novel Fluoroaluminosilicate Glasses High in Fluorine. *J Dent Res.* 1979; 58 (6): 1607-19.
3. ten Cate J. M., van Duinen R. N. B. Hypermineralization of Dentinal Lesions Adjacent to Glass-ionomer Cement Restorations. *J. Dent Res.* 1995; 74 (6): 1266-71.
4. Hara A. T., Queiroz C. S., Freitas P. M., Giannini M., Serra M. C., Cury J. A. Fluoride release and secondary caries inhibition by adhesive systems on root dentine. *Eur J Oral Sci.* 2005; 113 (3): 245-50.
5. Anusavice K., Phillips R. Phillips' Science of Dental Materials. 11th ed. St. Louis, USA; W.B. Saunders; 2003.
6. Hewlett E. R., Mount G. J. Glass ionomers in contemporary restorative dentistry a clinical update. *J Calif Dent Assoc.* 2003; 31 (6): 483-92.
7. Khoroushi M., Keshani F. A review of glass-ionomers: From conventional glass-ionomer to bioactive glass-ionomer. *Dent Res J. (Isfahan).* 2013; 10 (4): 411-20.
8. Kavaloglu Cildir S., Sandalli N. Compressive strength, surface roughness, fluoride release and recharge of four new fluoride-releasing fissure sealants. *Dent Mater J.* 2007; 26 (3): 335-41.
9. Vermeersch G., Leloup G., Vreven J. Fluoride release from glass-ionomer cements, compomers and resin composites. *J Oral Rehabil.* 2001; 28 (1): 26-32.
10. Mjör I. A., Toffenetti F. Secondary caries: a literature review with case reports. *Quintessence Int.* 2000; 31 (3): 165-79.
11. D'Arcangelo C., Zarow M., De Angelis F., Vadini M., Paolantonio M., Giannoni M., et al. Five-year retrospective clinical study of indirect composite restorations luted with a light-cured composite in posterior teeth. *Clin Oral Investig.* 2014; 18 (2): 615-24.
12. Tam L. E., Chan G. P., Yim D. In vitro caries inhibition effects by conventional and resin-modified glass-ionomer restorations. *Oper Dent.* 1997; 22 (1): 4-14.
13. McCabe J. F., Walls A. Applied dental materials. 9th ed. Chicago, USA: Blackwell Pub; 2008.
14. Savarino L., Breschi L., Tedaldi M., Ciapetti G., Tarabusi C., Greco M., et al. Ability of restorative and fluoride releasing materials to prevent marginal dentine demineralization. *Biomaterials.* 2004; 25 (6): 1011-7.
15. Burke F. M., Ray N. J., McConnell R. J. Fluoride-containing restorative materials. *Int Dent J.* 2006; 56 (1): 33-43.
16. Pellizzari V., Michels A., Luiz S., de Souza E., Tabchoury C., Rached R. Fluoride Ion Release of Self-Adhesive Resin Cements and Their Potential to Inhibit In Situ Enamel and Dentin Demineralization. *Oper Dent.* 2017; 42 (5): 548-58.
17. Scheibe K.G.B.A., Almeida K.G.B., Medeiros I. S., Costa J. F., Alves C.M.C. Effect of different polishing systems on the surface roughness of microhybrid composites. *J Appl Oral Sci.* 2009; 17 (1): 21-6.
18. Wessel S. W., Chen Y., Maitra A., van den Heuvel E. R., Slomp A. M., Busscher H. J., et al. Adhesion forces and composition of planktonic and adhering oral microbiomes. *J Dent Res* 2014; 93: 84-8.
19. Aykent F., Yondem I., Ozyesil A. G., Gunal S. K., Avunduk M. C., Ozkan S. Effect of

- different finishing techniques for restorative materials on surface roughness and bacterial adhesion. *J Prosthet Dent* 2010; 103: 221-7.
20. McConnell M. D., Liu Y., Nowak A. P., Pilch S., Masters J. G., Composto R. J. Bacterial plaque retention on oral hard materials: Effect of surface roughness, surface composition, and physisorbed polycarboxylate. *J Biomed Mater Res A* 2010; 92: 1518-27.
 21. Kimyai S., Lotfipour F., Pourabbas R., Sadr A., Nikazar S., Milani M. Effect of two rophylox methods on adherence of *Streptococcus mutans* to microfilled composite resin and giomer surfaces. *Med Oral Patol Oral Cir Bucal* 2011; 16: e561-7.
 22. Heintze S. D., Forjanic M., Ohmiti K., Rousson V. Surface deterioration of dental materials after simulated toothbrushing in relation to brushing time and load. *Dent Mater* 2010; 26: 306-19.
 23. Jost-Brinkmann P. G. Effect of air polishing on the fluoride release of (resin-modified) glass ionomer cements and of a polyacid-modified composite resin. *Clin Oral Investig.* 1998; 2 (2): 91-5.
 24. Bayrak G. D., Sandalli N., Selvi-Kuvvetli S., Topcuoglu N., Kulekci G. Effect of two different polishing systems on fluoride release, surface roughness and bacterial adhesion of newly developed restorative materials. *J Esthet Restor Dent.* 2017; 29 (6): 424-34.
 25. Mousavinasab S. M., Meyers I. Fluoride release by glass ionomer cements, compomer and giomer. *Dent Res J (Isfahan).* 2009; 6 (2): 75-81.
 26. Neelakantan P., John S., Anand S., Sureshbabu N., Subbarao C. Fluoride Release From a New Glass-ionomer Cement. *Oper Dent.* 2011; 36 (1): 80-5.
 27. Rothwell M., Anstice H. M., Pearson GJ. The uptake and release of fluoride by ion-leaching cements after exposure to toothpaste. *J Dent.* 1998; 26 (7): 591-7.
 28. Hattab F. N., el-Mowafy O. M., Salem N. S., el-Badrawy W. A. An in vivo study on the release of fluoride from glass-ionomer cement. *Quintessence Int.* 1991; 22 (3): 221-4.
 29. Delbem A. C. B., Pedrini D., França J. G. M., Machado T. M. Fluoride release/recharge from restorative materials effect of fluoride gels and time. *Oper Dent.* 2005; 30 (6): 690-5.
 30. Tay F. R., Pashley E. L., Huang C., Hashimoto M., Sano H., Smales R. J., et al. The Glass-ionomer Phase in Resin-based Restorative Materials. *J Dent Res.* 2001; 80 (9): 1808-12.
 31. Yap A. U. J., Tham S. Y., Zhu L. Y., Lee H. K. Short-term fluoride release from various aesthetic restorative materials. *Oper Dent.* 2002; 27 (3): 259-65.
 32. Ehrmann E., Medioni E., Brulat-Bouchard N. Finishing and polishing effects of multiblade burs on the surface texture of 5 resin composites: microhardness and roughness testing. *Restor Dent Endod.* 2019; 44 (1).
 33. Ozel E., Korkmaz Y., Attar N., Karabulut E. Effect of one-step polishing systems on surface roughness of different flowable restorative materials. *Dent Mater J.* 2008; 27 (6): 755-64.
 34. Pala K., Tekçe N., Tuncer S., Serim M. E., Demirci M. Evaluation of the surface hardness, roughness, gloss and color of composites after different finishing/polishing treatments and thermocycling using a multitechnique approach. *Dent Mater J.* 2016; 35 (2): 278-89.
 35. Bollen C. M., Lambrechts P., Quirynen M. Comparison of surface roughness of oral hard materials to the threshold surface roughness for bacterial plaque retention: a review of the literature. *Dent Mater.* 1997; 13 (4): 258-69.
 36. McKnight-Hanes C., Whitford G. M. Fluoride Release from Three Glass Ionomer Materials and the Effects of Varnishing with or without Finishing. *Caries Res.* 1992; 26 (5): 345-50.



Attribution (BY-NC) - (BY) You must give appropriate credit, provide a link to the license, and indicate if changes were made. You may do so in any reasonable manner, but not in any way that suggest the licensor endorses you or your use. (NC) You may not use the material for commercial purposes.